

**Report No. CDOT-DTD-R-00-1**  
**Final Report**

## **PCCP Texturing Methods**

**Ahmad Ardani**  
**William (Skip) Outcalt**



**January 2000**

**COLORADO DEPARTMENT OF TRANSPORTATION  
RESEARCH BRANCH**

**2000-1**

1. Report No. CDOT-DTD-R-00-1	2. Government Accession No.	3. Recipient's Catalog No.	
4. Title and Subtitle PCCP Texturing Methods Project IR (CX) 070 - 4 (153)		5. Report Date January 2000	
		6. Performing Organization Code	
7. Author(s) Ahmad Ardani, Skip Outcalt		8. Performing Organization Report No. CDOT-DTD-R-00-1	
9. Performing Organization Name and Address  Colorado Department of Transportation 4201 E. Arkansas Ave. Denver, Colorado 8022		10. Work Unit No. (TRAIS)	
		11. Contract or Grant No.	
12. Sponsoring Agency Name and Address  Colorado Department of Transportation 4201 E. Arkansas Ave. Denver, Colorado 8022		13. Type of Report and Period Covered Final Report	
		14. Sponsoring Agency Code	
15. Supplementary Notes  Prepared in cooperation with the U.S. Department of Transportation, Federal Highway Administration			
16. Abstract  This report presents a 5- year evaluation and construction details of nine test sections with varying textural characteristics. Included in the report is an overview of the methodologies used to texture concrete pavement surfaces and a discussion of frictional attributes of various textures at different speeds and their impact on noise properties. Also included in the report are descriptions of texture-measuring devices and texture-installing equipment, a description of the state-of-the-art equipment used to acquire sound pressure levels, plus a thorough discussion of data acquisition/analysis.			
Frictional characteristics of the individual test sections were evaluated using the ASTM E 274 skid testing procedure. Ribbed-tire and smooth-tire friction tests were conducted to acquire skid numbers at three different speeds of 40, 50, and 65 mph. To examine the noise properties of the test sections, noise measurements were acquired to acoustically assess the impact of various surface textures at three different locations:  <ul style="list-style-type: none"> <li>• Inside the test vehicle</li> <li>• 25 feet from the center line (3 feet away from the right shoulder)</li> <li>• Near the right rear tire of the test vehicle, away from the exhaust pipe</li> </ul>			
Implementation  The results of this study indicated that longitudinal tining, in addition to possessing adequate frictional property, is easier to install and, more importantly, produces a much lower noise level than the traditional CDOT's transverse tining. CDOT has already adopted the longitudinal tining as a preferred method of texturing concrete pavements.			
17. Key Words  surface texture, tining frictional characteristics, skid numbers noise properties	18. Distribution Statement  No restriction: This report is available to the public through the National Technical Information Service, Springfield, VA 22161		
19. Security Classif. (of this report)	20. Security Classif. (of this page)	21. No. of Pages	22. Price

# PCCP Texturing Methods

by

Ahmad Ardani  
William (Skip) Outcalt

Report No. CDOT-DTD-R-00-1

Prepared by  
Colorado Department of Transportation  
Research Branch

Sponsored by the  
Colorado Department of Transportation  
In Cooperation with the  
U.S. Department of Transportation  
Federal Highway Administration

January 2000

Colorado Department of Transportation  
Research Branch  
4201 E. Arkansas Ave.  
Denver, CO 80222  
(303) 757-9506

## **ACKNOWLEDGEMENTS**

Special thanks are hereby expressed to the ACPA/CDOT Oversight Group for providing excellent comments and for their continued support. The members of the panel included: Mr. Steve Horton, Mr. Bernard Paiz, Mr. Greg Lowery, Mr. Hal Toland, and Mr. Dick Hines (CDOT - Staff Construction and Materials); Mr. Ken Wood (Region IV Materials); Mr. Sid Motchan (Region VI Materials); and Mr. Ron Youngman of the Colorado/Wyoming Chapter of ACPA.

The authors gratefully acknowledge Mr. Gerry Peterson, CDOT's Region I Materials Engineer, for all his support and valuable contribution. Mr. Peterson was instrumental in providing the study site and for conveying the details of the research experiment to the contractor and making sure that all the pieces of the puzzle fit together.

Our special thanks to the Project Engineer, Mr. Dennis Copeland and his staff, for coordinating and overseeing all the field activities. We also would like to express our sincere appreciation for all the expert help and support provided by Mr. Doyt Bolling (FHWA, Region 8), Mr. Carlton Hayden and Mr. Bradley Hibbs (FHWA, U.S. Department of Transportation).

The authors would also like to thank the Interstate Highway Construction (IHC) personnel, particularly Mr. Steve Vanoster and Cal Thomas for being so cooperative and responsive to the changes during construction.

## **EXECUTIVE SUMMARY**

This report presents the final results of the "PCCP Texturing Methods" research study, documenting the noise properties and the frictional characteristics of various concrete pavement textures. The report describes the testing and construction details of nine test sections with varying textural characteristics. Included in this report is an overview of the methodologies used to texture concrete pavement surface and a discussion of frictional attributes of various surface textures at different speeds and their impact on noise properties. Also included in the report is a description of the state-of-the-art equipment used to acquire sound pressure levels, texture-measuring devices and texture installing equipment, plus a discussion of data acquisition/analysis.

To evaluate the frictional characteristics of individual test sections, skid numbers were acquired according to ASTM E 274 skid testing procedure. Ribbed-tire (ASTM E 501) and smooth-tire (ASTM E 524) friction tests were conducted to obtain skid numbers at 40, 50, and 65 mph for all the test sections. Five skid resistance tests were conducted for each test section, as required by the standard ASTM procedure E 274. The arithmetic averages of the skid resistance tests were then used to indicate the skid number (SN) for individual test sections at a specified speed.

Review of the acquired data revealed a definite relationship between speed, types of surface texture, and the magnitude of skid numbers. As speed increased, the skid numbers declined. This relationship was clearly more pronounced and consistent using the smooth tire. Skid numbers acquired with the smooth tire clearly showed a distinct difference in magnitude for surfaces with macrotexture and microtexture. The difference in skid numbers for microtexture and macrotexture were not as evident or consistent using the ribbed-tire. This phenomenon confirmed the findings of many research papers, revealing the insensitivity of the ribbed-tire towards macrotexture.

Numerous texture-measuring devices provided by FHWA were used to quantitatively measure texture depth. The various methods used to measure the depth of textures included: Texture Van, Texture Beam with an LVDT and a Laser Stylus, Outflow Meter,

Tire Tread Gauge and the standard Sand-Patch Method. Explanations of these innovative techniques are presented in the body of the report.

Noise measurements were acquired as a joint effort between the CDOT's Research Branch and a local noise consultant, David L. Adams Associates, Inc. The primary purpose of the measurements was to acoustically assess the impact of various surface textures installed in the test sections. Sound pressure levels (SPL) were acquired at the following three locations:

- Inside the test vehicle
- 25 feet from the center line (3 feet away from the right shoulder)
- Near the right rear tire of the test vehicle, away from the exhaust pipe

The sound pressure levels generated at the control section were normalized to represent a datum (zero SPL), and were compared with SPL taken from other test sections.

Longitudinal macrotexture and microtexture were the most quiet surfaces based on the SPL taken at the shoulder, inside the test vehicle, and at the rear tire. State standard section (combination of uniform 1-inch spacing) exhibited the highest noise level among all the test sections, with the microphone at the rear tire position.

### **Implementation Statement**

The results of this study indicated that longitudinal tining, in addition to possessing adequate frictional properties, provides the following advantages over the traditional CDOT's standard transverse tining:

- ▶ Lower noise level
- ▶ Ease of installation
- ▶ Lower costs

CDOT has already adopted the longitudinal tining as a preferred method of texturing concrete pavements.

## TABLE OF CONTENTS

1.0 INTRODUCTION.....	1
2.0 BACKGROUND.....	5
3.0 OBJECTIVES.....	7
4.0 PCCP TEXTURING METHODS.....	8
4.1 Site Description.....	8
4.2 Construction of Test Sections.....	10
5.0 DATA ACQUISITION AND ANALYSIS.....	22
5.1 Frictional Data.....	22
5.2 Texture Measurement.....	27
5.2.1 Texture Van (Laser Van).....	27
5.2.2 Outflow Meter.....	31
5.2.3 Texture Beam.....	31
5.2.4 Sand Patch Method.....	32
5.2.5 Tire Gage.....	37
5.3 Noise Measurement.....	37
5.4 Roughness Data.....	43
6.0 CONCLUSIONS AND RECOMMENDATIONS.....	45
6.1 Conclusions.....	45
6.2 Recommendations.....	46
REFERENCES.....	48
APPENDIX A	
APPENDIX B	
APPENDIX C	

## **LIST OF PHOTOGRAPHS**

1. View of a Ribbed and a Smooth Tire.....	3
2. Application of Burlap Drag.....	11
3. View of the Longitudinal tining Assembly.....	11
4. Popcorn-like Mortar Balls Due to Longitudinal Tinning.....	12
5. Transverse Indentation .....	12
6. Application of Astro-turf Drag.....	14
7. Astro-turf Plugged-up with Grout.....	14
8. Application of Transverse Astro-turf.....	15
9. View of Installed Transverse Astro-turf Texture.....	15
10. Typical Transverse Tining Operation.....	16
11. 1" Uniform Spaced Transverse Tinning (State Standard).....	16
12. $\frac{1}{2}$ " Uniform Spaced Transverse tining.....	17
13. Random Transverse Tining .....	17
14. Installation of Longitudinal Grooves.....	19
15. Close-up View of Longitudinal Grooves.....	20
16. Grooved Rumble Strip in the Right Shoulder.....	20
17. Installation of Transverse Grooves.....	21
18. Close-up of Random Transverse Grooves.....	21
19. Inside of a Texture Van.....	30
20. View of an Outflow Meter.....	30
21. Texture Beam With an LVDT, and a Laser Stylus.....	34
22. Sand Patch Method of measuring texture depth.....	34
23. Tire Gage Method of Measuring Texture Depth.....	36
24. Sound Pressure Measurement at the Roadside.....	36
25. View of the Microphone Behind the Rear Tire.....	41
26. Acquiring Truck Noise Levels at the Roadside.....	41

## **LIST OF FIGURES**

1. Test Sections Location Map.....	6
2. Test Sections Layout.....	9
3. 1994 Ribbed-tire Skid Numbers at 40, 50 and 65 mph.....	23
4. 1994 Smooth-tire Skid Numbers at 40, 50 and 65 mph.....	23
5. Ribbed-tire Skid Numbers at 40 mph for 1994 through 1999.....	25
6. Smooth-tire Skid Numbers at 40 mph for 1994 through 1999.....	25
7. Ribbed-tire Skid Numbers at 65 mph for 1994 through 1999.....	26
8. Smooth-tire Skid Numbers at 65mph for 1994 through 1999.....	26
9. Speed Gradients Ribbed-tire Vs. Smooth-tire .....	28
10. Laser Van Root-Mean-Square Values (RMS).....	29
11. Indirect Texture Measurement (Outflow Meter).....	29
12. LVDT Beam, Average RMS.....	33
13. Laser Beam, Average RMS.....	33
14. Sand Patch Method, Average Texture Depth in Inches.....	35
15. Tire Gage, Average Texture Depth in Inches.....	35
16. Sound Pressure Levels At Shoulder.....	40
17. Sound Pressure Levels Inside Test Vehicle.....	40
18. Sound Pressure Levels At the Rear Tire.....	40
19. Comparison of Sound Pressure Levels For All the Test Sections.....	42
20. Comparison of Sound Pressure Levels (Car Vs. Semi-Truck).....	42
21. Profilograph Data (Inches Per Mile).....	44

## **1.0 INTRODUCTION**

Surface texture in rigid pavements plays an important role in providing safety (providing skid resistant surfaces) for the travelling public. The depth, spacing, and orientation (transverse or longitudinal) of the surface texture can significantly affect the frictional characteristics, noise properties, and quality of ride.

In general, transverse tining has been the only permitted method of texturing used by the Colorado Department of Transportation (CDOT) and the majority of the other transportation agencies. There are a few states that use longitudinal tining or sawing to texture their pavements on a regular basis and are quite satisfied with its performance. Among them is the State of California, which has continued to this date to longitudinally texture concrete pavements.

The frictional characteristics of the concrete pavement surface can be divided into two general groups: microtexture and macrotexture. Microtexture comes primarily from exposing the sand particles in the mortar (1), while macrotexture refers to grooves and channels formed in the plastic and/or in the hardened concrete. Forster (2), in the Transportation Research Record 1215, defines microtexture as those "surface asperities less than 0.5 mm in height and macrotexture as those with surface asperities of greater than 0.5 mm in height".

Macrotexture, with its channels and grooves, provides a drainage system that allows water to escape from under the tire, and consequently plays an important role in reducing the likelihood of hydroplaning. As discussed by the American Concrete Institute Committee (3), the term "hydroplaning" refers to the separation of tire contact from the pavement surface by a layer of water which causes loss of steering and braking control of the vehicle. This phenomenon is complex and is a function of water depth, vehicle speed, tire-inflation pressure, pavement texture and tire-tread depth and design.

The type and quality of fine aggregate used in a concrete mix plays an important role in


maintaining adequate skid resistance characteristics. As discussed in the FHWA Technical Advisory T 5050.17 (4), "regardless of the finishing or texturing method used, adequate durable skid resistance characteristics cannot be attained unless the fine aggregate has suitable wear and polish resistance characteristics."

Research by the Portland Cement Association indicates that the siliceous particle content of the fine aggregate should be greater than 25 percent in order to maintain longer lasting skid resistance characteristics. However, it should be noted that the presence of siliceous particles in a concrete mix might pose the possibility of alkali-silica reactions (ASR). Remedial measures should be taken to overcome the ASR reactions.

The most widely used method (indirect method) of acquiring frictional data (skid numbers) in the United States is the ASTM E 274 skid testing procedure with a ribbed tire (ASTM E 501). According to many of the papers reviewed on the subject of the skid testing, the ribbed tire lacks sensitivity to draining capability of pavement macrotexture, while it shows high sensitivity to pavement microtexture.

The primary reason for the ribbed tire's insensitivity to macrotexture is its deep grooves, which provide drainage for water regardless of pavement macrotexture. On the other hand, tests with the smooth tire (ASTM E 524) have produced skid-resistance data which are sensitive to both macrotexture and microtexture (5). Another advantage of using a smooth tire is that the influence of tire wear on the friction data is eliminated (6). Photograph 1 compares the ribbed and the smooth tires.

In general, skid numbers are acquired with a skid trailer by the ASTM method E 274 in the United States. These numbers are used by the states as guidelines for evaluating the frictional characteristics of pavements. However, as discussed in the National Cooperative Highway Research Program (NCHRP) Report Number 104, "no state establishes statutory requirements for

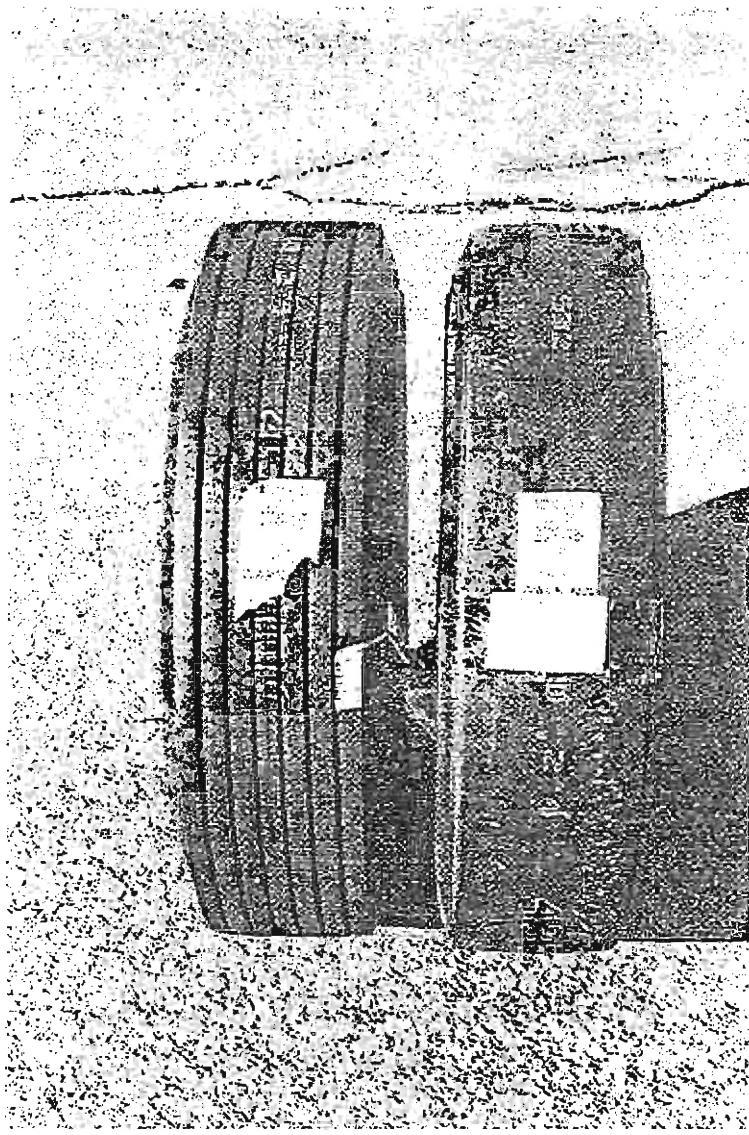

**Photo 1:** View of the ribbed tire (ASTM E 501 and  
The smooth tire (ASTM E524)

"minimum skid resistance" (7). Liability implications may be the primary reason for not establishing such statutory requirements for minimum skid resistance.

Reported skid number (SN) guidelines range from 30 to 40 for interstate highways and all highways with legal speeds in excess of 40 mph (65 km/h). Lower skid numbers are generally acceptable for urban areas where speed limits are less than 40 mph and for roads with the average daily traffic (ADT) of less than 3000 vehicles (7).

There are numerous direct methods available to quantitatively measure texture. Among the ones that were used for this study were: the texture van; the texture beam consisting of an LVDT (Linear Voltage Differential Transducer) and a commercial caser stylus; the outflow meter (indirect method); the tire tread depth gauge; and the standard sand patch test. A complete description of all these methods is presented in section 5.2.

The pavement surface texture not only impacts the frictional characteristics, but also plays a major role on the magnitude of the noise generated at the interface of the tire and pavement surface. To examine the noise characteristics of the various surface textures, noise data were acquired at the following three locations:

1. Inside the test vehicle
2. 25 feet from the center line (3 feet away from the right shoulder)
3. Near the right rear tire of the test vehicle away from the exhaust pipe

Noise data acquisition was conducted as a joint effort between the CDOT's Research Branch and a local noise consultant, David L. Adams Associates, INC. The test vehicle used was a 1994 Oldsmobile Cutlass Sierra station wagon provided by CDOT. A thorough analysis of the acquired noise data is presented in Section 5.3.

## **2.0 BACKGROUND**

There are a number of methods used to texture the surface of Portland cement concrete pavements. The effects of these texturing methods are not well defined. Some pavement engineers feel that texturing, especially formed when the concrete is in the plastic state, has an adverse effect on the long-term performance of rigid pavements. Some, on the other hand, believe that texturing plays an important role in providing a drainage system for the surface water and creating a skid resistant surface with adequate friction for the travelling public.


There is also the noise issue, both in the urban and rural areas. Some recent research papers have indicated that a change in the surface texture can have a profound effect on the traffic induced noise characteristics. Very little is known about the effectiveness of various texturing methods used by the Colorado Department of Transportation (CDOT) and other transportation agencies.

Questions have been raised regarding constructability, cost, and the performance of various surface textures in rigid pavements. What are the impacts of various texturing methods on the frictional characteristics, noise properties, and on the ride quality of the rigid pavements?

Based on the recommendations of the American Concrete Pavement Association (ACPA) and CDOT Oversight Group, and in an attempt to answer some of these questions, the Research Branch of CDOT in cooperation with Region I Materials, initiated a study to examine the pros and cons of various texturing methods.

The ultimate goal was to develop guidelines and specifications for future construction. To achieve the objectives of this study, nine test sections with various textures were installed on a stretch of Interstate 70, 50 miles east of Denver, Colorado (Figure 1). This final report describes the construction, data collection and data analysis for all the test sections.

Figure 1

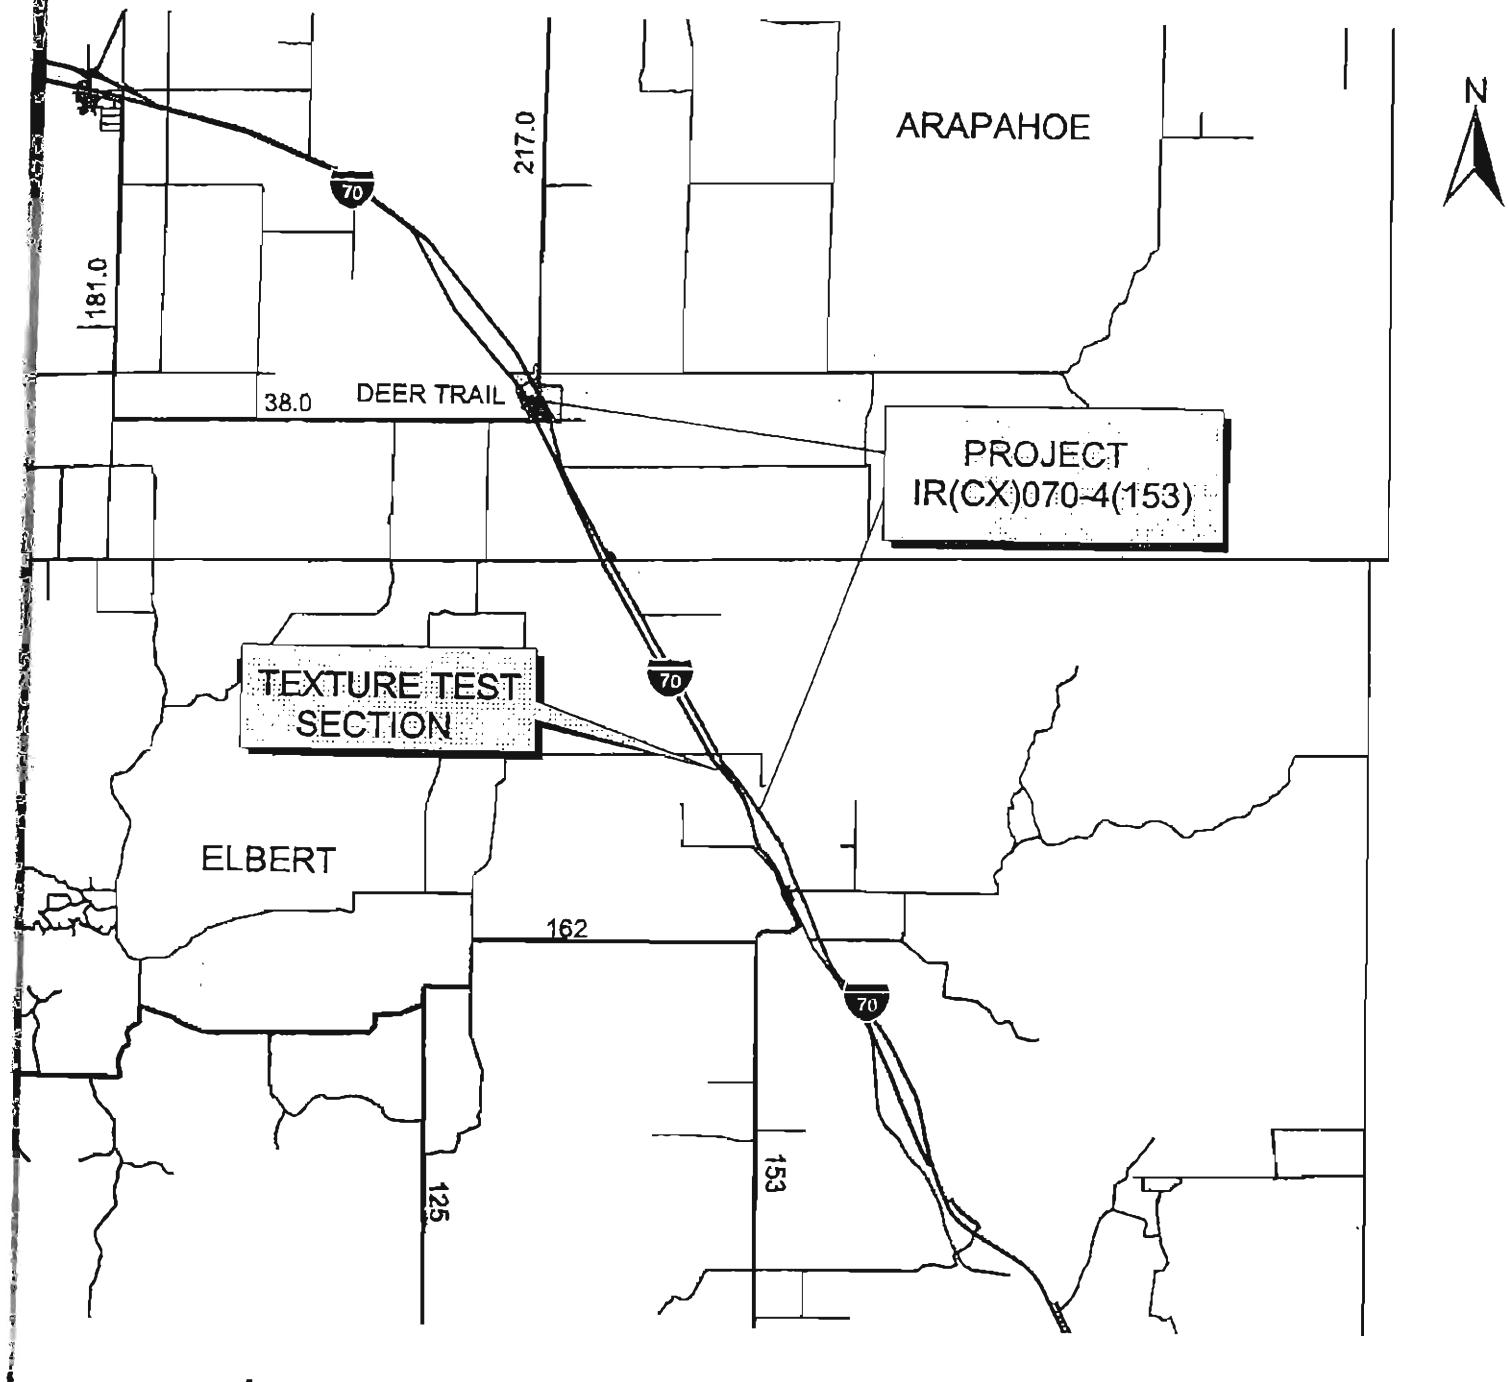

Date Produced: November 18, 1999

### **3.0 OBJECTIVES**

The primary objectives of this study were:

1. To document the constructability, costs, and the functional practicability of several PCCP surface textures installed on I-70 for the project IR (CX)70 - 4 (153) in Colorado.
2. To assess the long-term impacts of various surface textures on the frictional characteristics, noise properties, and the ride quality of concrete pavements.
3. To identify the best performing surface texture that is cost-effective, minimizes tire noise and provides adequate frictional characteristics over a long period.

## **4.0 PCCP TEXTURING METHODS**

### **4.1 Site Description**

The subject research site is located on I-70, "Project IR (CX) 070-4," approximately 60 miles east of Denver. It has an average daily traffic (ADT) of 6600 vehicles, with 40 percent of that consisting of heavy vehicles. The construction consisted of paving 10 miles of I-70 from Deer Trail East, beginning at about milepost 328. The 30-year design called for a full depth overlay of concrete Class P with a nominal thickness of 11 inches over the badly deteriorated existing concrete pavement.

The siliceous particle content of the fine aggregate was measured at approximately 96 percent using the ASTM test D 3042. This is well over the limit of 25 percent recommended by the Portland Cement Association, indicating a very polish resistant fine aggregate with very little carbonates. This divided four-lane interstate highway will receive an accumulated 18-K ESAL of 21,300,000 over the next 30 years.

The details of the concrete mix design, including the test results from the siliceous particle content of the fine aggregate, are presented in Appendix C. The following is the description of all the test sections:

<b>Stations</b>	<b>Texturing Method Used</b>	<b>Length in ft.</b>
1) 2715 - 2743	transverse tining 1"/ state standard	2800
2) 2743 - 2768	trans. astro-turf/ no tining	2500
3) 2768 - 2789	long. astro-turf/ trans. tining random	2100
4) 2789 - 2806	long. astro-turf/ trans. tining 1/2"	1700
5) 442 - 452	long. astro-turf/ trans. sawing random	1000
6) 452 - 480	long. astro-turf/ trans. tining 1"	2800
7) 480 - 490	long. astro-turf/ long. sawing 3/4"	1000
8) 490 - 500	long. astro-turf/ no tining	1000
9) 500 - 510	long. astro-turf/ long. tining 3/4"	1000

Figure 2  
 CONCRETE TEXTURING STUDY on I 70 at DEER TRAIL  
 TEST SECTION LAYOUT  
 (Length is to scale)

 <i>Direction of Travel (Eastbound)</i>	<table border="1" style="width: 100%; border-collapse: collapse;"> <tr><td style="padding: 5px;">Test #9</td><td style="padding: 5px;">Longitudinal Astroturf Drag 3/4" Longitudinal Tining</td></tr> <tr><td style="padding: 5px;">Test #8</td><td style="padding: 5px;">Longitudinal Astroturf Drag No Tining</td></tr> <tr><td style="padding: 5px;">Test #7</td><td style="padding: 5px;">Longitudinal Astroturf Drag 3/4" Longitudinal Saw Grooving</td></tr> <tr><td style="padding: 5px;">Test #6</td><td style="padding: 5px;">Longitudinal Astroturf Drag 1" Transverse Tining</td></tr> <tr><td style="padding: 5px;">Test #5</td><td style="padding: 5px;">Longitudinal Astroturf Drag Random Transverse Saw Grooving</td></tr> <tr><td style="padding: 5px;">Test #4</td><td style="padding: 5px;">Longitudinal Astroturf Drag 1/2" Transverse Tining</td></tr> <tr><td style="padding: 5px;">Test #3</td><td style="padding: 5px;">Longitudinal Astroturf Drag Random Transverse Tining</td></tr> <tr><td style="padding: 5px;">Test #2</td><td style="padding: 5px;">Transverse Astroturf Drag No Tining</td></tr> <tr><td style="padding: 5px;">Test #1</td><td style="padding: 5px;">State Standard 1" Transverse Tining</td></tr> </table>	Test #9	Longitudinal Astroturf Drag 3/4" Longitudinal Tining	Test #8	Longitudinal Astroturf Drag No Tining	Test #7	Longitudinal Astroturf Drag 3/4" Longitudinal Saw Grooving	Test #6	Longitudinal Astroturf Drag 1" Transverse Tining	Test #5	Longitudinal Astroturf Drag Random Transverse Saw Grooving	Test #4	Longitudinal Astroturf Drag 1/2" Transverse Tining	Test #3	Longitudinal Astroturf Drag Random Transverse Tining	Test #2	Transverse Astroturf Drag No Tining	Test #1	State Standard 1" Transverse Tining
Test #9	Longitudinal Astroturf Drag 3/4" Longitudinal Tining																		
Test #8	Longitudinal Astroturf Drag No Tining																		
Test #7	Longitudinal Astroturf Drag 3/4" Longitudinal Saw Grooving																		
Test #6	Longitudinal Astroturf Drag 1" Transverse Tining																		
Test #5	Longitudinal Astroturf Drag Random Transverse Saw Grooving																		
Test #4	Longitudinal Astroturf Drag 1/2" Transverse Tining																		
Test #3	Longitudinal Astroturf Drag Random Transverse Tining																		
Test #2	Transverse Astroturf Drag No Tining																		
Test #1	State Standard 1" Transverse Tining																		
	Begin Test Sta 2715+00 Approx. MP 335.3																		

Note: Burlap drag was applied to all test sections immediately behind the paver as shown in Photograph 2. The depth and the width of all the tining and sawing were specified at  $1/8" \pm 1/16"$ .

Figure 2 shows the sequence of the test sections as constructed.

#### **4.2 Construction of Test Sections**

The construction of the test sections began with paving the eastbound lanes from the east end westerly, beginning at station 510. The first test section (section 9) installed was textured with longitudinal astro-turf, followed by longitudinal tining. The tines were uniformly spaced at 3/4-inch intervals. To install longitudinal tining, the tining operator had to modify the tining equipment (bridge). The tining springs were assembled on the bottom of a steel truss, which in turn was secured to the bottom of the tining bridge.

Photograph 3 illustrates the entire tining assembly. Sensors at the four corners of the tining bridge were used to adjust the elevation and to achieve proper compression on the tining springs.

The tining-bridge was also used to drag astro-turf in the front and to apply curing compound from the back. During the installation of the longitudinal tining, the tines rolled the concrete paste (mortar) into popcorn-like balls all over the surface of the pavement (Photograph 4). However, once the concrete cured, these mortar balls were crushed by the traffic at the construction site and then easily removed by brooming.

Every time the tining operation was stopped, the tines formed a transverse indentation across the pavement surface as shown in Photograph 5. For future longitudinal tining, the contractor should be required to make provisions for raising the tines when the tining operation is stopped. This should prevent indentation of the plastic concrete surface.

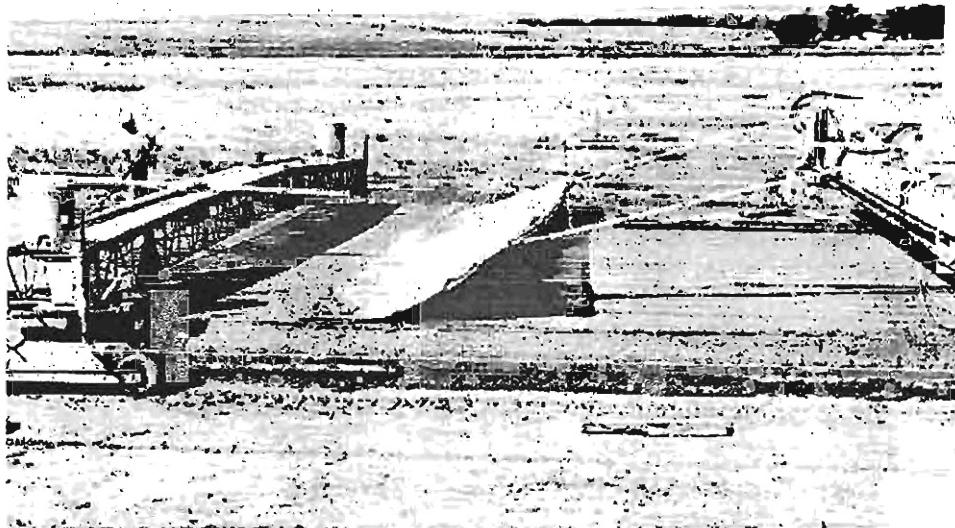


Photo 2: Application of burlap drag to all the test sections

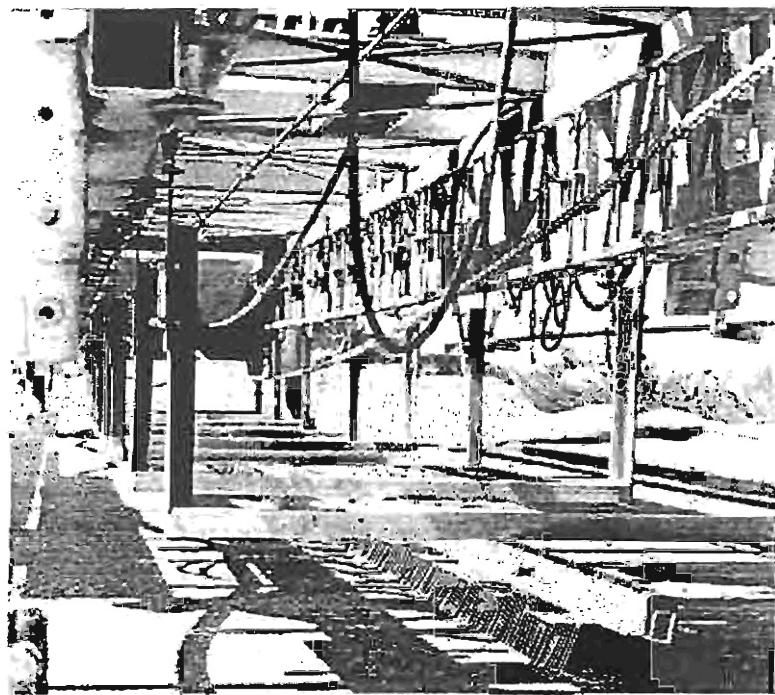


Photo 3: View of the longitudinal timing assembly

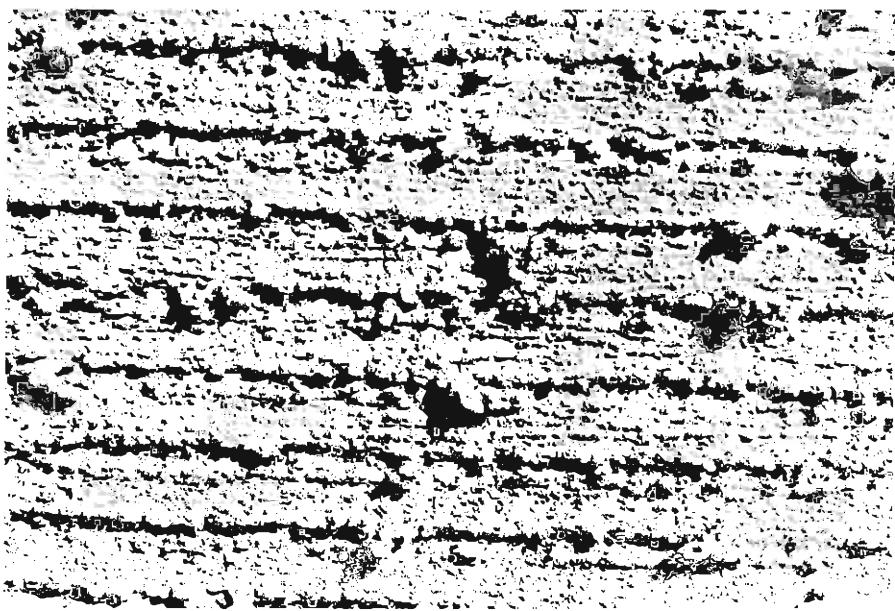


Photo 4: Popcorn-like mortar balls (longitudinal tining)

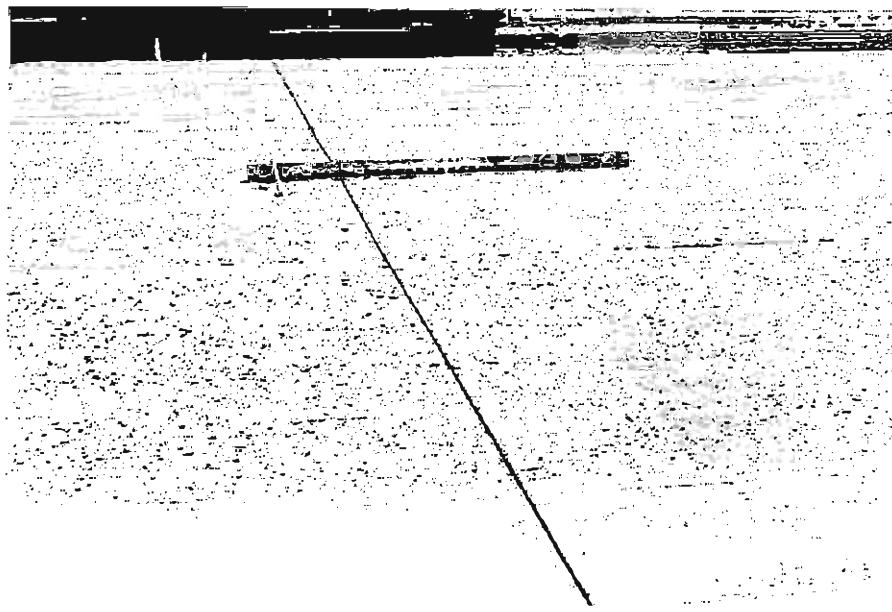


Photo 5: Transverse indentation of plastic concrete

The longitudinal astro-turf drag was applied from the front of the bridge simultaneously with longitudinal tining. The astor-turf used was 38 feet wide, covering the entire width of the pavement surface and 5.8 feet long, of which 4.8 feet contacted the surface. Due to a very stiff mix (slump of less than 1") the astro-turf was not capable of forming deep enough texture. To make the texturing more pronounced, several boards were placed on the astro-turf as shown in Photograph 6. Occasionally, the surface of the contact area became plugged with mortar (Photograph 7) and the tining operator had to raise the astro-turf and shake out the excess grout.

Photograph 8 shows the installation of transverse astro-turf texture. The set-up used was similar to that of transverse tining. A 12 foot wide, 2 foot long piece of astro-turf was folded in half and nailed to a 2" x 2" x 12 foot long pi  e of wood. The entire unit was then attached to the tining bridge in a manner similar to transverse tines.

Prior to installing transverse astro-turf test section the Principal Investigator (P.I), the Region I Materials Engineer, and the contractor met to discuss the possibility of encountering problems with the transverse texturing operation. It was decided to texture only the first 100 feet of the day's paving with this method to determine its feasibility and its possible continuation for the entire day's paving. If it was determined that transverse astro-turf was not adequately texturing the pavement surface, the contractor could then be directed to convert from transverse astro-turf texturing to longitudinal astro-turf texturing. However, as it can be seen in Photograph 9, the astro-turf adequately textured the pavement surface and as a result, transverse astro-turf texturing was continued for the entire day.

Photograph 10 shows a typical transverse tining operation. The state standard test section (control) which uses a combination of longitudinal burlap drag and 1" uniform transverse tining is shown in Photograph 11. Photograph 12 shows the combination of astro-turf drag with transverse tining of 1/2" uniform spacing. Transverse tining with random spacing of 5/8", 7/8" and 3/4" is shown in Photograph 13.

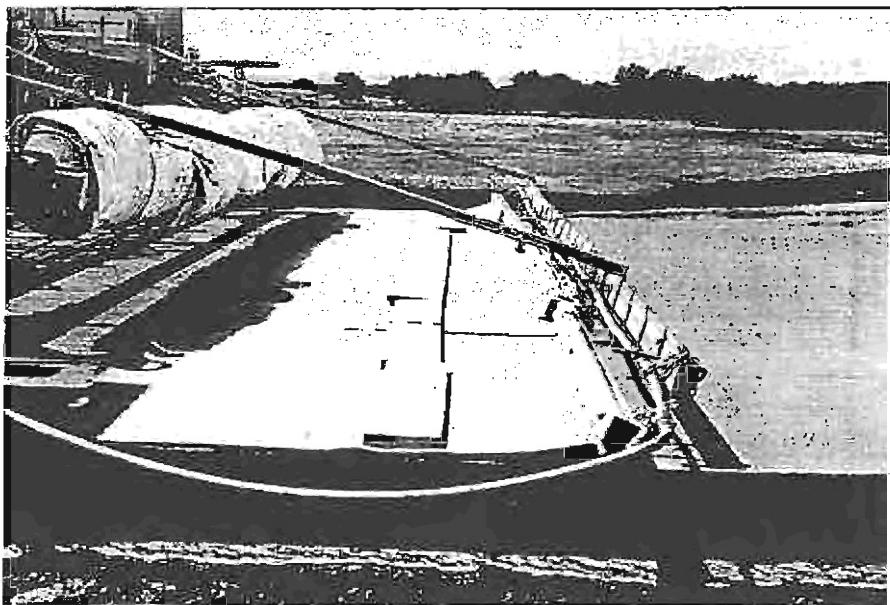


Photo 6: View of the astro-turf drag with planks for added weight

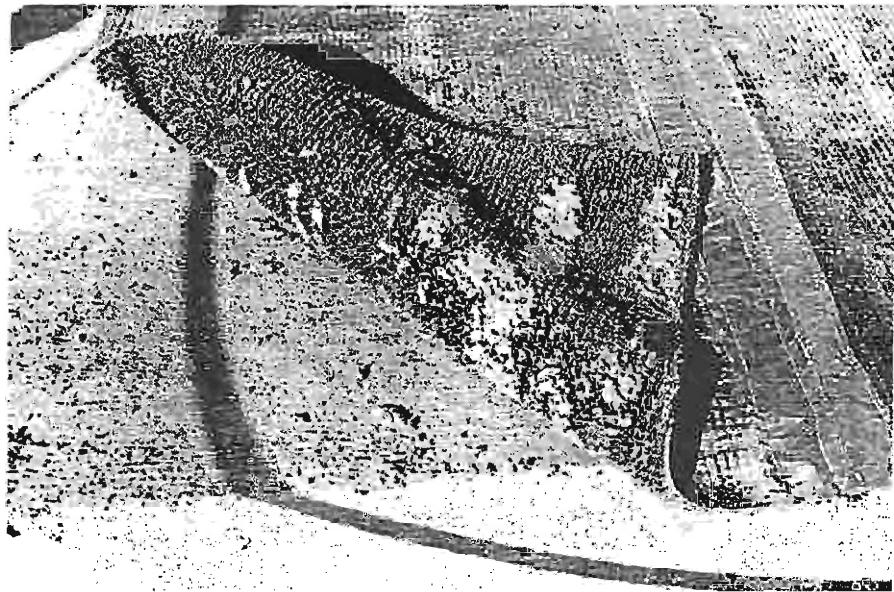


Photo 7: Astro-turf plugged up with grout

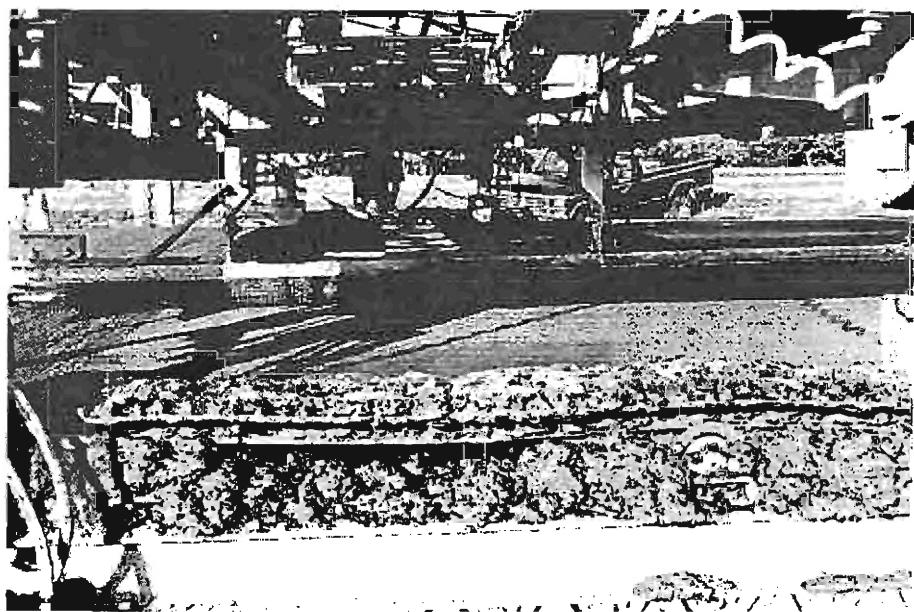


Photo 8: Installation of transverse astro-turf texture

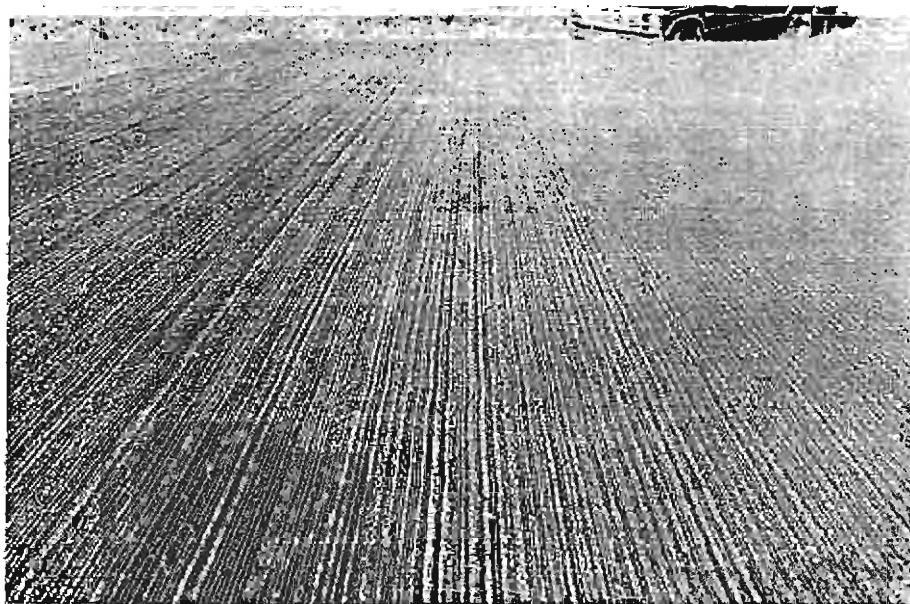


Photo 9: Close-up of transverse astro-turf texture

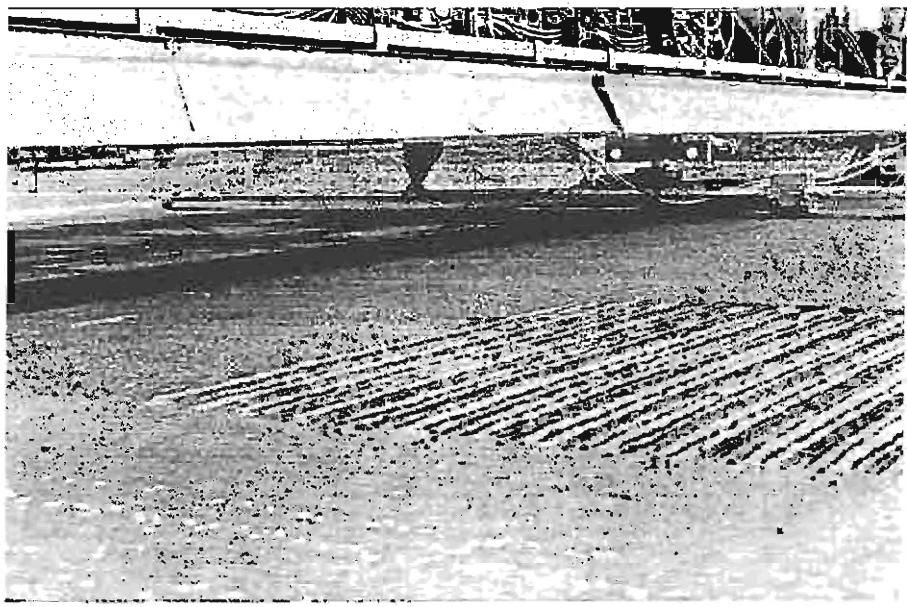


Photo 10: Typical transverse tining operation

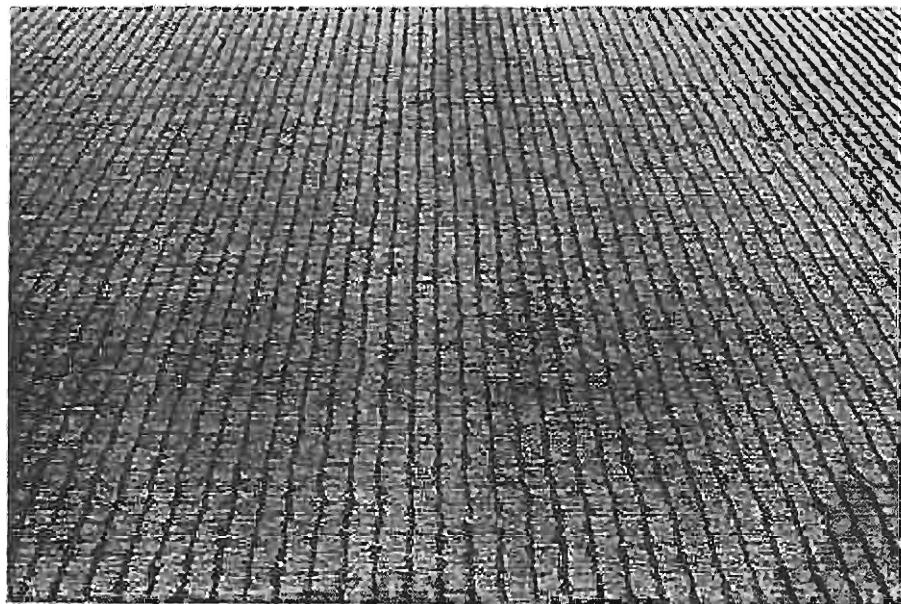


Photo 11: 1-inch uniform spaced transverse tining (state standard)

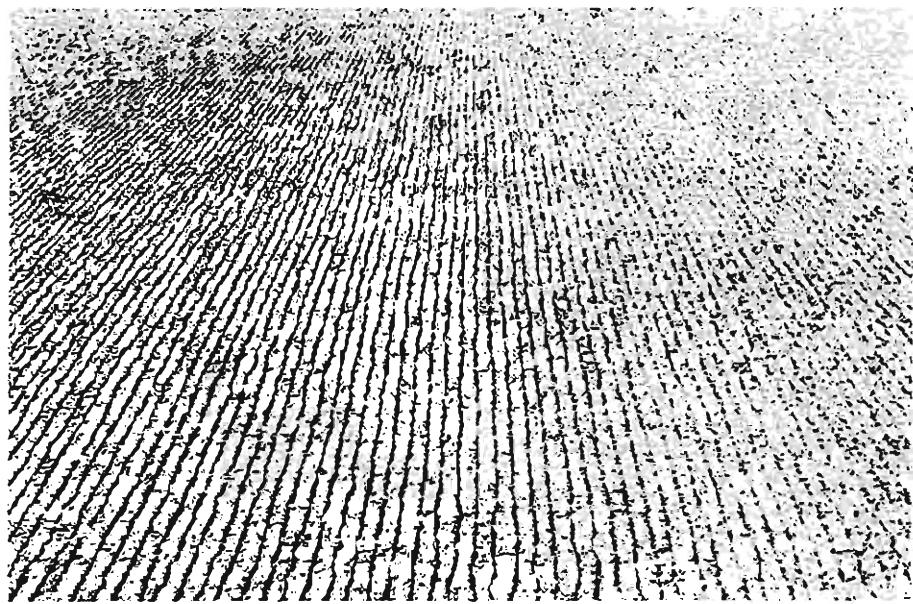


Photo 12: 1/2-inch uniform spaced transverse tining



Photo 13: Random transverse tining with 5/8", 7/8", and 3/4" spacing

A self-propelled sawing machine (CUSHIN CUT, HG-130) was used to install the longitudinal grooves with uniform spacing of 3/4 of an inch (Photograph 14). The grooving machine was equipped with 46 blades, 14 inches in diameter each, and had a total effective cutting width of 34-1/2 inches. The machine, which had an approximate cutting rate of 1000 linear feet per hour, required 12 passes to groove the entire test section. Photograph 15 shows a close-up view of the longitudinal grooving. The rumble strips on both the left and the right shoulders were also grooved. Photograph 16 shows a grooved rumble strip on the right shoulder.

A self-propelled Transverse Bridge Deck Groover (TBDG) was used to install the transverse grooves with random spacing of 5/8, 7/8, and 3/4 of an inch, as shown in Photograph 17. The transverse grooving machine was equipped with a moving head, with 38 blades, 14 inches in diameter each, and with a total effective cutting width of 29 inches. A close-up view of the transverse grooving is shown in Photograph 18.

In general, transverse and longitudinal grooving appeared orderly, and aesthetically more pleasing than transverse and longitudinal tining. However, the extra costs associated with these types of texturing may make them economically undesirable. Nevertheless, the longer life that can be achieved with grooved textures may offset their extra initial costs.

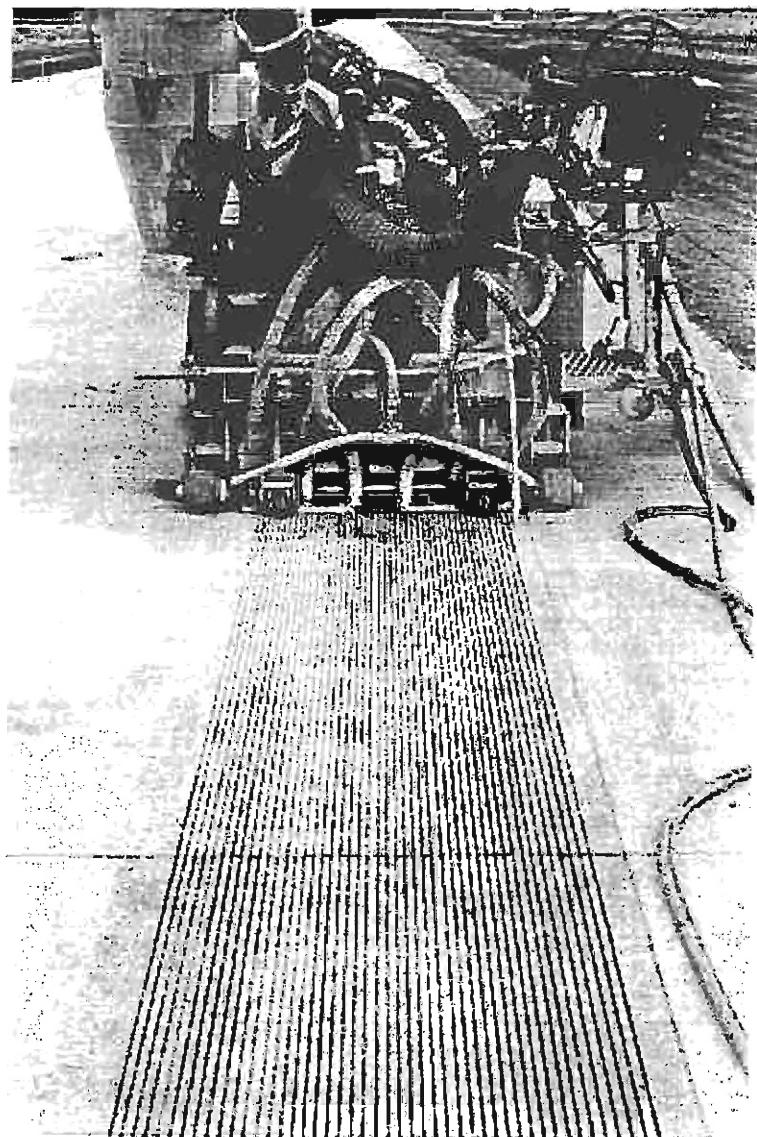


Photo 14: Installation of the longitudinal grooves



Photo 15: Close up view of longitudinal grooves

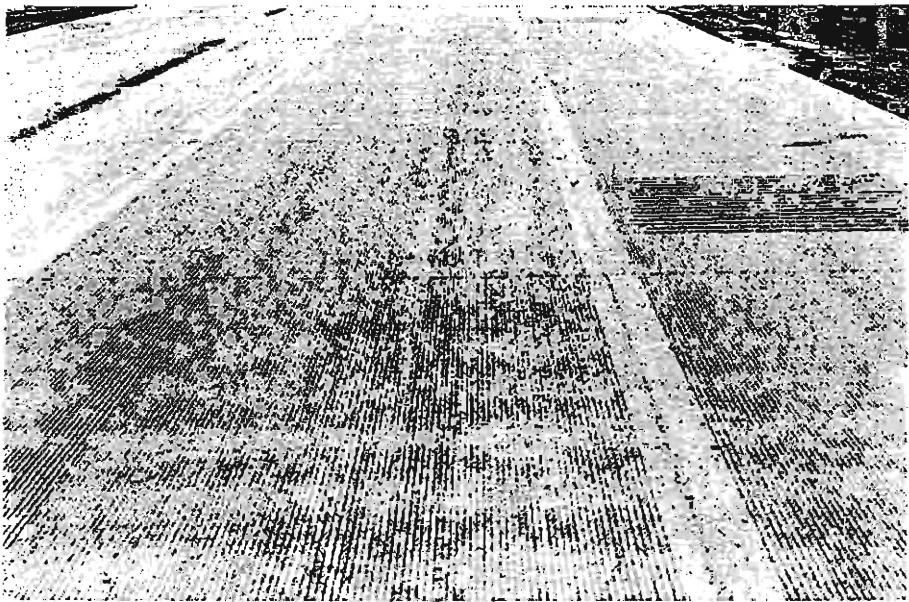


Photo 16: Grooved rumble strip in the right shoulder

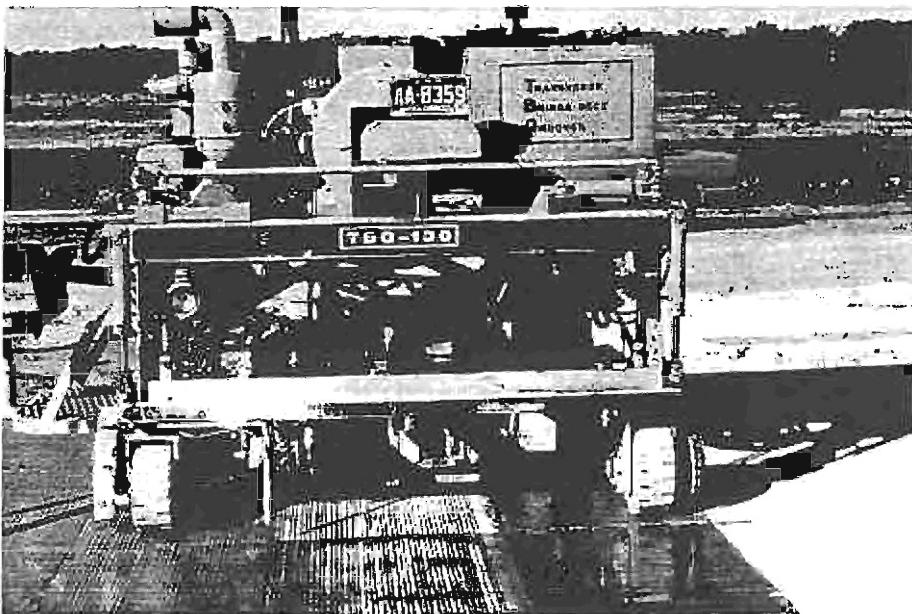


Photo 17: Installation of transverse grooves

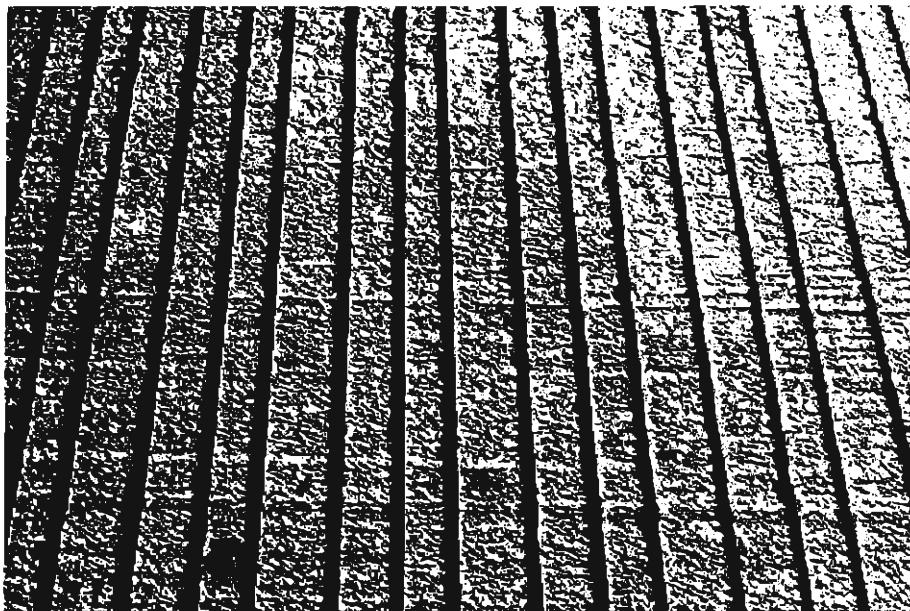


Photo 18: Close-up view of random transverse grooves with 5/8", 7/8", and 3/4" spacing

## **5.0 DATA ACQUISTION AND ANALYSIS**

### **5.1 Frictional Data**

To evaluate the frictional characteristics of individual test sections, skid numbers were acquired according to ASTM skid testing procedure E 274. This procedure measures the locked-wheel frictional forces between a tire of standardized design, size, and inflation pressure, and the wetted road surface at a constant speed of 40 miles per hour (7). Skid number is determined from the force required to slide the locked test tire at a stated speed, divided by the effective wheel load and multiplied by 100 (8).

Ribbed-tire (ASTM E 501) and smooth-tire (ASTM E 524) tests were used to obtain skid numbers at 40, 50, and 65 mph for all the test sections. Five skid resistance tests were conducted for each test section, as required by the standard ASTM procedure E 274. The arithmetic averages of the skid resistance tests were then used to indicate the skid number (SN) for individual test sections at a specified speed. ASTM E 501 and ASTM E 524 skid numbers were acquired at 40, 50, and 65 mph in October of 1994, and the results were plotted in Figure 3 and Figure 4.

A glance at these figures quickly revealed a definite relationship between speed, types of surface texture, and the magnitude of skid numbers. As speed increased, the skid numbers declined. However, this relationship was clearly more pronounced and consistent using the smooth tire. Skid numbers acquired using the smooth tire clearly showed a distinct difference in magnitude for surfaces with macrotexture and microtexture. For example, the smooth tire showed significantly lower skid numbers for test sections 2 and 8, which received only transverse and longitudinal astro-turf (microtexture), and showed higher skid numbers for the rest of the test sections with macrotexture surfaces.

The difference in skid numbers for microtexture and macrotexture were not as evident or consistent using the ribbed tire. This phenomenon confirms the findings of many research papers, revealing the insensitivity of the ribbed-tire towards macrotexture. The primary reason for the

## RIBBED-TIRE SKID NUMBERS OCTOBER 1994

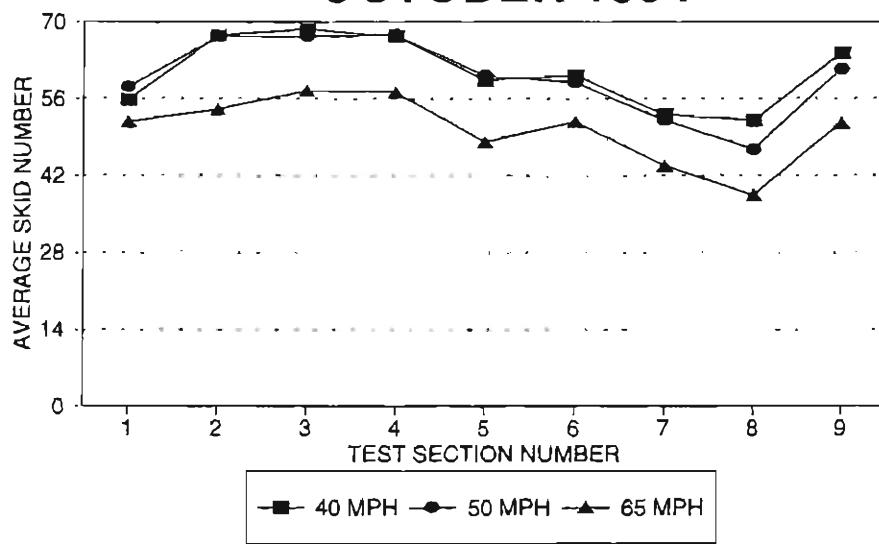


Figure 3

## SMOOTH-TIRE SKID NUMBERS OCTOBER 1994

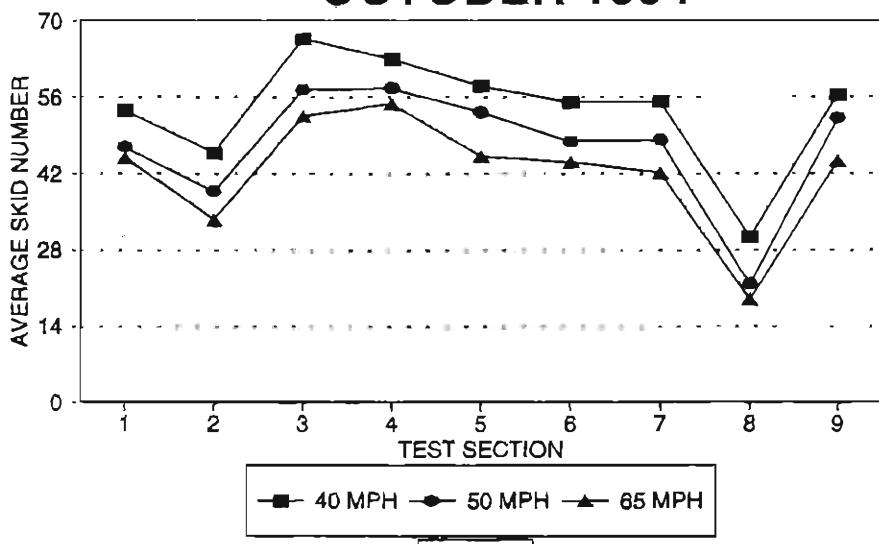


Figure 4

ribbed tire's insensitivity to macrotexture is its deep grooves, which provide drainage for water and somewhat ignore the drainage capability of the sawed or tined surfaces.

Figure 5 through 8 show the ribbed and smooth-tire skid numbers at 40 and 65 mph for years 1994 through 1999. The skid numbers taken in 1995 showed appreciable decline in magnitude in comparison with the skid numbers taken in 1994. For example, skid numbers taken with ribbed tire at 40 mph (SN40R) in 1995 were an average of seven points lower than those taken in 1994. The SN40R for test sections number 2 (textured with astro-turf in the longitudinal direction) showed the highest drop in magnitude, approximately 15 points.

It should be noted however, that even though the 1995 SN40R were much lower than the 1994 SN40R, they were still much higher than the skid number of 35, which is being used by many states as their minimum acceptable limit. The drop in the magnitude of 1995 skid numbers taken with smooth tire at 40 mph (SN40S) was even more pronounced. The 1995 SN40S were an average of 11 points lower than their corresponding 1994 SN40S. As before, test section 2 showed the highest drop, approximately 24 points.

Skid numbers kept declining during 1996; However, the rate of drop in skid numbers magnitude from 1995 to 1996 was significantly lower than the rate of drop in skid numbers from 1994 to 1995. For example, skid numbers taken with ribbed tire at 40 mph were an average of seven points lower than those taken in 1994. The average drop in skid numbers magnitude from 1995 to 1996 measured to be less than 1 point (0.77 to be exact). All the test sections including the microtexture test sections (sections 2 and 8) showed more than adequate skid numbers (SN40R = 49.9).

The rate of reduction in skid numbers for the smooth tire were also minimal. The drop in the skid numbers magnitude from 1995 to 1996 averaged less than 1 point (.80 to be exact), while the rate of drop from 1994 to 1995 averaged 11 points. As before, the two microtexture test sections (test sections 2 and 8) showed very low skid numbers, SN40S = 20.6 and SN40S = 20.4

## RIBBED-TIRE SKID NUMBERS 40 MPH

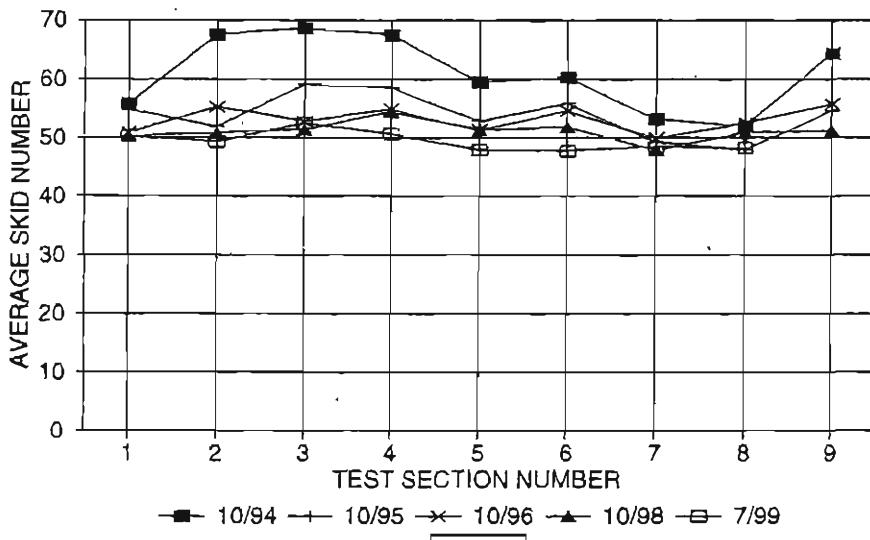


Figure 5

## SMOOTH-TIRE SKID NUMBERS 40 MPH

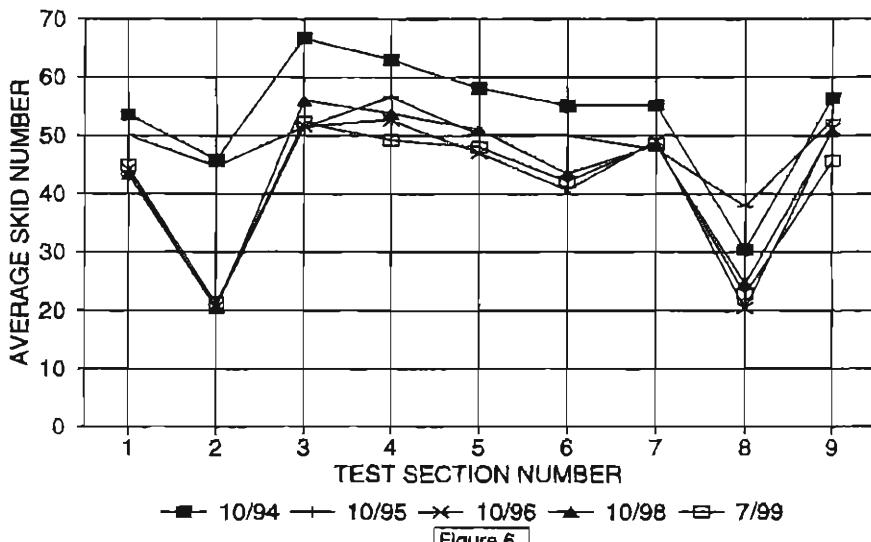


Figure 6

## RIBBED-TIRE SKID NUMBERS 65 MPH

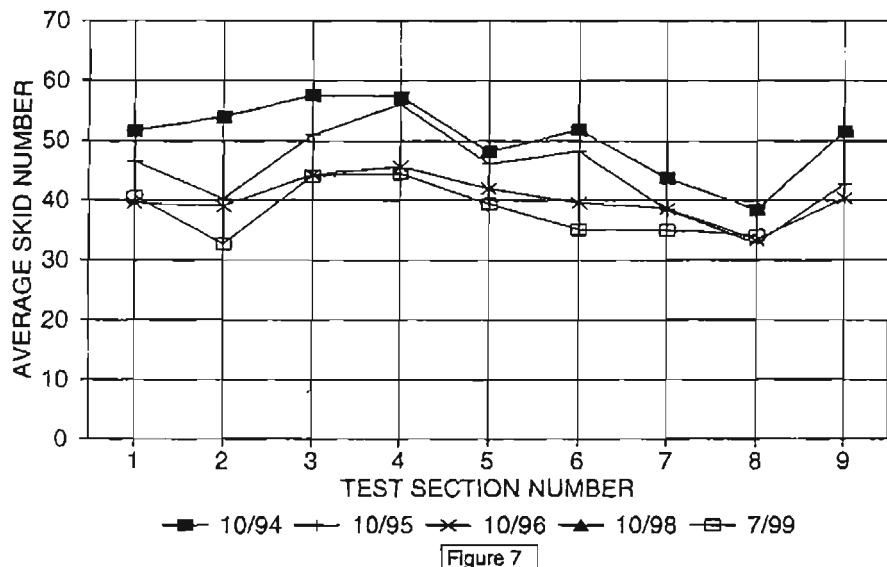


Figure 7

## SMOOTH-TIRE SKID NUMBERS 65 MPH

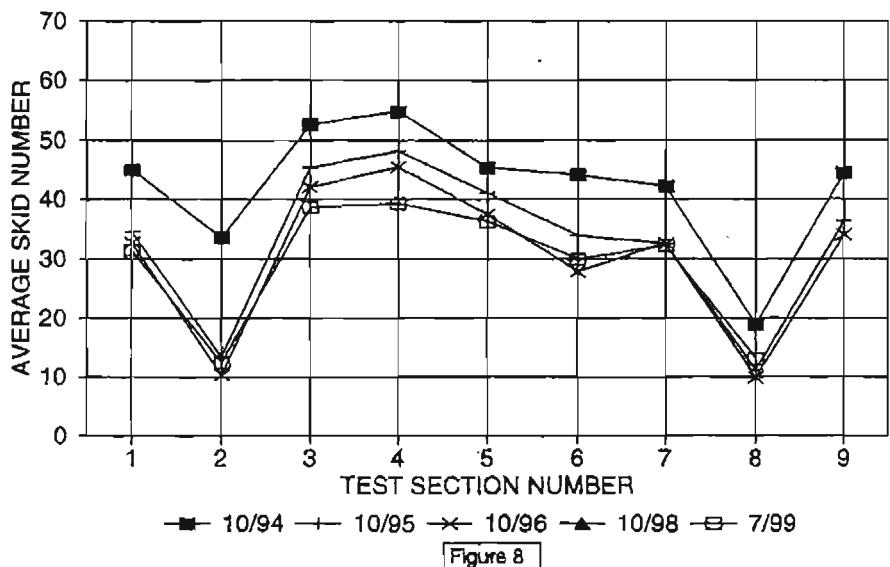


Figure 8

respectively. Overall, the skid numbers showed no appreciable change in magnitude after 1995 through 1999. For complete view of skid numbers at different speeds refer to Appendix A.

The smooth-tire and the ribbed-tire speed gradient for the individual test sections are shown in Figure 9. As shown in Figure 9, the relationship between the skid numbers and the speed appeared to be approximately linear for the smooth tire. However, this relationship was not as linear for most of the test sections using the ribbed tire. The speed gradient variations between 40 and 50 mph were minimal and inconsistent using the ribbed tire. On the other hand, all the test sections tested with the smooth tire showed a consistent drop in gradients as the speed increased.

In general, the smooth-tire gradients were steeper than their corresponding ribbed tire gradients. For more analysis on the relationship between the variables refer to scatter charts in Appendix A.

## **5.2 Texture Measurement**

Several different types of texture measuring devices were utilized to measure the amount of texture in each of the test sections. The following is the summary of the data acquired and the description of the equipment used. Equipment descriptions were provided by the FHWA, Pavement Division (9).

### **5.2.1 Texture Van (Laser Van)**

The texture van equipment (Photograph 19) can measure texture at travel speeds and does not interfere with normal traffic. It uses a television camera to take snapshots of a small pavement section in the wheel track (about 4 inches long). It takes a pre-selected number of exposures spaced about 50 feet apart at 50 miles per hour. To assure image sharpness the exposure time is given by a strobe light, and an infrared sensor assures that the field of view is in focus. A slit mask forms the images over the lens, giving two profile edges at every exposure.

An rms (root mean square) value is computed for each of the two profiles. The final output is an average rms value for the test section. Figure 10 compares the average rms values for the

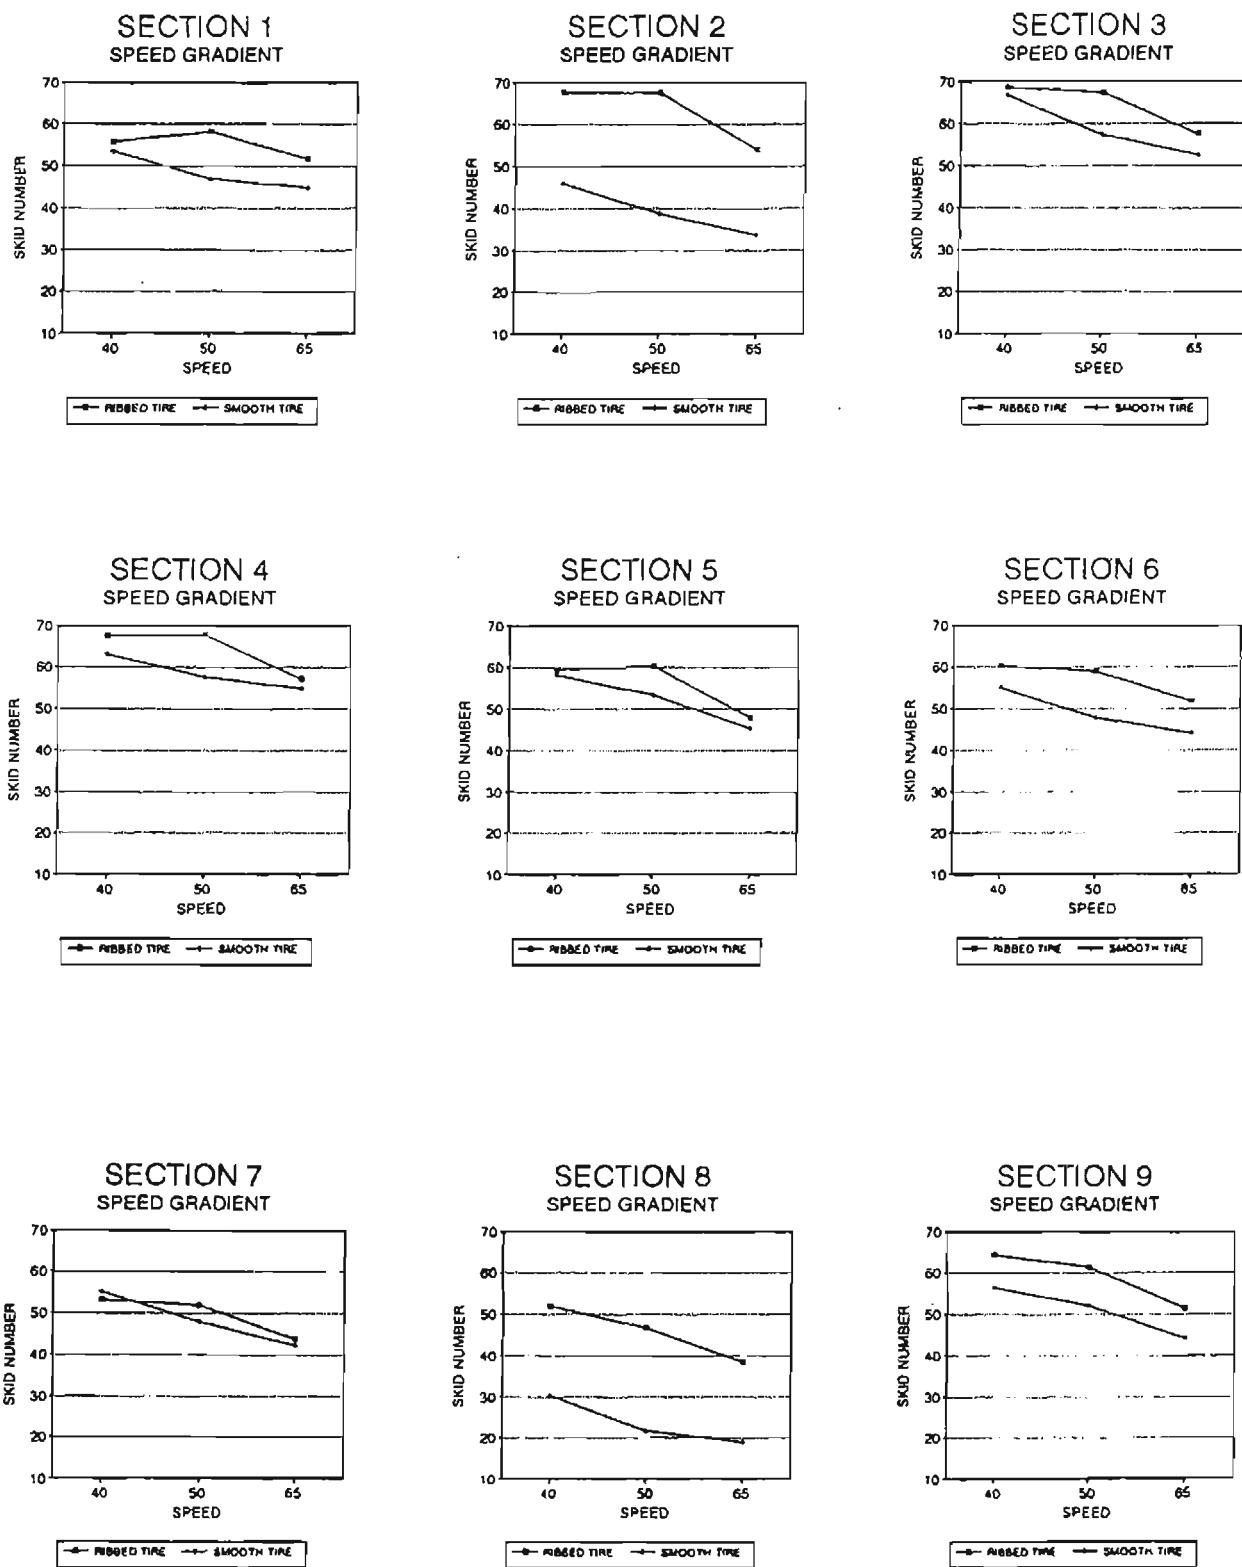


Figure 9

## TEXTURE MEASUREMENT LASER VAN

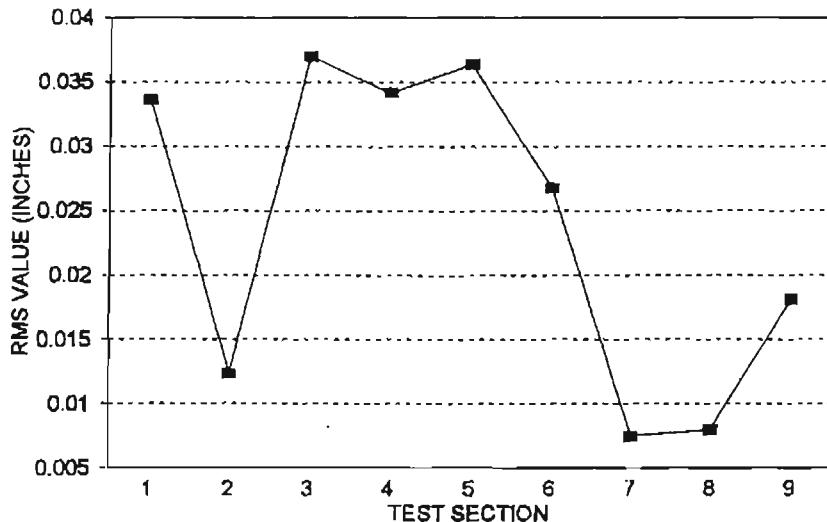


Figure 10

## INDIRECT TEXTURE MEASUREMENT WATER FLOW METER

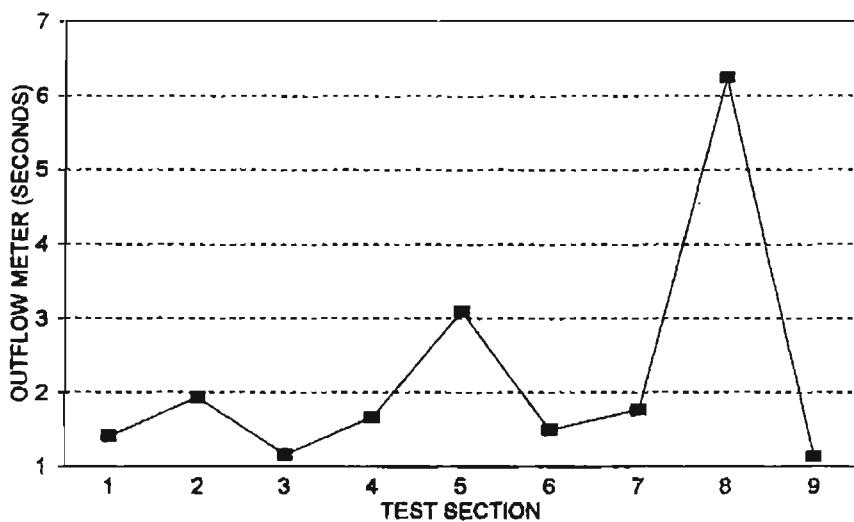


Figure 11



Photo 19: Inside of a texture measuring van

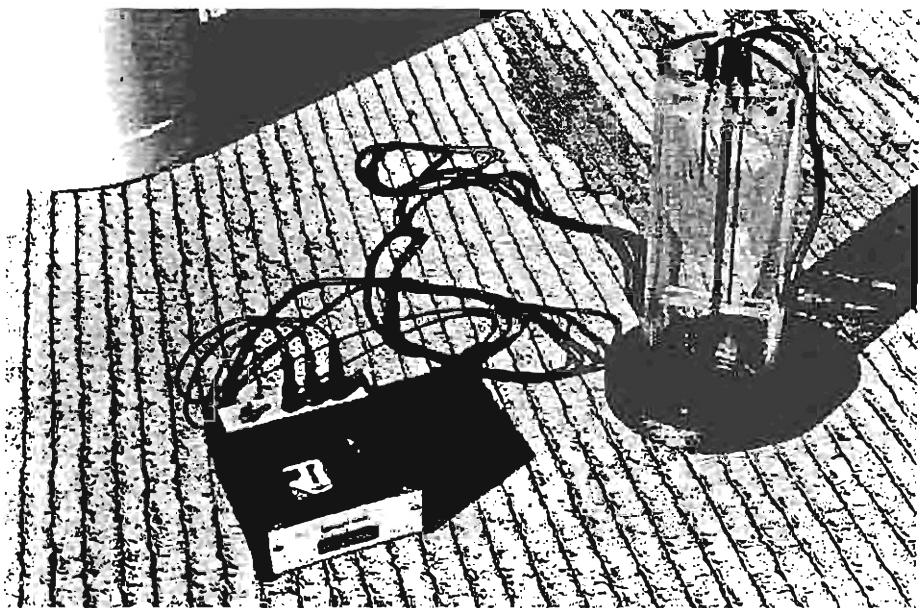


Photo 20: View of an outflow meter

individual test sections. As expected, the texture van showed lower values for sections 2 and 8 with microtexture; however, it also showed low values for longitudinal sawing (test section 7) and for longitudinal tining (test section 9). This may indicate that the laser van is more sensitive to the transverse texture than to the longitudinal texture. It should also be noted that, of the two microtextures (section 2 and 8), section 2 with the transverse orientation showed higher rms values.

### **5.2.2 Outflow Meter**

This is an indirect measure of texture (Photograph 20). A cylinder with rubber seals on its lower end is placed on the surface and loaded by weights to assure good contact. An electric timer is connected to probes inside the cylinder. The cylinder is filled with water. To start the test, the plunger sealing of the outlet is lifted and the water escapes between the rubber seals and the pavement surface. The time for the water to escape is a measure of texture. Deep textured surfaces will allow fast escape of water; i.e. the outflow time for deep textured surfaces is shorter than the outflow time for shallow textured surfaces.

Figure 11 shows the rate of the dissipation of water in seconds for all the test sections. Section 8 with longitudinal astro-turf (microtexture) took the longest to dissipate the water. The fastest draining texture appeared to be test section 9 (longitudinal tining) and test 3 (random transverse tining). In general, the time of water dissipation was less than 2 seconds for most of the test sections.

### **5.2.3 Texture Beam**

The texture beam shown on photograph 21 is capable of tracing texture over a straight line up to two feet long. A motor driven carriage carries two texture sensors. One is a mechanical stylus. The vertical motion is transmitted to an LVDT (Linear Variable Differential Transformer) and the output is recorded via a digitizing board on a computer.

The second sensor is a commercial laser stylus with its power supply and signal processor. The output is treated the same way as the LVDT output. The resulting texture traces can be displayed and processed. An rms value (similar to the texture van) can be computed. The profile can also be processed to display a texture spectrum. Figures 12 and 13 show the average rms values for both the LVDT and the commercial laser stylus. The only questionable rms value detected was for test section 1 (state standard, macrotexture with 1" transverse tining), for which measurements were lower than for the rms values of test section 2 and 8 with microtexture.

#### 5.2.4 Sand patch Method

This method is a volumetric measurement using the ASTM procedure E-965. A given amount of fine sand or glass beads particles (1.5 cubic inches) is poured over a selected spot on the pavement surface. The particles are then spread carefully in a circular pattern until all of them are below the texture peaks. Photograph 22 illustrates texture depth measurement using the sand patch test method. The covered area is estimated by measuring and averaging several diameters. The sand patch texture depth is given by dividing the known volume of glass beads or sand by the estimated area. TD (texture depth) = volume/area.

The results of the sand patch test appeared to be more consistent and realistic than the previously described methods. As shown in figure 14, the two microtexture test sections (test sections 2 and 8) showed lower texture depth than the macrotexture test sections. The average TD for sections 2 and 8 measured to be 0.03 and 0.02 inches respectively, while the average TD of the macrotexture test sections measured from a low of 0.036 inches for section 1 (state standard) to a high of 0.048 inches for section 9 (longitudinal tining).

The sand patch texture depth results correlated favorably with the smooth-tire skid numbers, indicating a linear relationship between the two methods with a correlation factor of  $r = 0.88$ . The similarity between the orientation of Figure 4 and Figure 14 further illustrates a good correlation between these two methods.

## TEXTURE MEASUREMENT LVDT BEAM

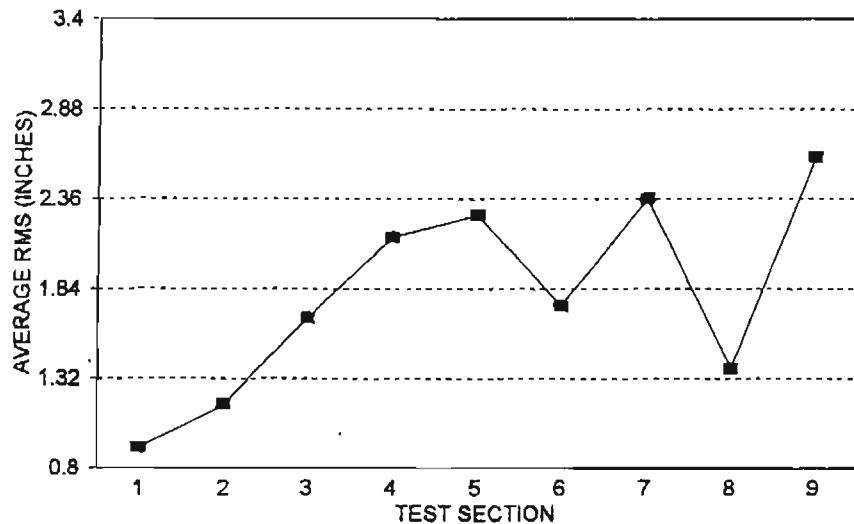


Figure 12

## TEXTURE MEASUREMENT LASER BEAM

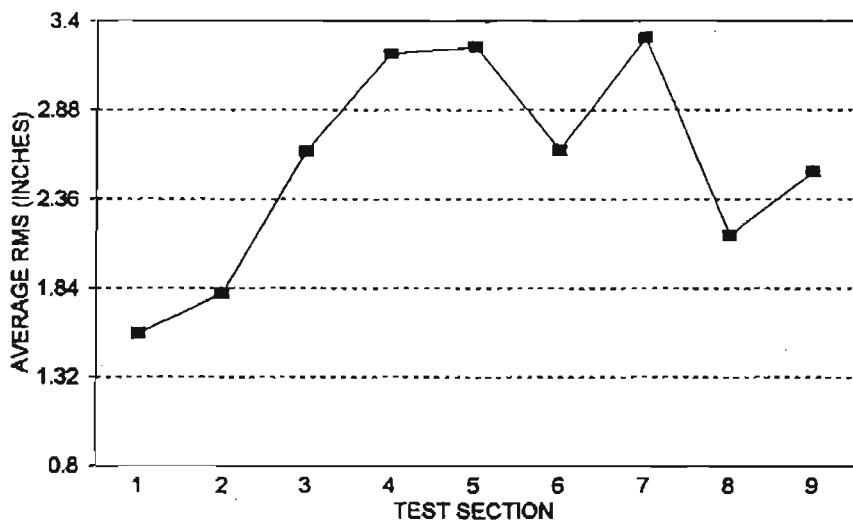


Figure 13

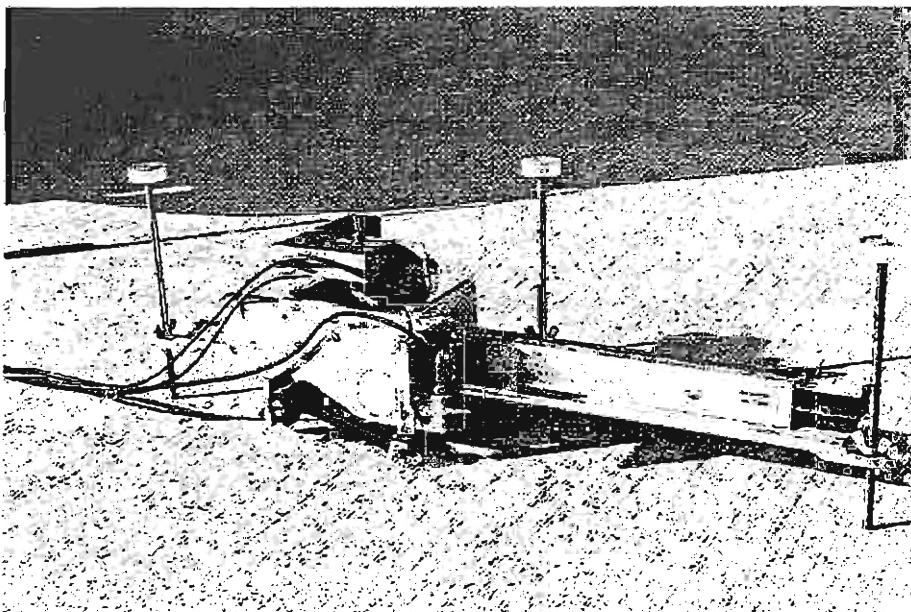


Photo 21: Texture beam, equipped with an LVDT and a laser stylus

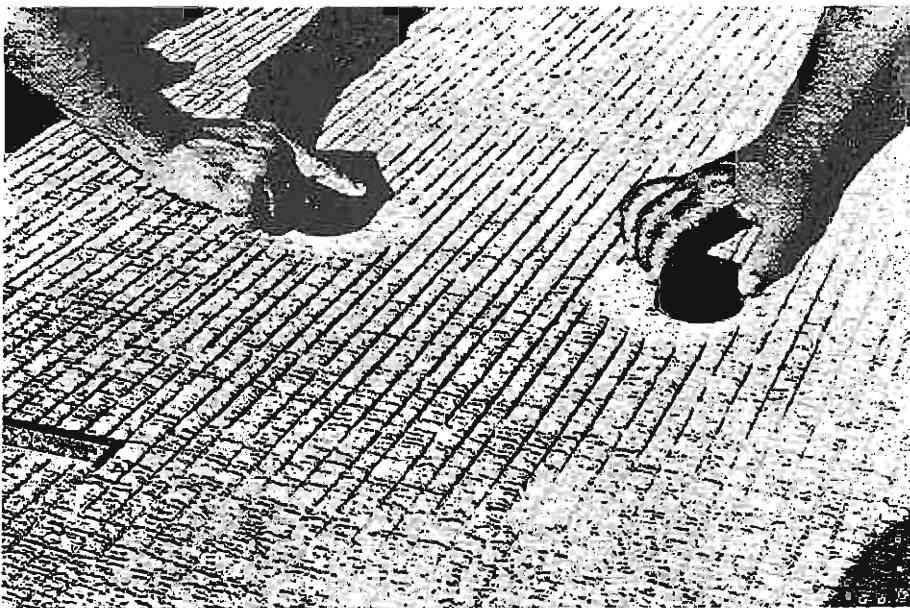


Photo 22: Sand patch test for measuring texture depth

## TEXTURE MEASUREMENT SAND PATCH METHOD

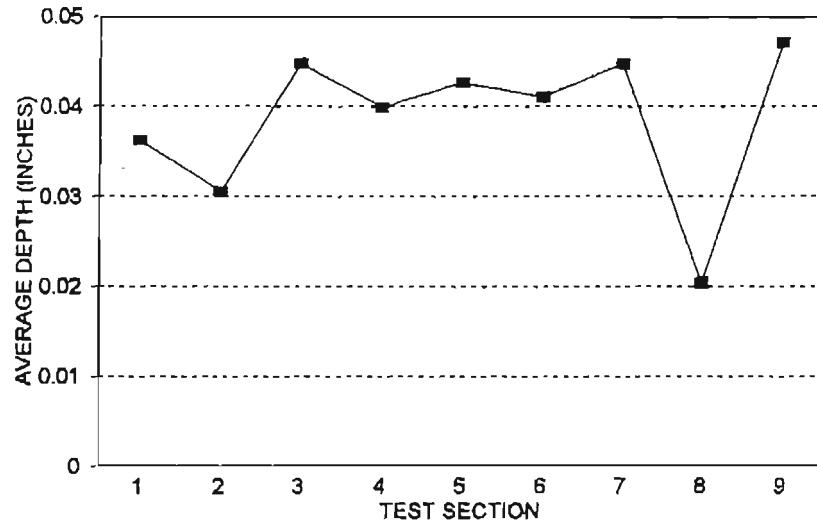


Figure 14

## TEXTURE MEASUREMENT TIRE GAUGE

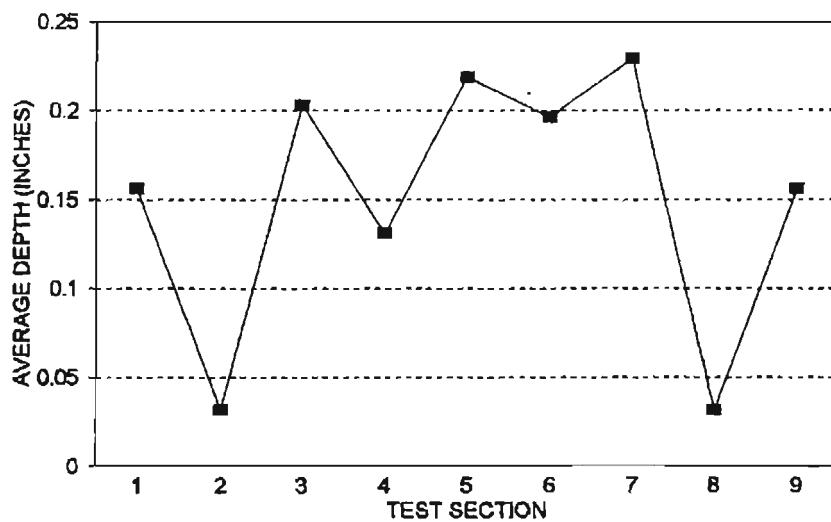


Figure 15



Photo 23: Texture depth measurement using a tire tread depth gauge

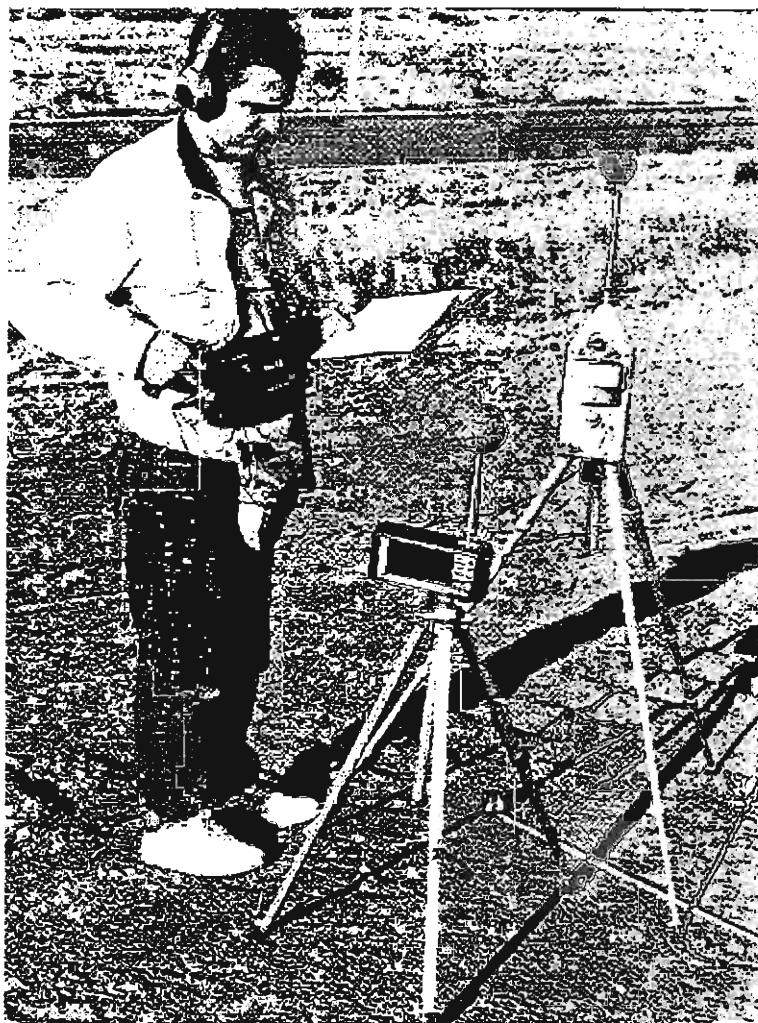


Photo 24: SPL measurement at the roadside

### **5.2.5 Tire Gauge**

A tire tread depth gauge with an accuracy of 1/32 of an inch was also used to measure texture depth (Photograph 23). Five texture depth measurements were taken and averaged at the same spot that the sand patch tests were taken. The results of the tire gauge measurements are shown in Figure 15. These measurements appeared to have a linear relationship with those of the sand patch tests with a correlation factor of  $r = 0.89$ . For an in-depth look at the test results and the relationships between various variables refer to scatter charts in Appendix A.

## **5.3 Noise Measurement**

Noise measurements were acquired as a joint effort between the CDOT's Research Branch and a local noise consultant, David L. Adams Associates, INC. The primary purpose of the measurements was to acoustically assess the impact of various surface textures installed in the test sections.

The test vehicle used was a 1994 Oldsmobile Cutlass station wagon provided by CDOT. Sound pressure level (SPL) measurements were recorded through a sound level meter to a digital tape recorder. The data extracted from the recordings were A-weighted sound levels, as well as 1/3-octave SPL with frequencies between 100 and 5000 Hz. The description of the equipment used in the assessment was as follows:

<u>Equipment</u>	<u>Manufacturer</u>	<u>Model No.</u>
Impulse Precision Sound Level Meter	Brue & Kjaer	2209
Strip Chart Recorder Level	Brue & Kjaer	2306
Digital Audio Recorder	Panasonic	SV-250

Noise data were acquired in the following three conditions:

1. SPL measurements were acquired at 25 feet from the centerline of the test sections. The microphone was placed on a tripod just beyond the shoulder of the road at a height of 4.5

feet (Photograph 24). The Oldsmobile station wagon was traveling in the driving lane at a speed of 65 miles per hour. In an effort to minimize the impact of engine noise, the station wagon coasted out of gear while passing the measurement station.

However, it should be noted that measurements taken with the engine on and with the engine off produced the same SPL, indicating that the tire noise was predominately louder than the engine noise. Figure 16 compares the change in SPL measurements of all the test sections relative to control section (state standard) at the shoulder. The sound generated at the control section was normalized to represent a datum (zero sound level pressure). Except for test section 3 (random transverse tining), all the other test sections showed lower decibels (dB) than the control section. Section 8 showed the lowest sound level pressure (6 dB lower than control).

The following table (reference 10) shows an approximation of human sensitivity to changes in sound level.

<u>Change in Sound Level (dB)</u>	<u>Change in Apparent Loudness</u>
1	Imperceptible
3	Just barely perceptible
6	Clearly noticeable
10	About twice (or half) as loud
20	About 4 times (or one-fourth) as loud

2. SPL measurements were acquired inside the test vehicle with the microphone positioned at ear height at the center of the front seat. These SPL measurements, which were taken at the coasting speed of 65 mph, represent the average SPL measurements over individual test sections.

Figure 17 compares the change in SPL measurements of all the test sections relative to the control section (state standard) at the driver's ear height. The sound generated at the control section was normalized to represent a datum (zero sound pressure level). As shown in Figure 13, the SPL measurements for all the test sections showed lower dB or the same dB levels as the control section. However, the lowest SPL measured was only 2 dB lower than the control section.

3. A mounting bracket was constructed and installed to allow SPL measurements to be taken near the right rear tire away from the exhaust pipe (Photograph 25). Figure 18 compares the change in SPL measurements for all the test sections relative to the control section (state standard) at the rear tire. As previously mentioned, the sound generated at the control section was normalized to represent a datum (zero SPL).

All the test sections showed lower sound levels than the control section as shown in Figure 18. Section 7 and 8 showed the lowest dB, 5 1/2 dB lower than the control section. It should be noted that for all the conditions mentioned above, 3 sets of data were acquired and then averaged. Figure 19 compares the A-weighted SPL measurements of all the three conditions. As expected, the SPL measurements taken near the rear tire and inside the test vehicle showed the highest and lowest dB respectively.

The three Figures in Appendix B show the SPL frequency distribution for all the test sections in all three conditions. The data are presented in a 1/3 octave band format. According to Chalupnik and Anderson (11) (12), noise components in the mid to upper frequencies between 1,000 Hz to 4,000 Hz are more annoying than the lower frequencies. These figures show that SPL generated in the control section (near tire and at the roadside) was higher than the other sections at the 1,000 - 1250 frequencies. The lowest SPL generated at the same frequencies was at sections 8 (longitudinal astro-turf, no tining) followed by section 7 (longitudinal sawing).

Figure 20 compares SPL Frequency distribution of a semi-truck with the test vehicle in a 1/3-octave band format (100 – 5000 Hz), as well as A-weighted SPL at the roadside. As can be

**SPL AT THE SHOULDER  
COMPARED TO STATE STANDARD SECTION**

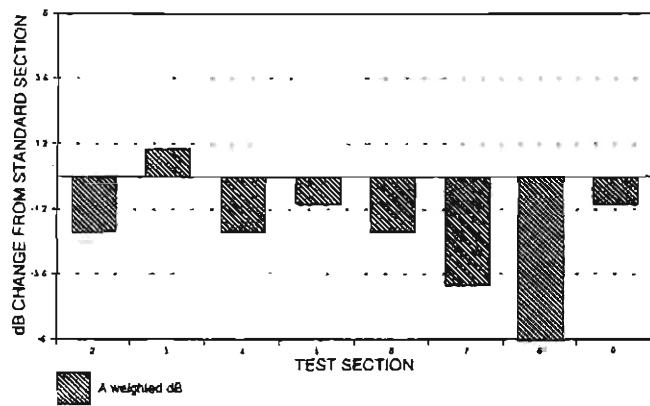


Figure 16

**SPL INSIDE TEST VEHICLE  
COMPARED TO STATE STANDARD SECTION**

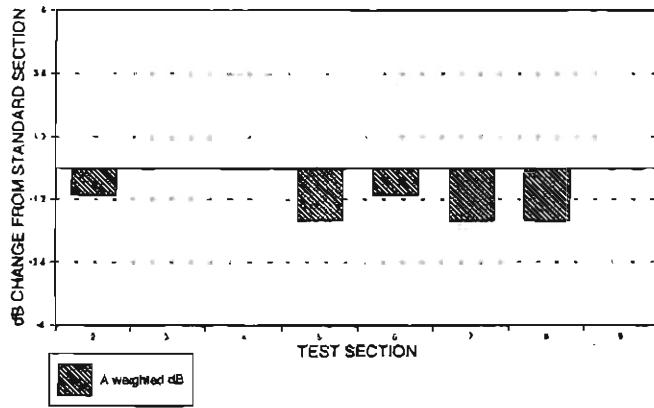


Figure 17

**SPL AT REAR TIRE  
COMPARED TO STATE STANDARD SECTION**

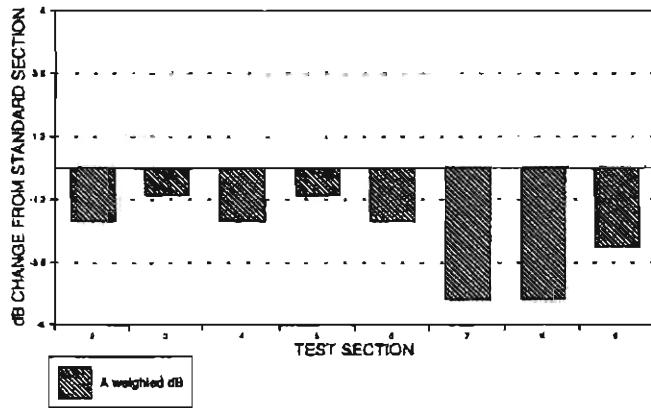


Figure 18

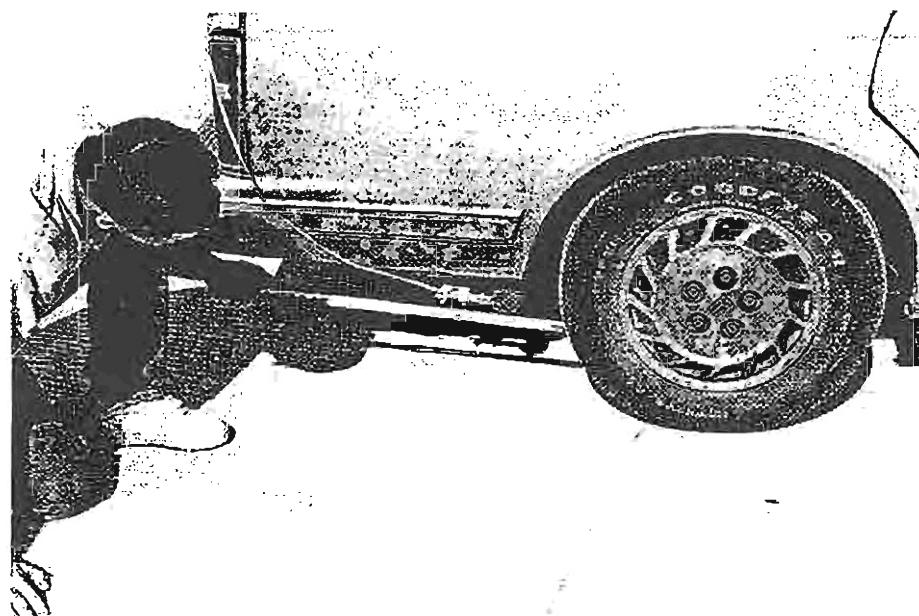


Photo 25: View of the microphone behind the rear tire

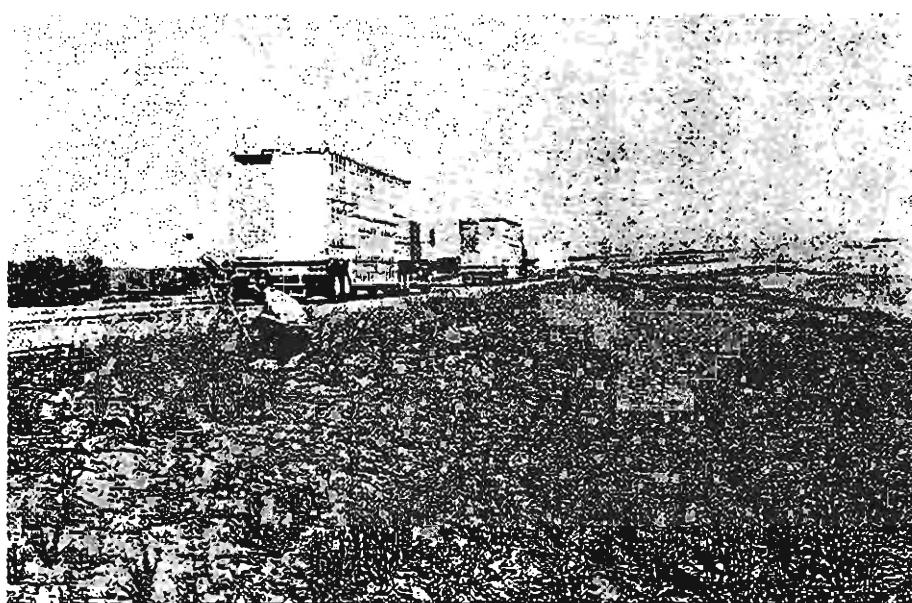


Photo 26: Acquiring truck noise levels at the roadside

## A-WEIGHTED SOUND LEVELS OCTOBER 1994

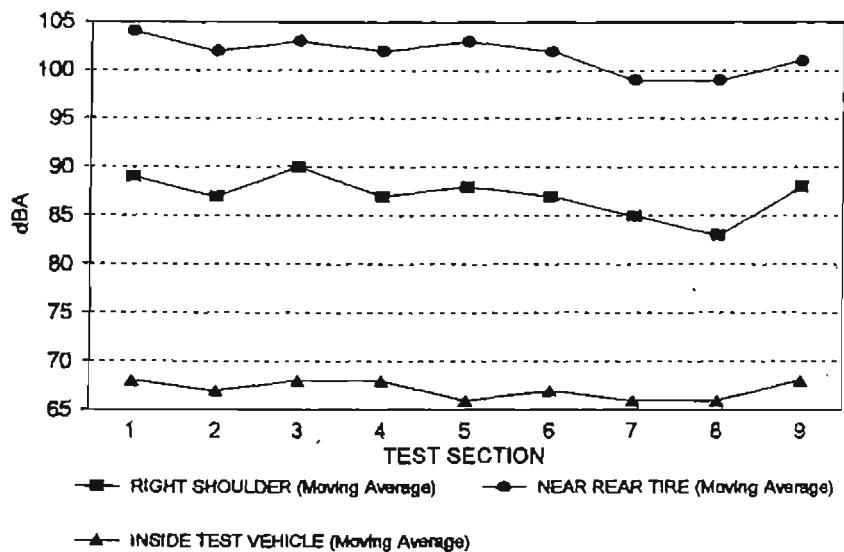


Figure 19

## SPL COMPARISONS CAR vs. TRUCK (SHOULDER SECT 1)

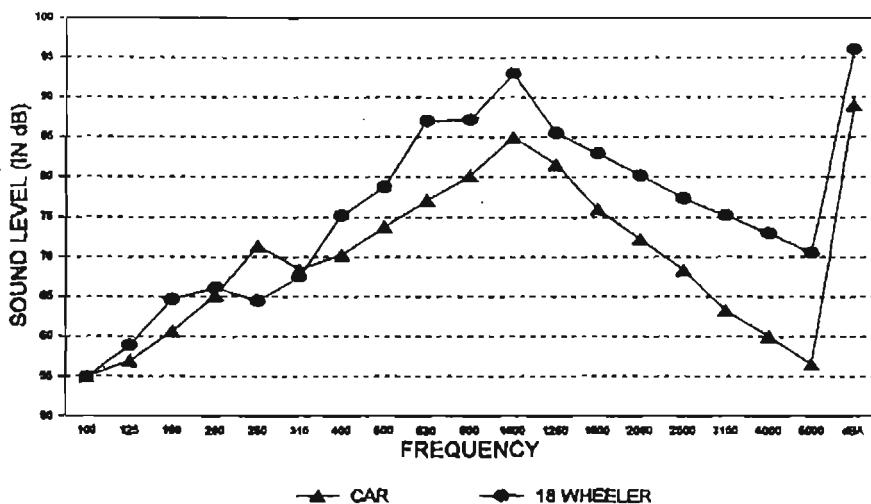


Figure 20

seen in this figure, the SPL for both the truck and the test vehicle peaked at 1000 Hz. However, the figure shows the noise from the truck (Photograph 26) to be at the higher annoyance range (by about 8 dB) than the noise from the test vehicle. The A-weighted dB for the truck was also 7 dB higher than the A-weighted dB of the test vehicle.

#### 5.4 Roughness Data

Figure 21 compares the average right- and left-wheel-path roughness data for all the test sections. Test section 6, which was textured using a combination of longitudinal astro-turf and 1-inch uniform tining, exhibited the highest roughness. It should be noted that dynamic effects that act on suspension systems and generate vibrations inside vehicles are primarily due to megatexture or small-scale roughness (explained below). The influence of surface texture on ride quality, with the exception of noise level, is minimal.

The Technical Committee Report on Surface Characteristics in Belgium (13), defines the various surface irregularities based on their wavelengths as follows:

Wavelength < 0.5 mm	Microtexture
Wavelength 0.5 mm - 50 mm	Macrotecture
Wavelength 50 mm - 500 mm	Megatexture
Wavelength 0.5 m - 50 m	Roughness

Based on the findings of the above mentioned report, it appears that irregularities with wavelengths greater than 50 mm and smaller than 150 mm (megatexture) have the most adverse effects on the quality of ride. Microtexture and macrotecture, with the exception of noise levels, have only beneficial effect (14).

# PROFILOGRAPH

OCTOBER 1994

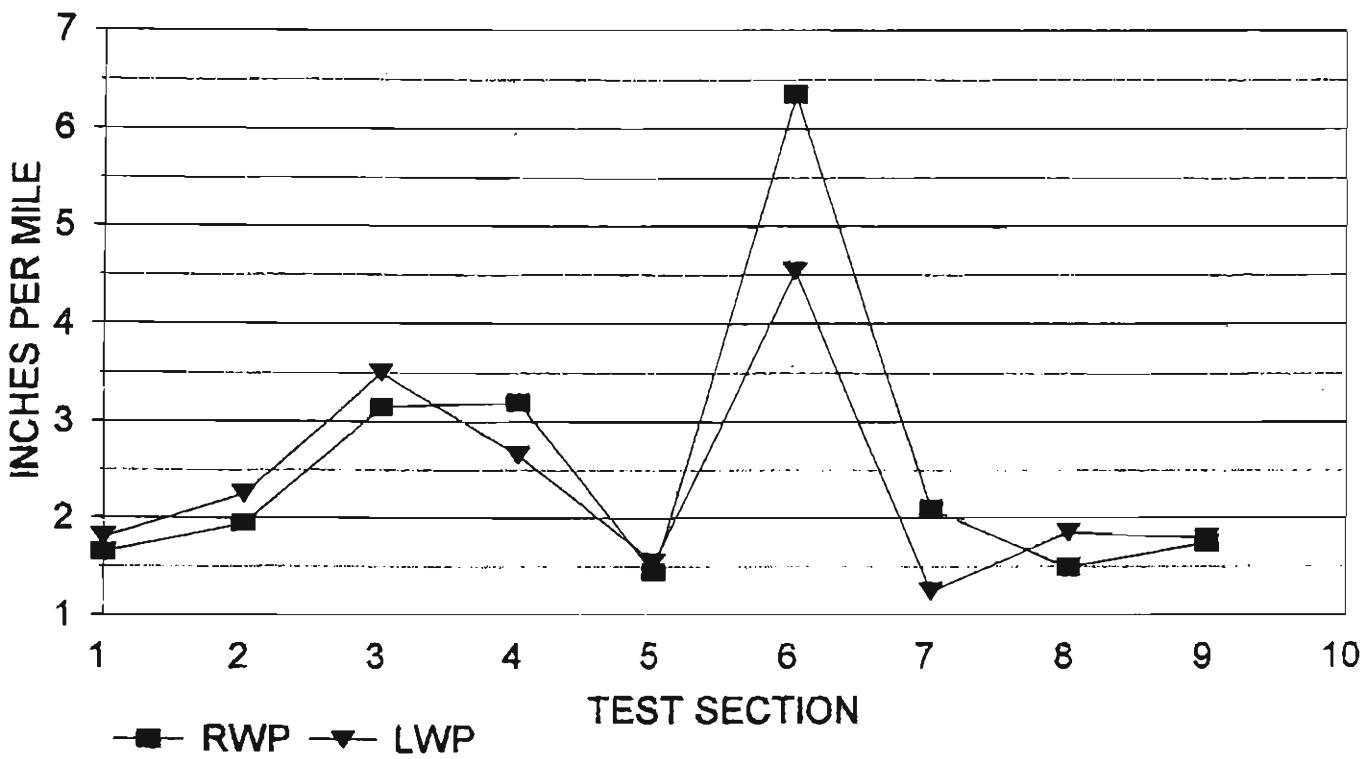


Figure 21

## **6.0 CONCLUSIONS AND RECOMENDATIONS**

The conclusions and recommendations presented here are based on the data that were acquired prior to opening to traffic in 1994 and the subsequent data that were acquired thereafter through 1999. The conclusions are also based in part on a national study called, "Noise and Texture on PCC Pavements." This study was sponsored by FHWA and conducted by Marquette University (15). As part of this national study, Colorado, Iowa, Michigan, Minnesota, North Dakota and Wisconsin provided 57 test sections to study the noise properties and the frictional characteristics of several different PCC textures.

### **6.1 Conclusions**

- The PCC surface texture has a profound effect on the traffic-induced noise characteristics generated at the interface of the tire and the pavement surface. The change in PCC surface texture also has a major effect on the frictional properties.
- Texture depth taken with various texture-measuring devices correlated favorably with the smooth-tire skid numbers taken at 40, 50, and 65 mph, indicating a linear relationship with excellent correlation factors. The results were not as linear with the ribbed-tire skid numbers. For a thorough view of the scatter diagrams (relationship between various variables) refer to Appendix A.
- Section 3 (combination of longitudinal astro-turf and random transverse tining) and section 8 (longitudinal astro-turf) showed the highest and lowest skid numbers respectively, using both the ribbed and the smooth tire.
- The highest drop in skid numbers occurred between the first year and the second year. The change in the magnitude of the skid numbers for both the smooth and the ribbed tire significantly leveled off after the second year.

- The relationship between the skid numbers and the speed appeared to be approximately linear for the smooth tire, and not as linear for the ribbed tire. In general, the smooth-tire speed gradients were steeper than the ribbed-tire speed gradients.
- Longitudinal macrotexture and microtexture were the most quiet surfaces based on the sound pressure levels (SPL) taken at the shoulder, inside the test vehicle, and at the rear tire.
- State standard section (combination of burlap drag and uniform 1" spacing) exhibited the highest noise level among all the test sections with the microphone at the rear tire position.
- SPL taken at the shoulder showed the A-weighted dB of a semi-truck to be approximately 7 dB higher than the A-weighted dB of the test vehicle.
- The influence of surface texture on ride quality is minimal.

## 6.2 Recommendations

- The use of smooth tire over the ribbed tire as a method of acquiring skid numbers is recommended. The smooth tire (ASTM E 524) showed more sensitivity to both microtexture and macrotexture than the corresponding ribbed tire (ASTM E 521). The primary reason for the ribbed tire's insensitivity to macrotexture is its deep grooves, which provide drainage for water and somewhat ignore the drainage capability of the sawed or tined surfaces.
- Longitudinally tinned PCC Pavements exhibit the lowest noise level and provide adequate friction. Their use is highly recommended.
- The use of the sand patch test method as a texture-depth measuring device is highly recommended. Excellent correlations were achieved using the sand patch test method and smooth-tire skid numbers (Appendix A).

- To ensure proper friction and to minimize noise, quality control for tine spacing and tine depth needs to be improved. Deeper tines generate louder sound levels.
- A research study to document the effects of various surface textures on safety in wet weather conditions is highly recommended.

## References

1. Dierstein, Philip G, "A Study of PCC Pavement Texturing Characteristics in Illinois," Physical Research Report No. 95, November 1979.
2. Forster, Stephen W., "Pavement Microtexture and Its Relation to Skid Resistance," Transportation Research Record 1215.
3. American Concrete Institute Committee 325, "Texturing Concrete Pavements," ACI Materials Journal, June 1988.
4. FHWA Technical Advisory T 5040.17, "Skid Accident Reduction Program," Pavement Notebook for FHWA Engineers, December 1980.
5. J.C Wambold, J.J. Henry, R.R. Blackburn, "Pavement Surface Texture: Significance And Measurement," FHWA / RD -84 / 092, July 1984.
6. Yager, Thomas J., "Summary of NASA Friction Performance Data Collected With ASTM E 501 and 524 Test Tires."
7. Woodrow J. Halstead, NCHRP Synthesis 104, "Criteria for Use of Asphalt Friction Surfaces," November 1983.
8. ASTM Committee E-17 on Pavement Management Technologies, "Standard Test Method for Skid Resistance of Paved Surfaces Using a Full-Scale Tire," October 1990.
9. PCC Surface Texture TWG, FHWA, Pavement Division HNR-20, "Texture Measuring Equipment."
10. Egan, M. David, "Architectural Acoustics," 1988.
11. Chalupnik, James D., Anderson, Donald S., "The Effect of Roadway Wear On Tire Noise," Washington State Department of Transportation, WA-RD 276.1, Final Report, August 1992.
12. Chalupnik, James D., Anderson, Donald S., "Roadside Tire Noise," Washington State Department of Transportation, WA-RD 320.1, Final Report, March 1994.
13. PIARC Report of the Technical Committee on Surface Characteristics. Presented at XVIIIth World Road Congress, Brussels, Belgium, 1987.
14. Fuchs, F., "An Overview of European Practice," Belgian Road Research Center.
15. Kuemmel, D., "Noise And Texture on PCC Pavements," Marquette University, 1998.

## **Appendix A**

Texture Measurement Averages						
Site	Laser Van (RMS in.)	Sand Patch (depth in)	Flow Meter (seconds)	Beam Laser (RMS in.)	Beam LVDT (RMS in.)	Tire Gage (in.)
1	0.034	0.036	1.403	1.575	0.919	0.156
2	0.012	0.031	1.923	1.806	1.170	0.031
3	0.037	0.045	1.158	2.639	1.673	0.203
4	0.034	0.040	1.662	3.209	2.139	0.131
5	0.036	0.043	3.093	3.252	2.267	0.219
6	0.027	0.041	1.491	2.648	1.742	0.196
7	0.007	0.045	1.763	3.303	2.360	0.229
8	0.008	0.020	6.247	2.148	1.377	0.031
9	0.018	0.047	1.133	2.519	2.603	0.156

Skid Measurement Averages 1994									
	1	2	3	4	5	6	7	8	9
SN40R	55.8	67.5	68.7	67.5	59.5	60.3	53.1	52	64.4
SN50R	58.1	67.4	67.3	67.7	60.3	59	52	46.7	61.4
SN65R	51.7	54	57.6	57.3	48.1	51.9	43.8	38.4	51.5
SN40S	53.6	45.9	66.8	63	58.1	55.1	55.2	30.4	56.4
SN50S	46.9	38.7	57.4	57.7	53.3	47.9	48.1	21.8	52.1
SN65S	45	33.6	52.6	54.8	45.3	44.1	42.2	19	44.4


Skid Measurement Averages 1995									
10/95	1	2	3	4	5	6	7	8	9
SN40R	54.7	52	59.1	58.6	52.8	55.9	49.3	47.9	54.6
SN50R	50.1	44.7	51.5	56.7	50.3	49.9	47.7	37.8	52.7
SN65R	46.5	40.2	51	56.1	46.1	48.2	38.4	32.8	42.7
SN40S	42.9	22.1	52.2	56.3	50.7	42.3	47.1	20.6	50.5
SN50S	41.5	17.1	49.7	54.5	45	38.9	45.7	16.3	48.5
SN65S	34.5	13.4	45.3	48.2	41.1	33.9	32.5	11.2	36.3

Skid Measurement Averages 1996									
10/96	1	2	3	4	5	6	7	8	9
SN40R	50.9	55.3	52.8	54.9	51.3	54.6	49.9	52.5	55.7
SN50R	45.3	46.4	48.8	49.8	47.1	47.3	47.3	45.6	49
SN65R	39.5	39	44.3	45.7	41.9	39.6	38.6	33.4	40.3
SN40S	44.3	20.6	51.6	52.7	47	40.6	49.1	20.4	51.2
SN50S	38.4	15.2	44.9	47.1	44	35.8	43.3	13.9	43
SN65S	32.8	10.3	42.1	45.5	37.5	27.9	32.6	9.9	34


Skid Measurement Averages 1998									
10/98	1	2	3	4	5	6	7	8	9
SN40R	50.3	50.8	51.4	54.5	51.3	51.8	48	50.8	51.2
SN50R									
SN65R									
SN40S	43.4	20.5	56.1	53.8	51	43.4	48.3	24.6	50.8
SN50S									
SN65S									

Skid Measurement Averages 1999									
7/99	1	2	3	4	5	6	7	8	9
SN40R	50.3	49.4	52.5	50.7	47.9	47.8	48.5	48.2	
SN50R									
SN65R	40.6	32.7	44.1	44.5	39.4	35.1	35	34.2	
SN40S	44.9	21.4	52.3	49.2	48	42.2	48.6	22.9	45.7
SN50S									
SN65S	31.5	12.4	38.7	39.3	36.3	29.9	32.2	13.2	


### SN40S vs SAND PATCH DEPTH

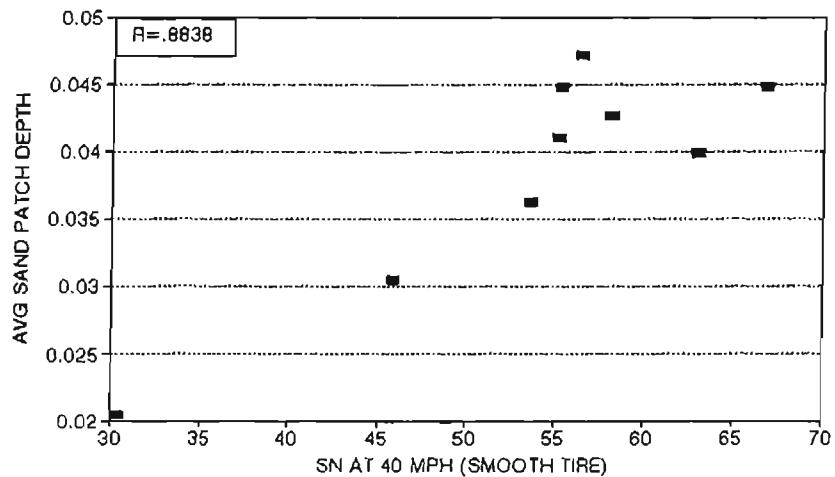


### SN50S vs SAND PATCH DEPTH

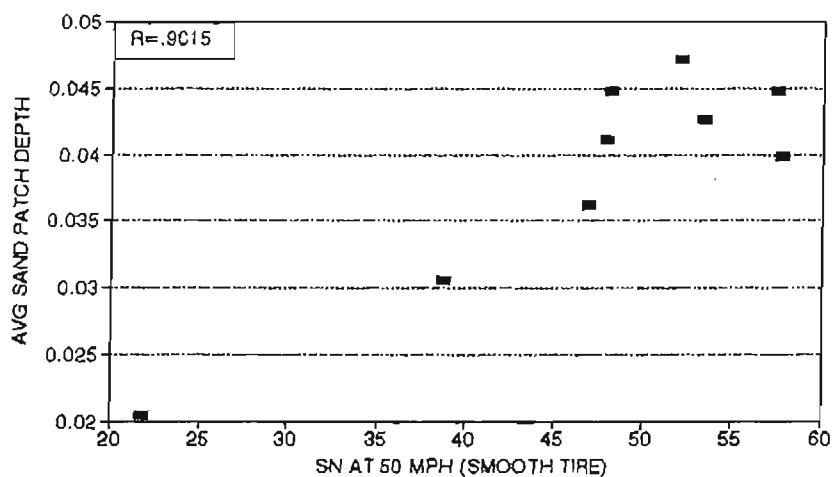


### SN65S vs SAND PATCH DEPTH

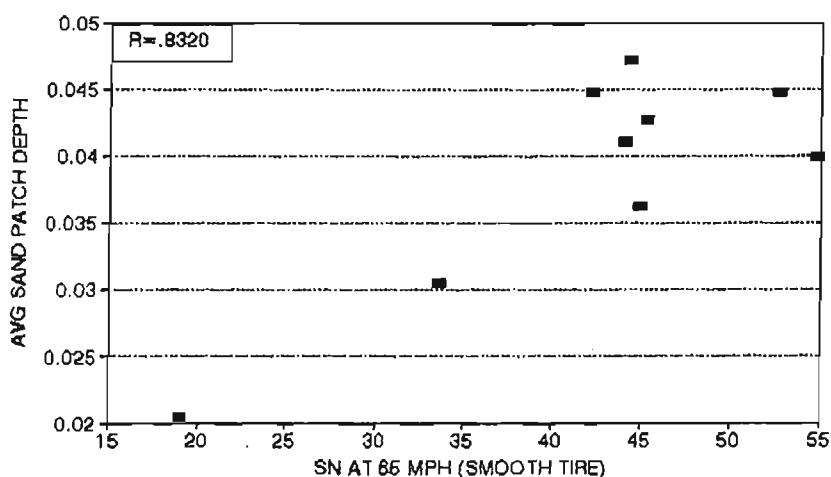


### SN40R vs SAND PATCH DEPTH

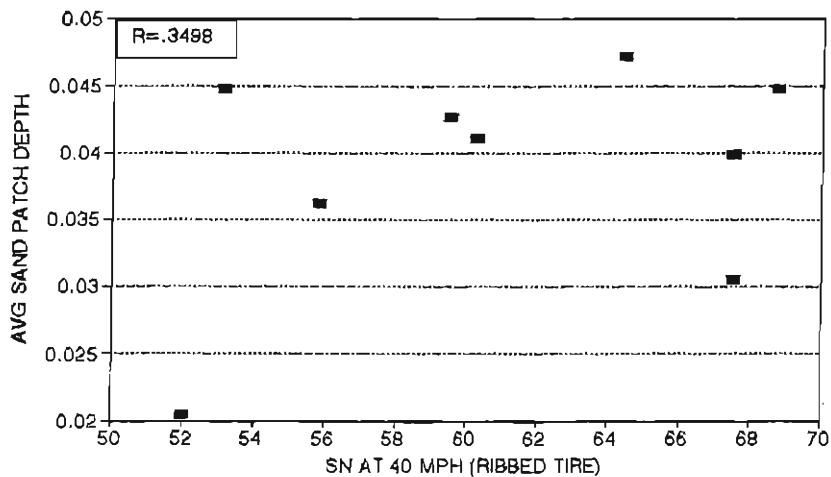


### SN50R vs SAND PATCH DEPTH

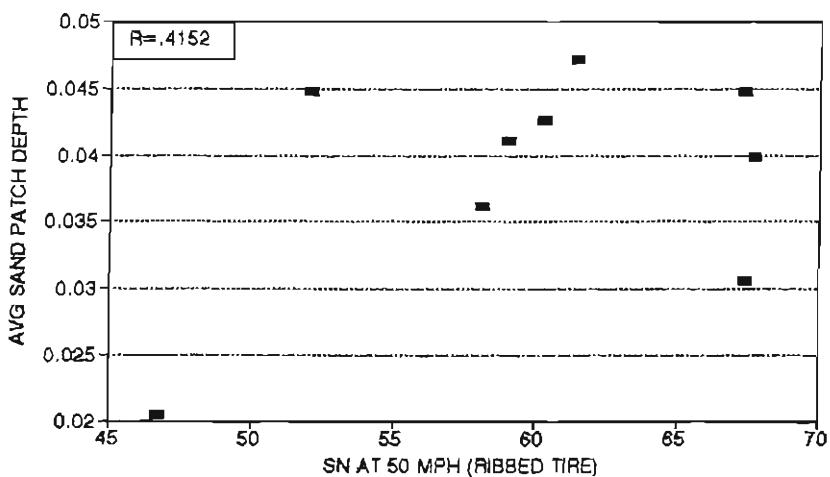


### SN65R vs SAND PATCH DEPTH

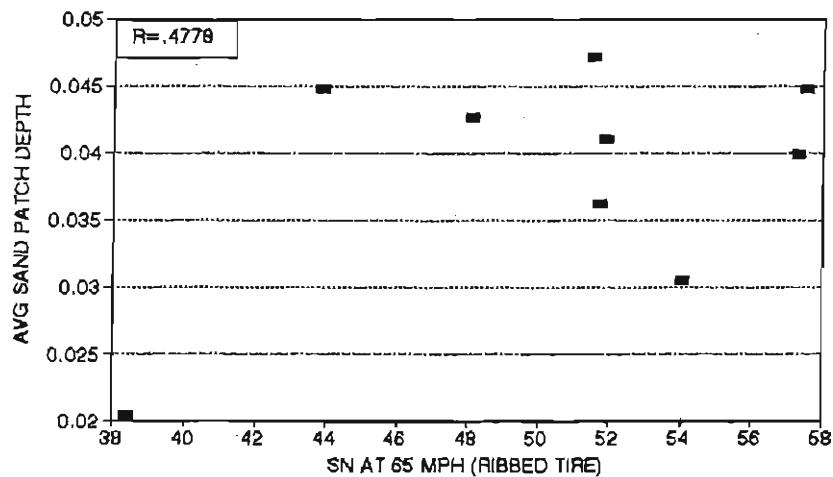


### SN40S vs. OUTFLOW METER

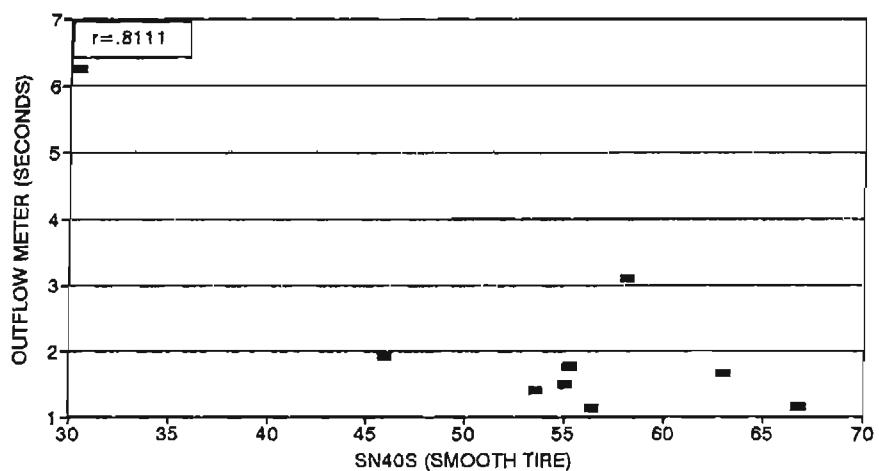


### SN50S vs. OUTFLOW METER

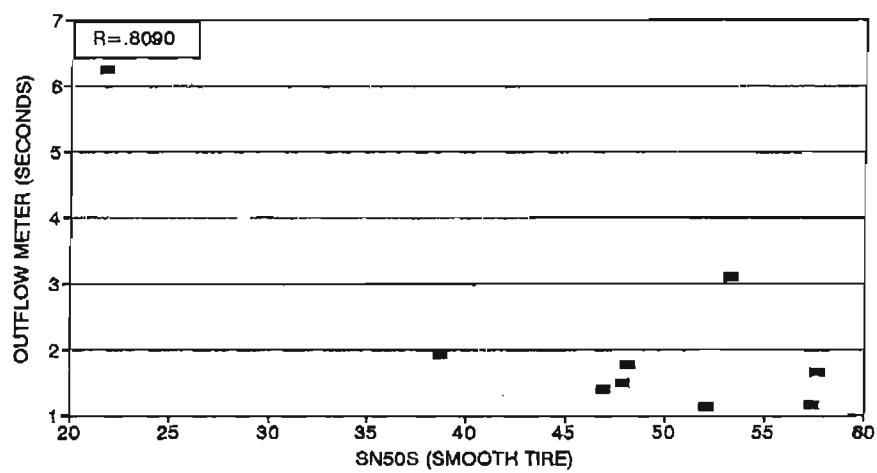


### SN65S vs. OUTFLOW METER

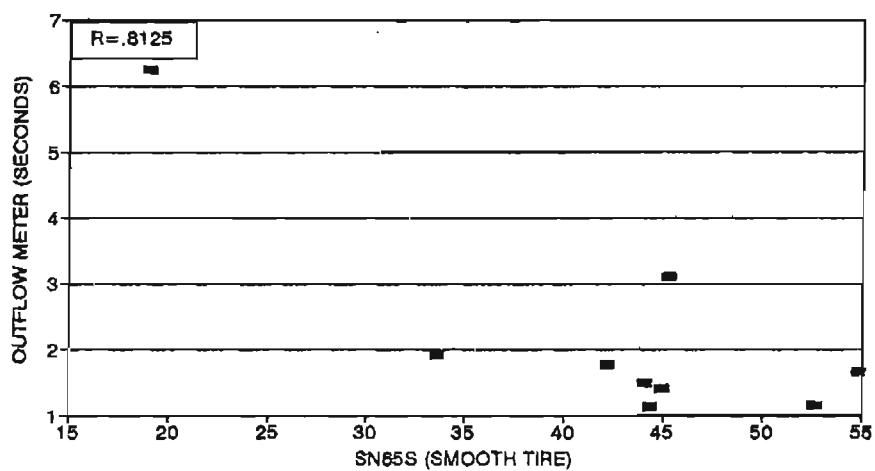


### SN40R vs. OUTFLOW METER

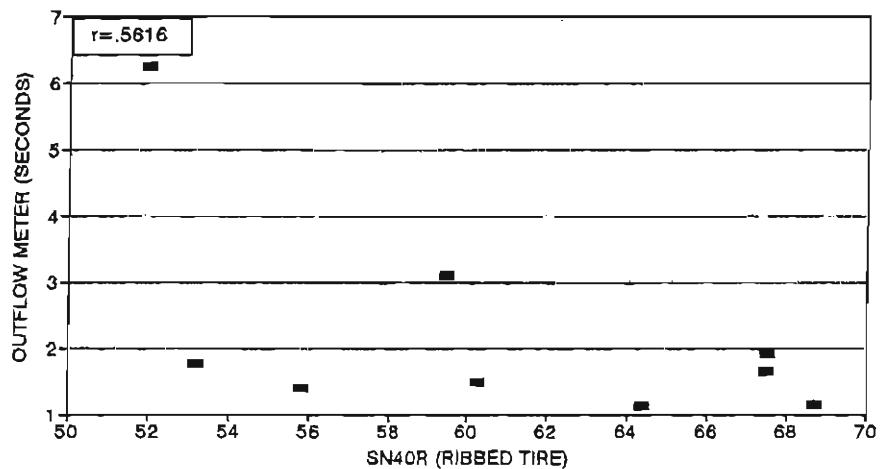


### SN50R vs. OUTFLOW METER

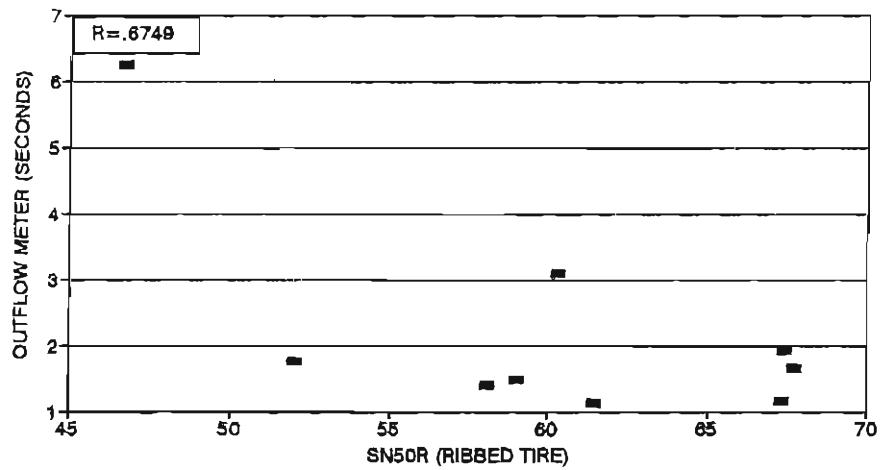


### SN65R vs. OUTFLOW METER

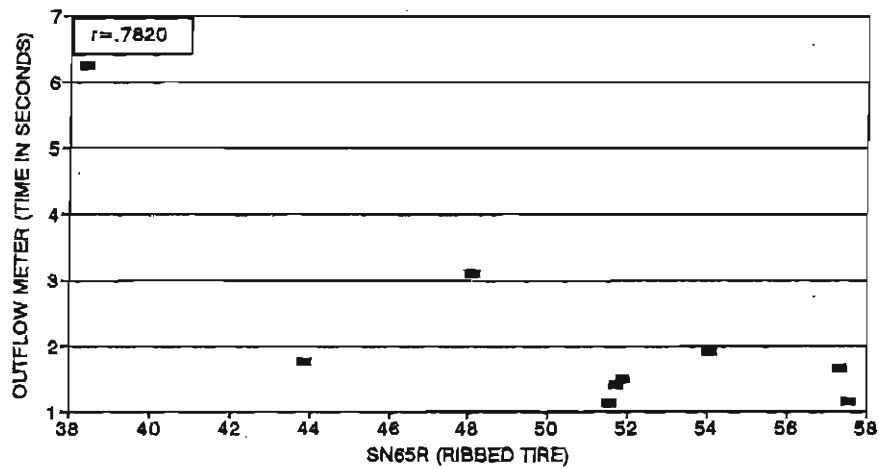


### SN40S vs. TIRE TREAD GAUGE

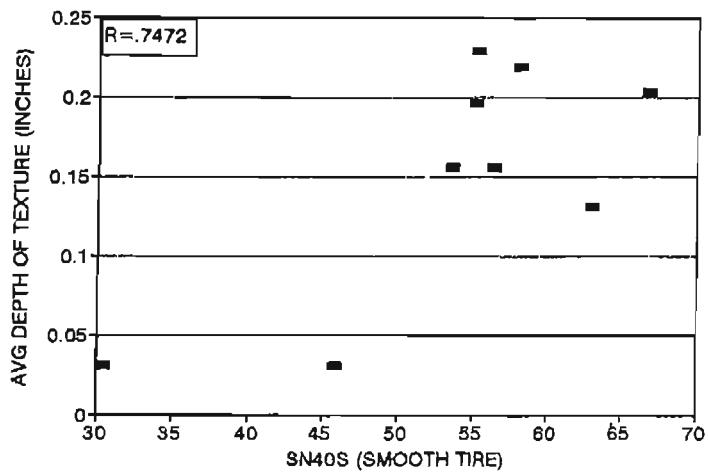


### SN50S vs. TIRE TREAD GAUGE

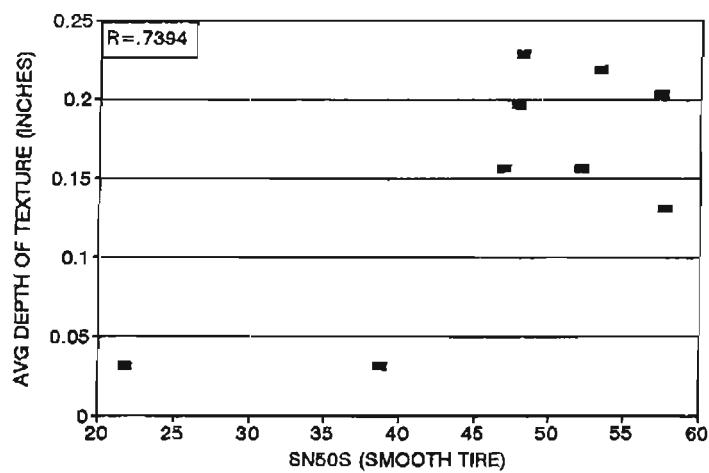


### SN65S vs. TIRE TREAD GAUGE

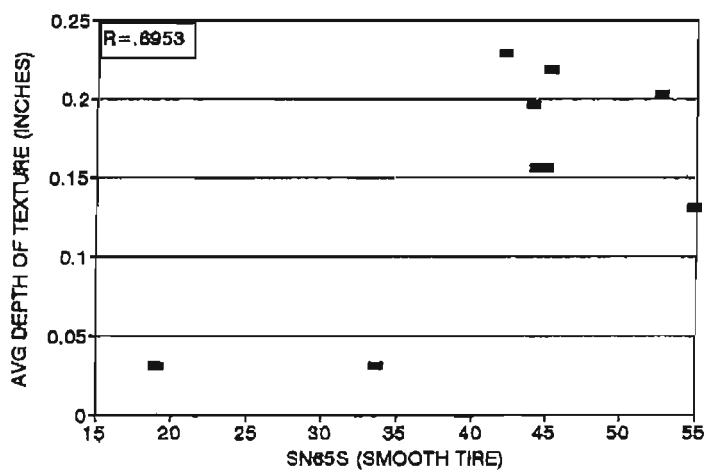


### SN40R vs. TIRE TREAD GAUGE

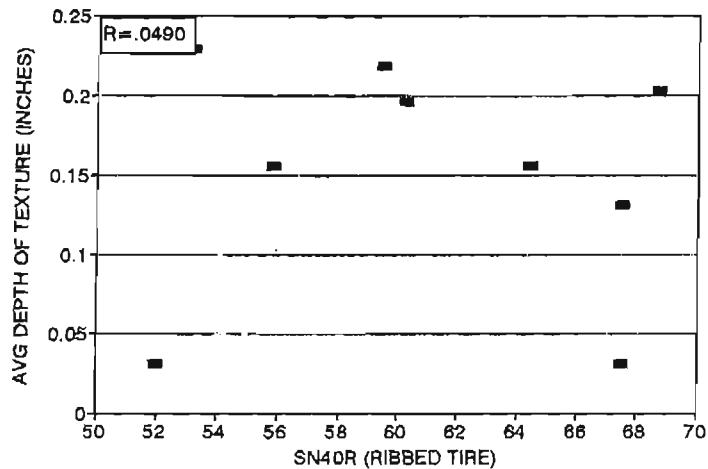


### SN50R vs. TIRE TREAD GAUGE

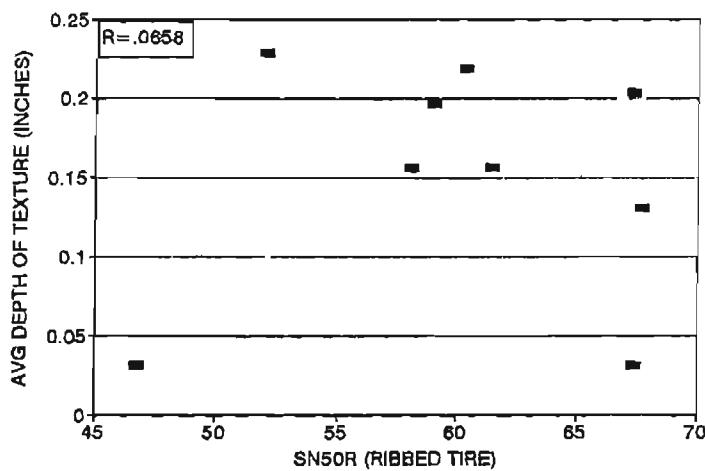


### SN65R vs. TIRE TREAD GAUGE

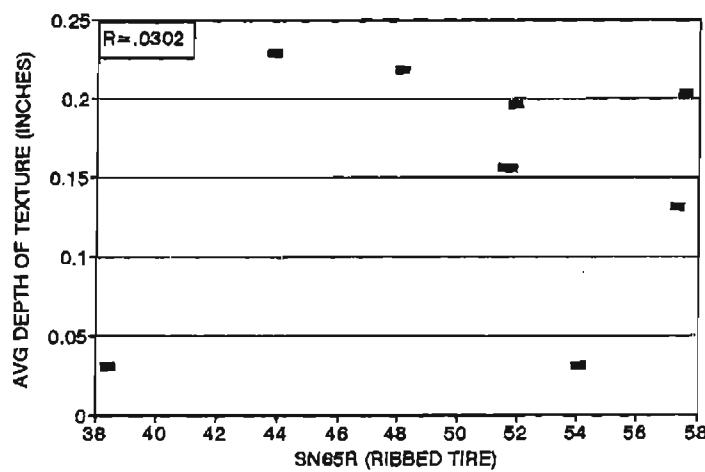


## SAND PATCH DEPTH VS TIRE TREAD GAUGE

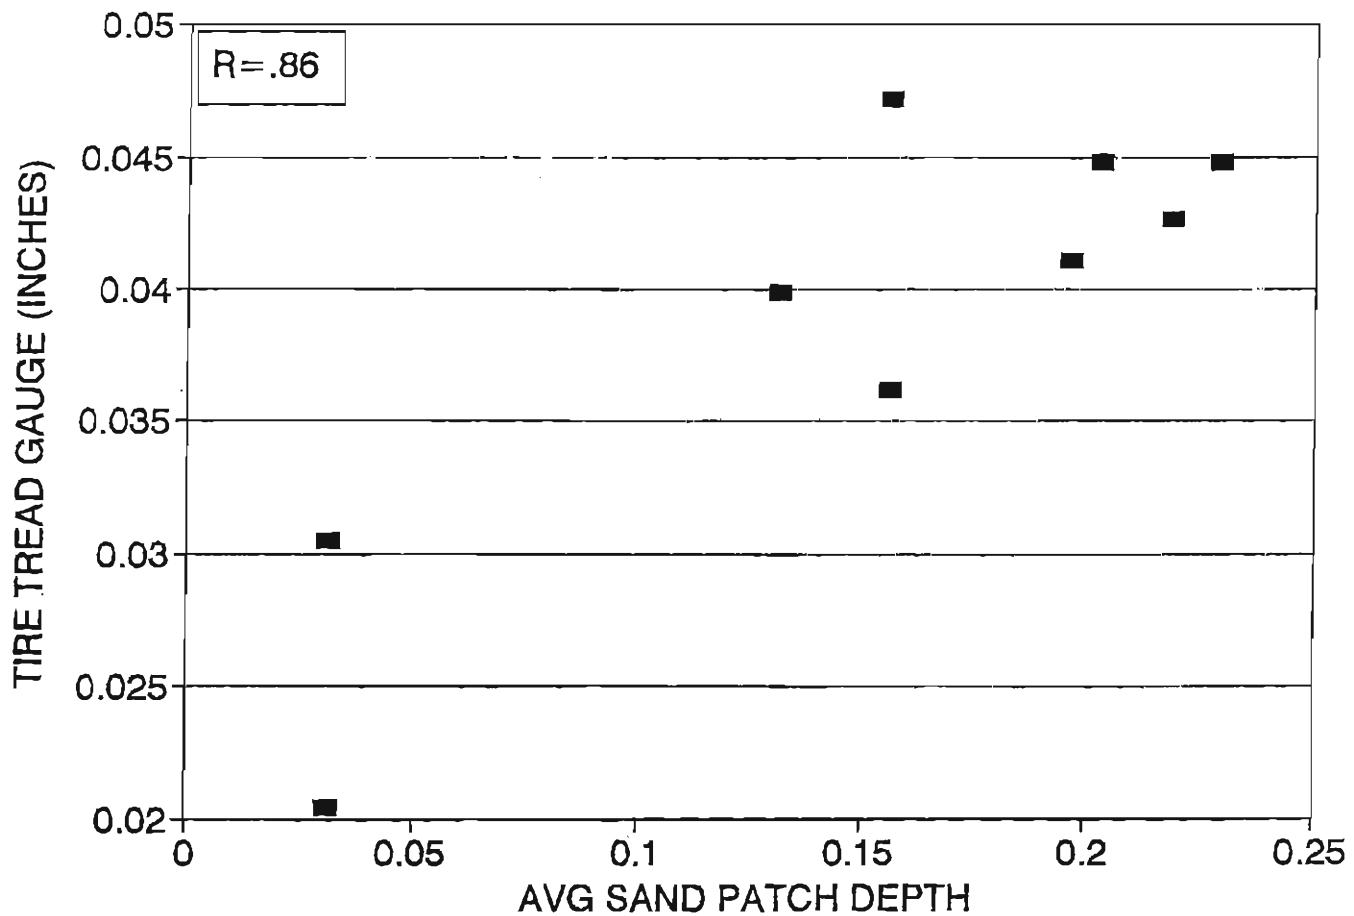


### SN40S vs LASER VAN DATA

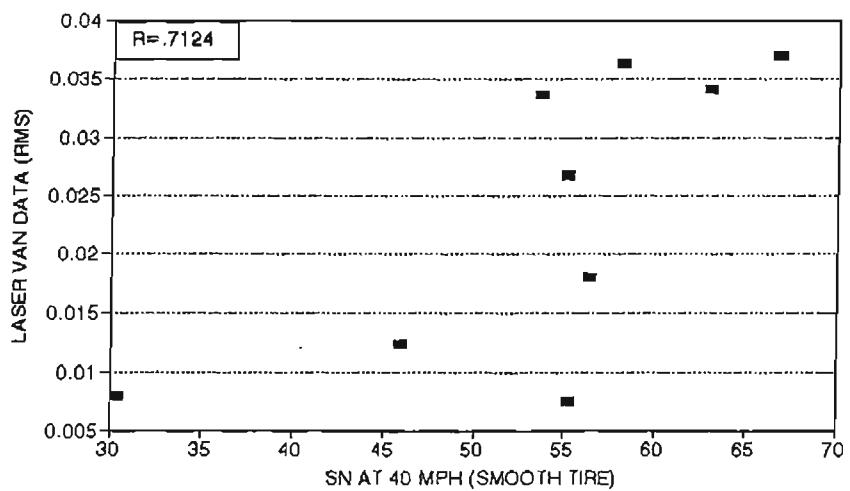


### SN50S vs LASER VAN DATA

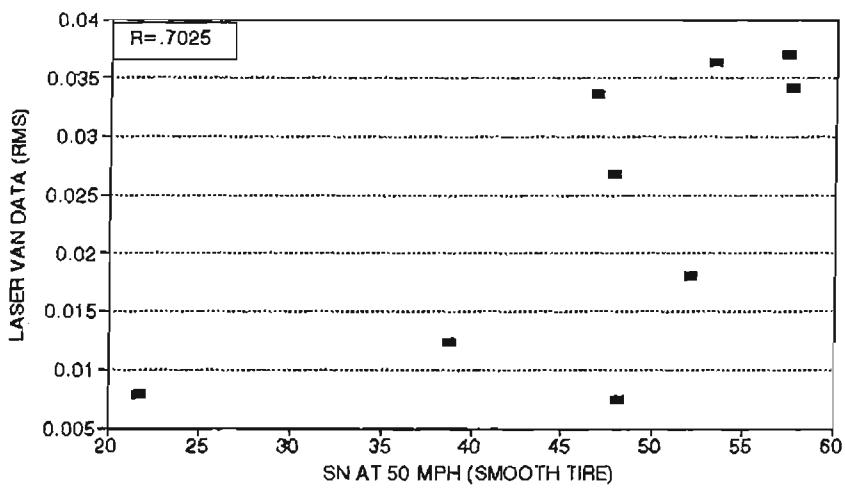


### SN65S vs LASER VAN DATA

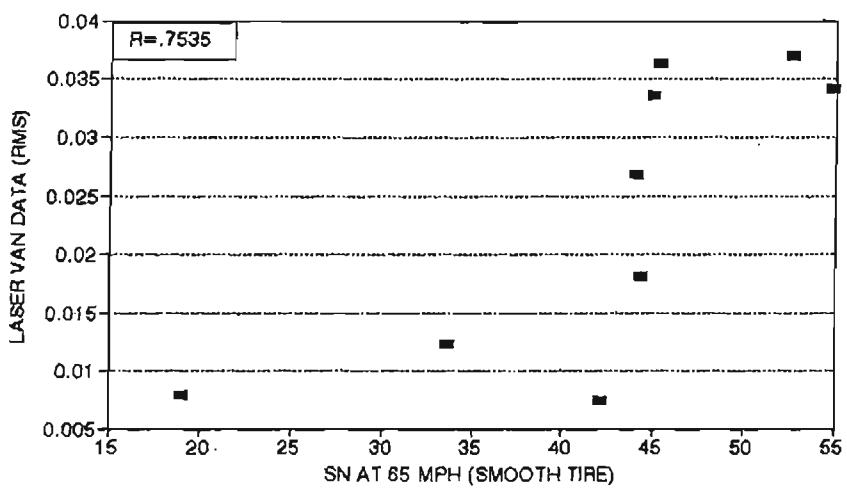


### SN40R vs LASER VAN DATA

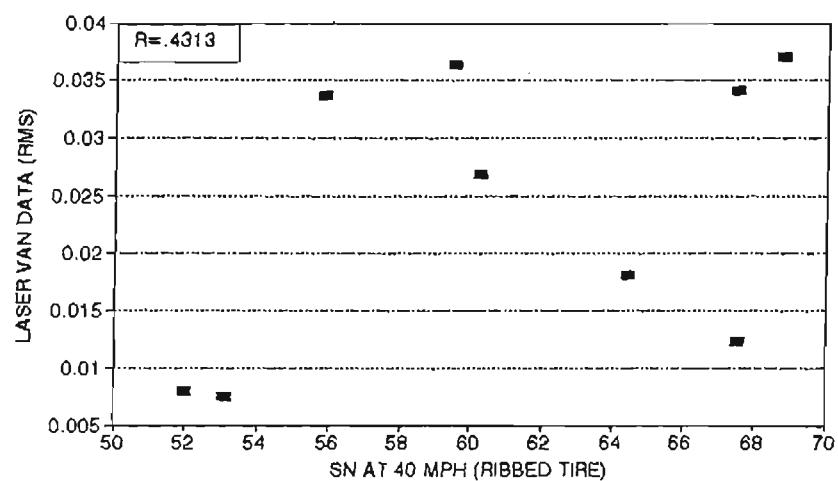


### SN50R vs LASER VAN DATA

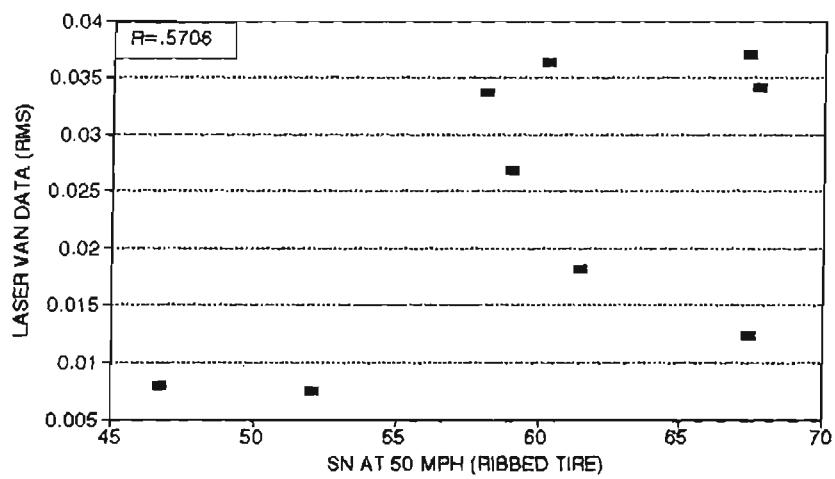


### SN65R vs LASER VAN DATA

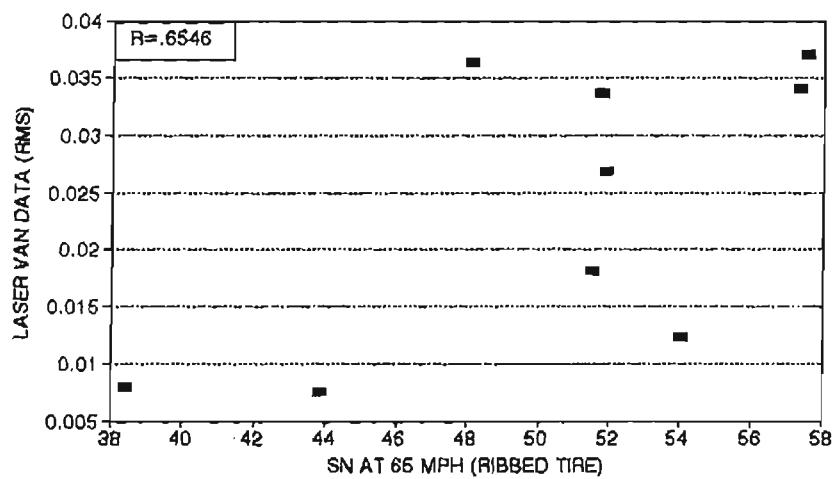


### SN40R vs. SN40S

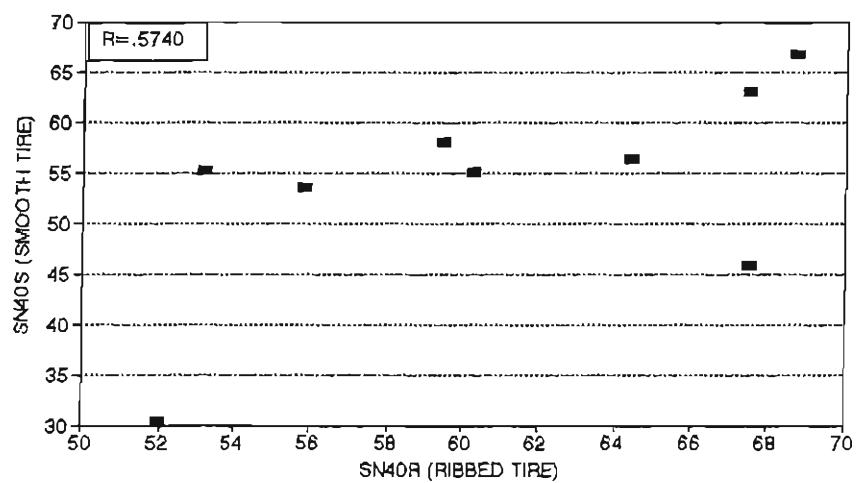

### SN50R vs. SN50S

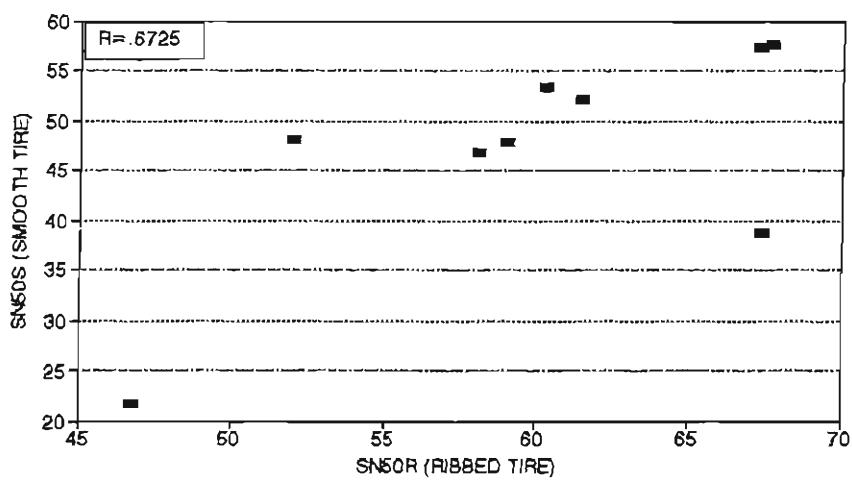


### SN65R vs. SN65S

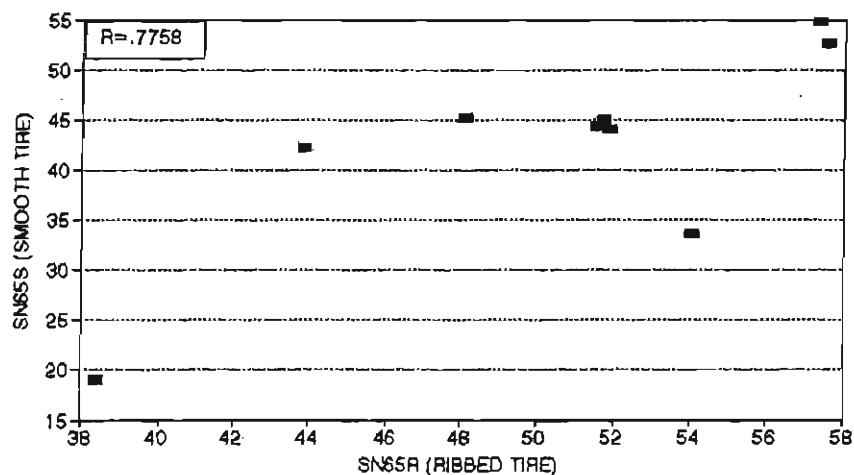


### SKID NUMBERS - 40 MPH

SMOOTH vs RIBBED TIRE

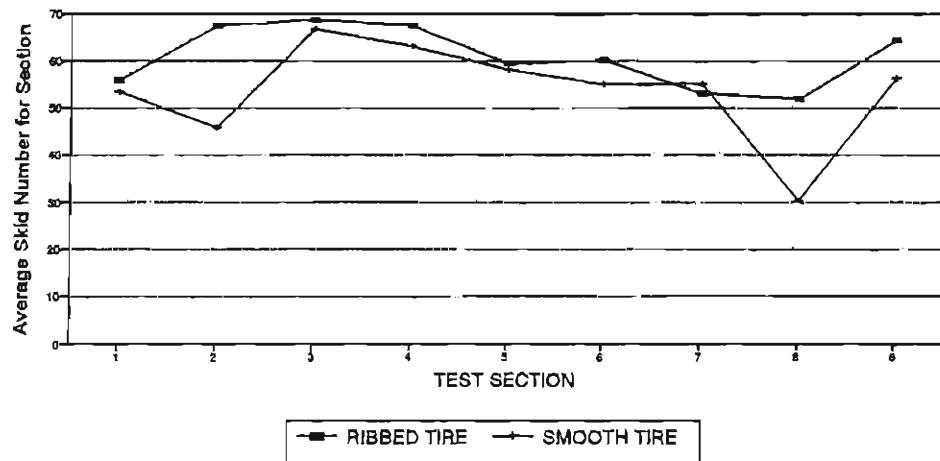


### SKID NUMBERS - 50 MPH

SMOOTH vs RIBBED TIRE

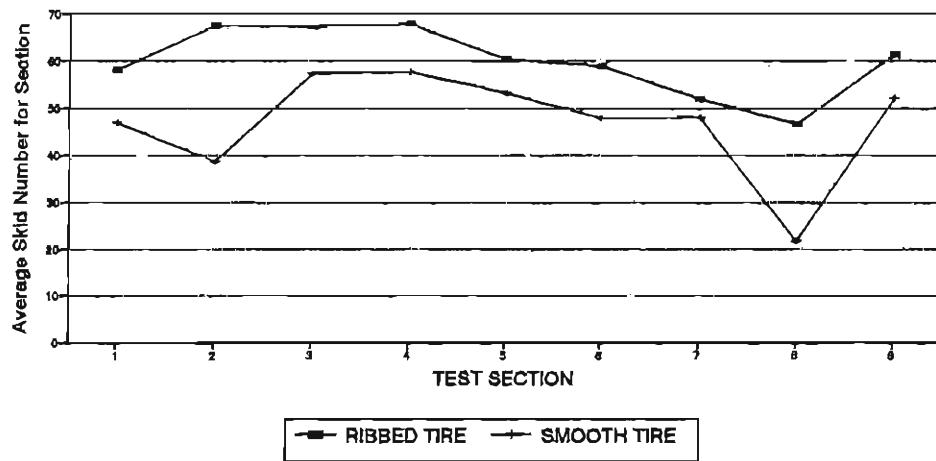

### SKID NUMBERS - 65 MPH

SMOOTH vs RIBBED TIRE

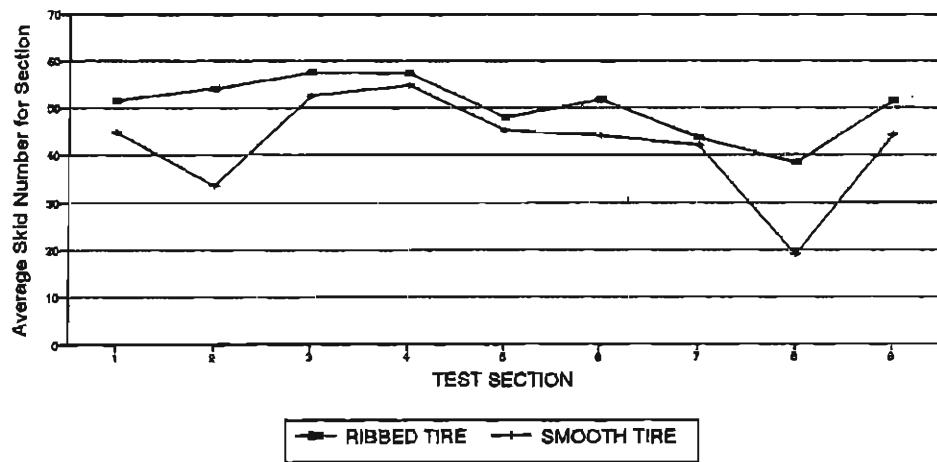


## **Appendix B**

TABLE 1: Sound Measurement Results

Location	1/3 Octave Band SPL (dB) Frequency (Hz.)																			
	100	125	160	200	250	315	400	500	630	800	1000	1250	1600	2000	2500	3150	4000	5000	dBA	
Roadside	74	73	74	76	80	75	75	77	79	81	85	81	75	71	67	62	59	56	89	
Section 1	74	73	74	75	78	74	75	77	79	81	82	78	75	71	67	62	58	56	87	
Section 2	75	75	74	75	78	74	75	77	79	81	82	78	75	71	67	62	58	56	87	
Section 3	74	75	74	76	79	79	79	81	83	83	85	79	74	69	66	61	58	55	90	
Section 4	75	73	74	74	76	75	76	78	79	81	82	79	73	69	65	60	57	55	87	
Section 5	76	73	73	75	77	75	74	74	75	80	83	80	80	72	67	62	59	56	88	
Section 6	75	72	74	75	78	74	74	75	77	81	83	80	74	71	66	61	57	55	87	
Section 7	72	70	72	71	74	71	72	74	74	79	81	75	72	66	64	59	55	52	85	
Section 8	71	69	70	72	71	71	69	72	71	74	79	74	72	69	65	60	57	53	83	
Section 9	73	72	75	74	79	76	76	77	78	83	84	77	71	68	65	60	57	55	88	
Tire	100	125	160	200	250	315	400	500	630	800	1000	1250	1600	2000	2500	3150	4000	5000	dBA	
Section 1	96	93	92	92	90	88	85	88	92	94	98	98	96	90	85	82	78	73	104	
Section 2	97	93	92	93	90	87	83	88	90	94	95	96	94	89	85	83	78	74	102	
Section 3	95	92	93	92	91	89	87	94	93	96	98	96	93	88	84	81	77	73	103	
Section 4	94	91	92	92	90	88	86	91	93	95	97	95	93	87	84	81	77	73	102	
Section 5	94	90	90	90	87	85	81	87	87	90	95	95	98	88	85	82	77	73	103	
Section 6	96	93	92	91	89	87	84	88	90	93	97	96	93	88	84	81	77	73	102	
Section 7	94	91	90	88	86	83	79	84	85	92	94	91	88	85	82	79	75	71	99	
Section 8	95	90	89	88	86	83	79	83	86	90	92	91	91	87	84	82	77	73	99	
Section 9	94	91	91	91	90	83	86	91	92	95	96	92	90	86	82	79	75	73	101	
Front Seat	100	125	160	200	250	315	400	500	630	800	1000	1250	1600	2000	2500	3150	4000	5000	dBA	
Section 1	73	70	70	84	66	65	60	59	58	58	59	56	52	48	47	46	47	48	68	
Section 2	73	70	70	63	65	64	59	58	57	57	58	54	51	48	47	47	48	67		
Section 3	74	71	71	84	68	66	60	60	58	59	59	55	51	48	47	46	48	49	68	
Section 4	76	70	70	84	67	65	59	59	58	58	58	54	50	47	47	46	48	49	68	
Section 5	73	70	68	81	64	62	57	58	55	56	57	54	52	47	47	47	49	66		
Section 6	75	71	70	63	66	64	59	58	58	57	58	55	51	48	47	47	48	49	67	
Section 7	75	69	68	61	64	62	58	57	56	56	56	53	50	47	47	47	48	49	66	
Section 8	75	69	67	61	63	62	58	56	55	56	56	53	50	48	47	47	48	49	66	
Section 9	76	70	70	84	68	66	60	60	59	58	57	53	50	48	47	47	48	49	68	
Typical Semi- *	100	125	160	200	250	315	400	500	630	800	1000	1250	1600	2000	2500	3150	4000	5000	dBA	
	74	75	78	77	73	74	80	82	89	88	93	85	82	79	76	74	72	70	96	

\* Sound measurements taken of a typical semitractor-trailer traveling west-bound. Microphone located 25 feet from centerline of the two lanes  
Truck in nearest lane.

### Front Seat SPL Measurements

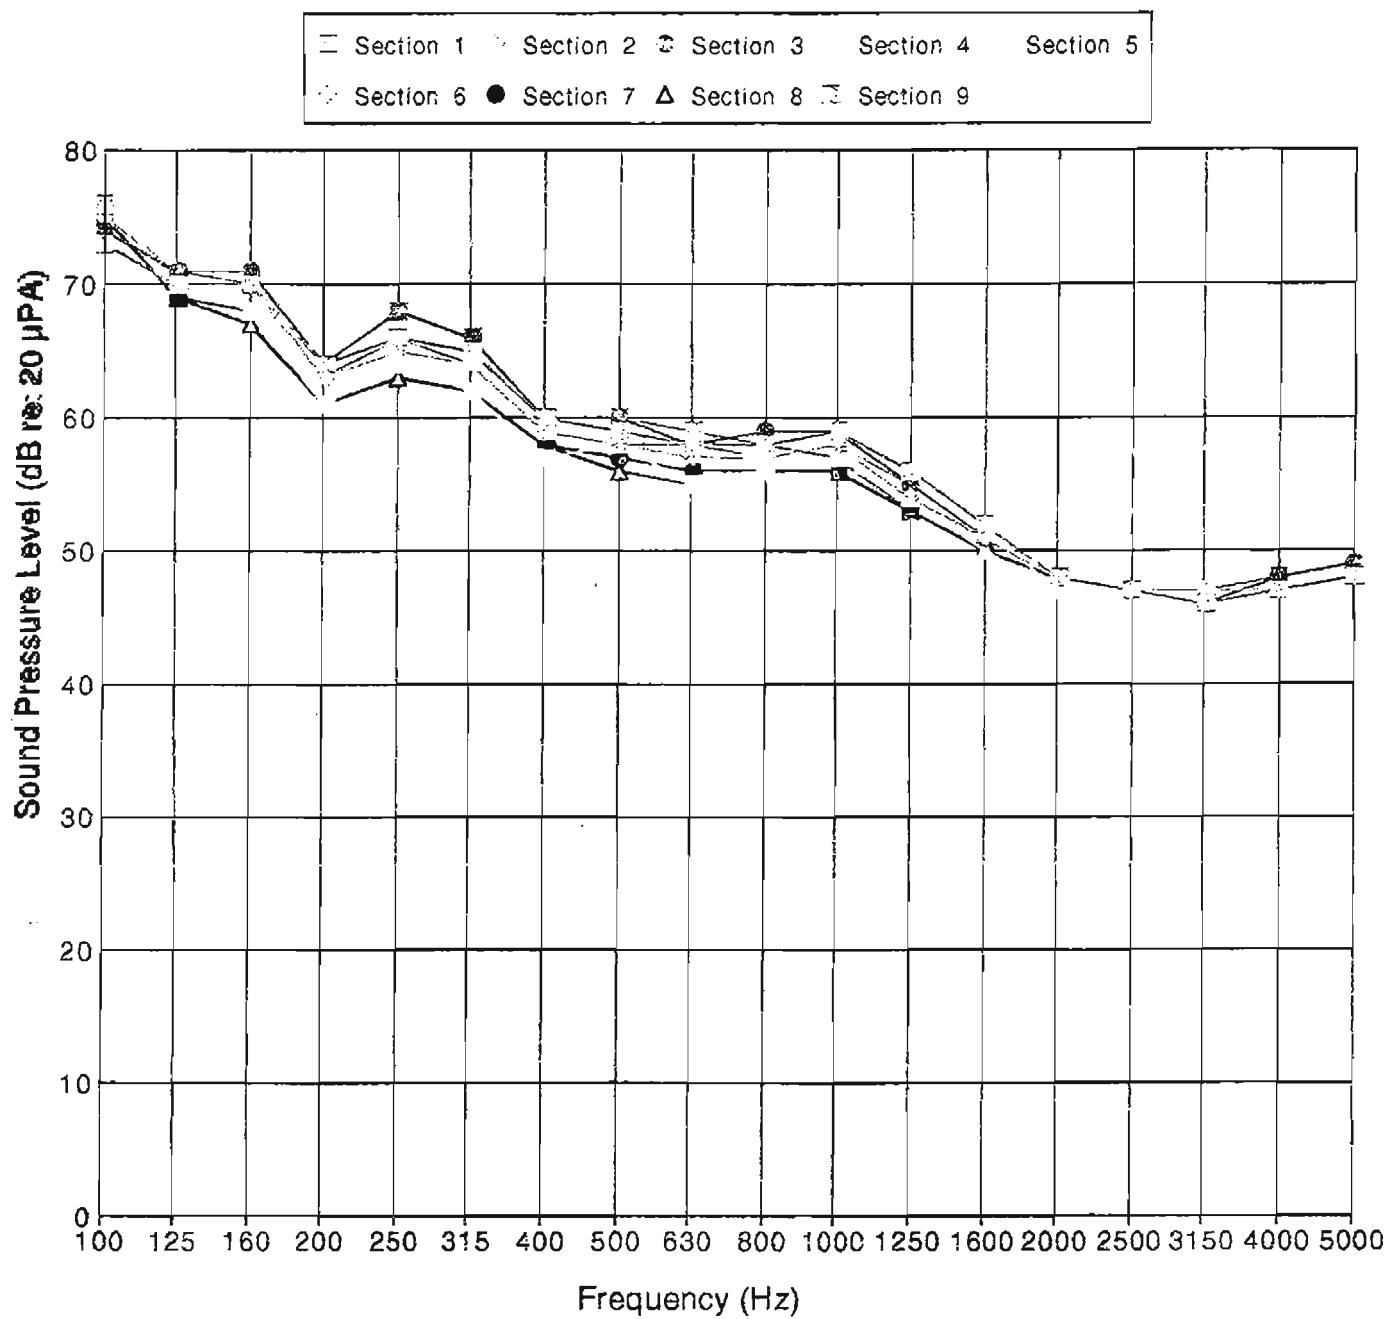


Graph No. 2: 1/3-Octave Band Sound Pressure Level Measurements

Location: Front Seat

Nov. 9, 1994 CDOT Pavement Noise Measurements DLAA Project No. 5017

### Roadside SPL Measurements

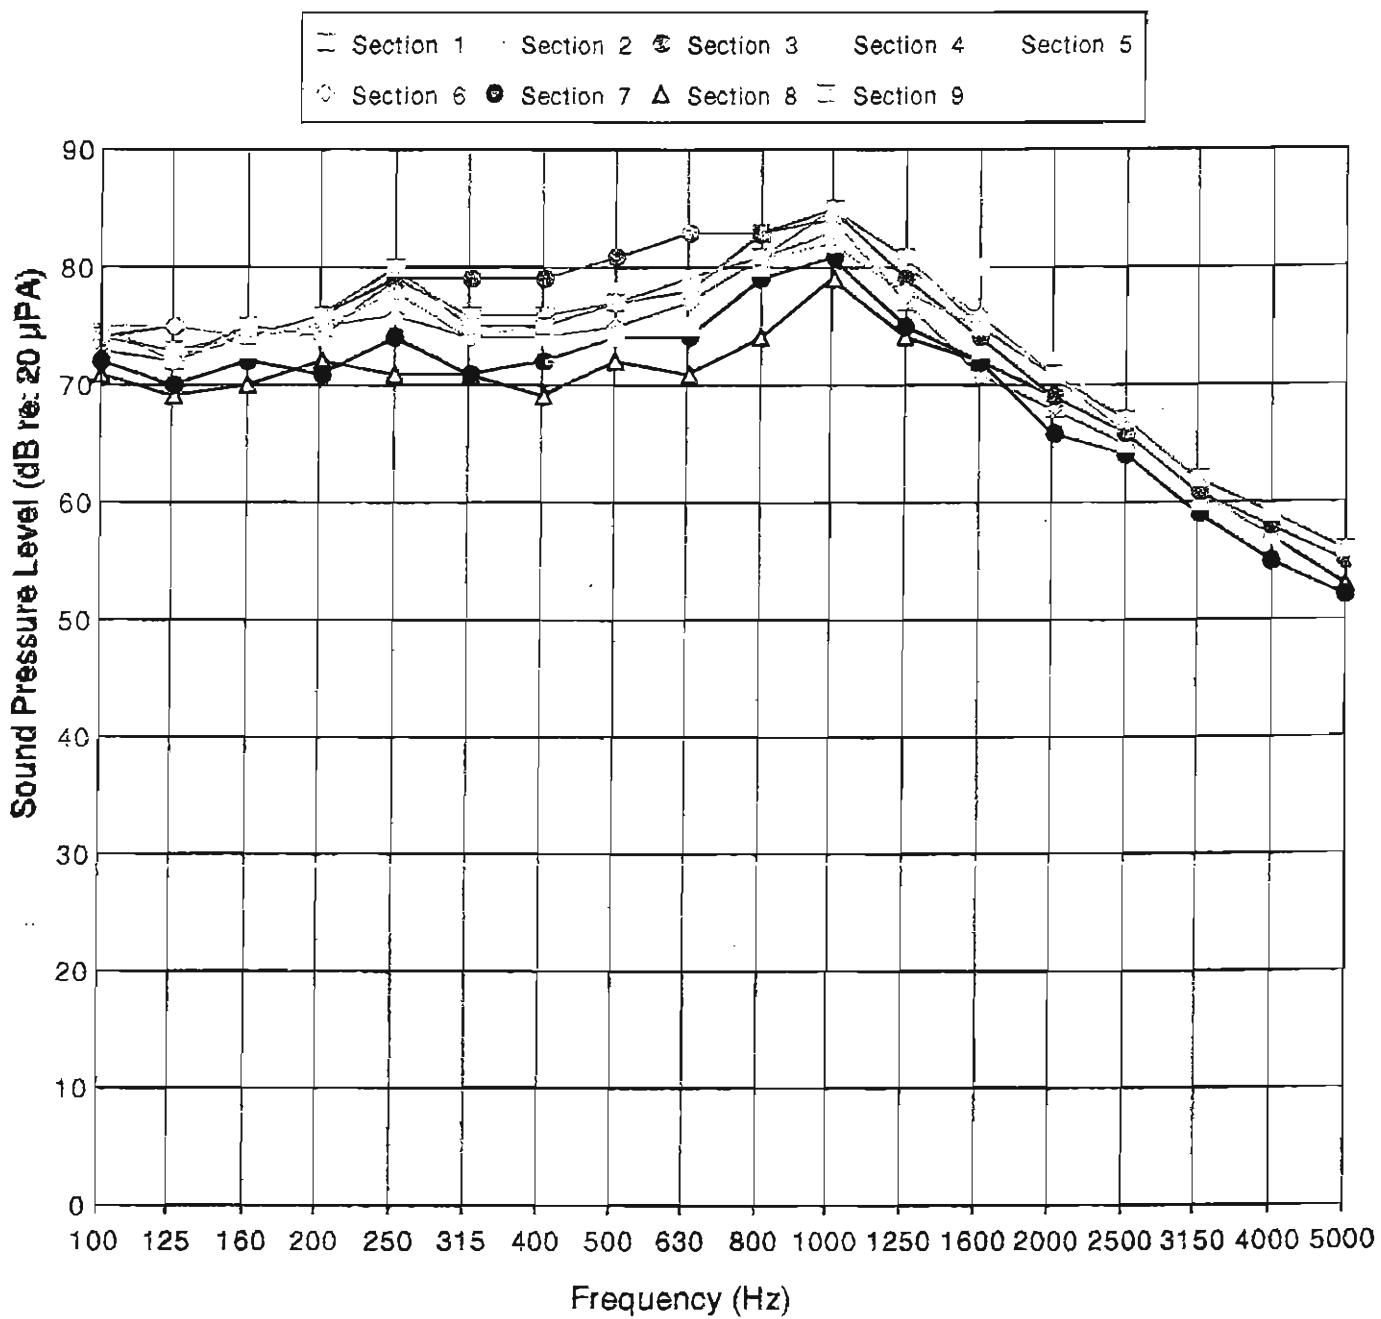


Graph No. 1: 1/3-Octave Band Sound Pressure Level Measurements

Location: Roadside

Nov. 9, 1994 CDOT Pavement Noise Measurements DLAA Project No. 5017

### Tire SPL Measurements

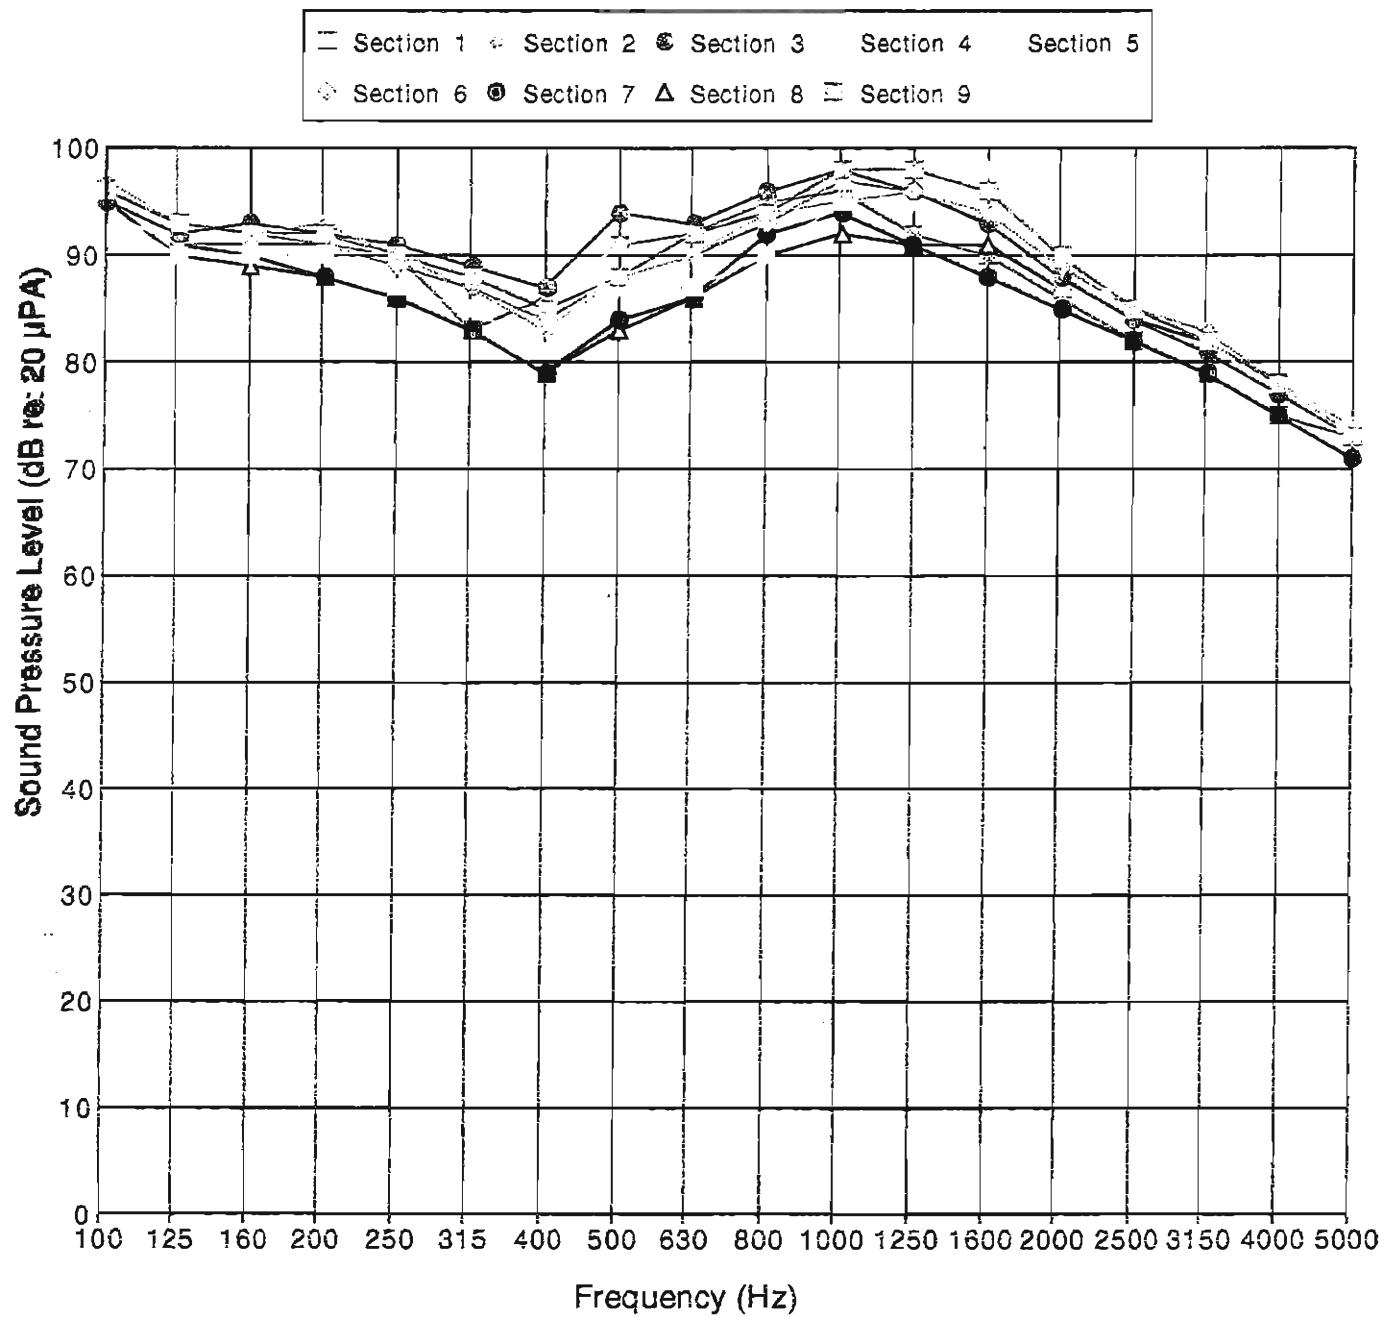


Graph No. 3: 1/3-Octave Band Sound Pressure Level Measurements


Location: Near Tire

Nov. 9, 1994 CDOT Pavement Noise Measurements DLAA Project No. 5017


### SOUND vs. SN40S

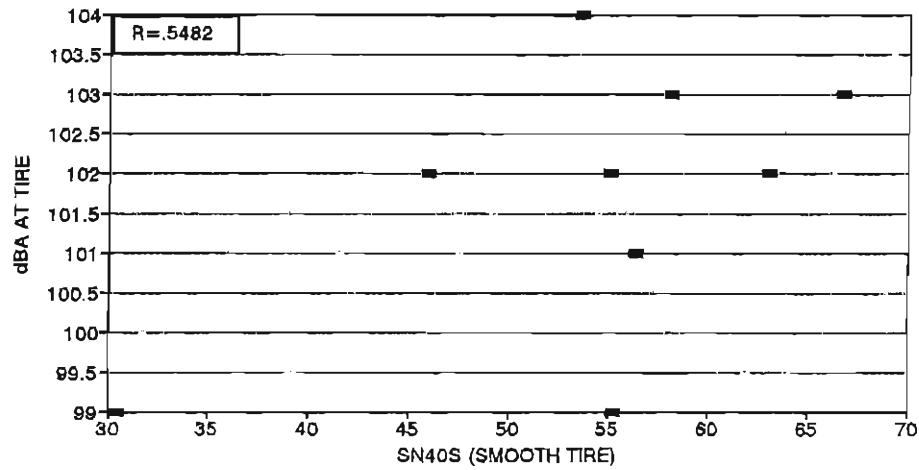


### SOUND vs. SN50S

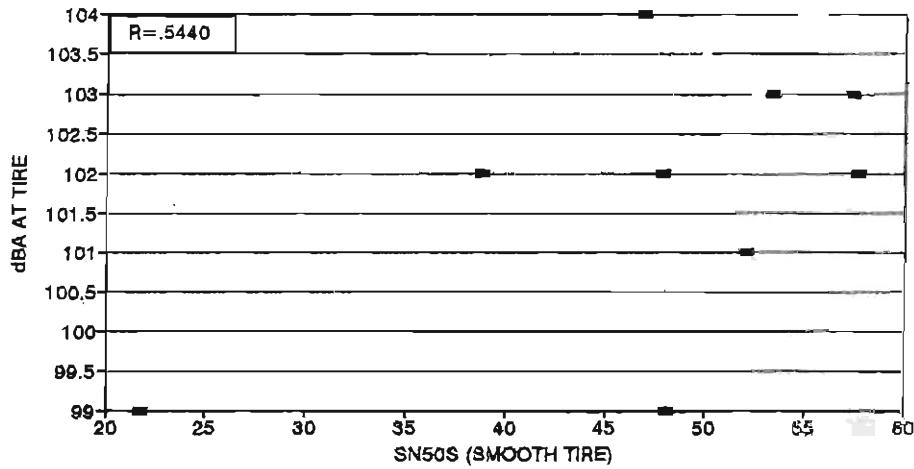


### SOUND vs. SN65S

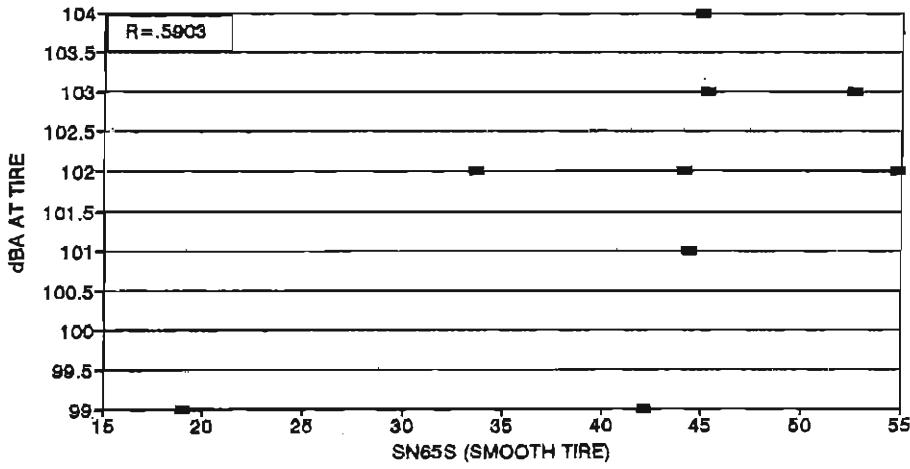


### SOUND vs. SN40R

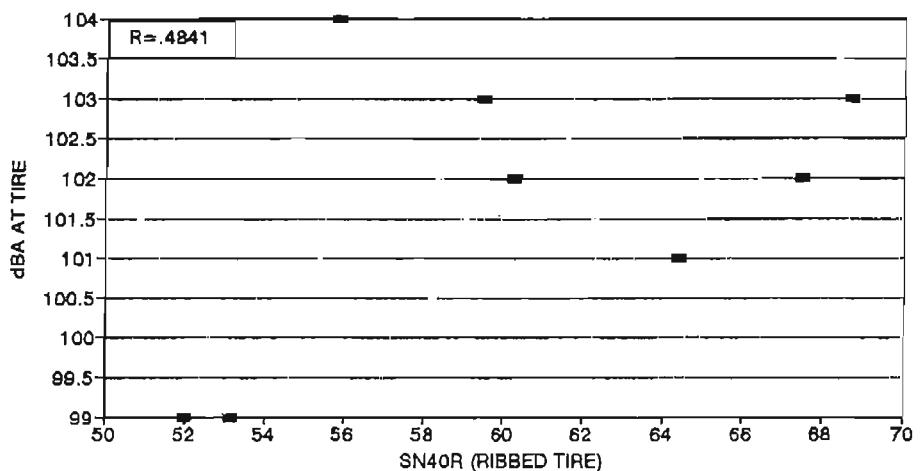

### SOUND vs. SN50R

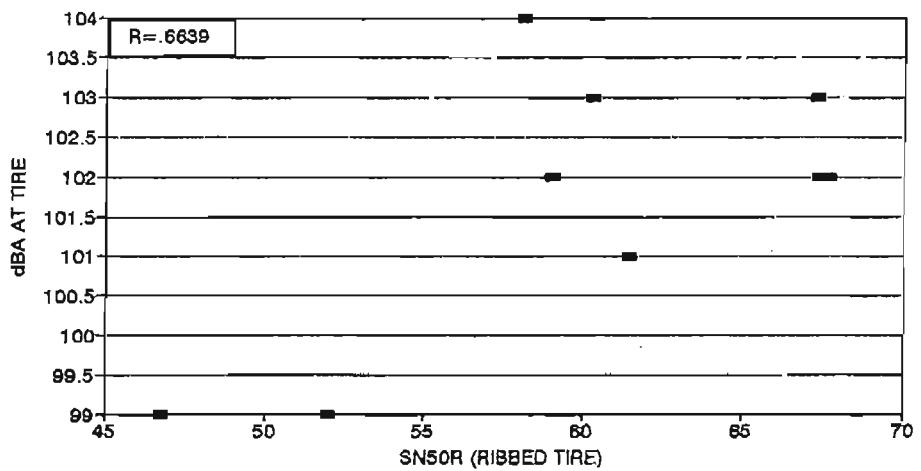

### SOUND vs. SN65R

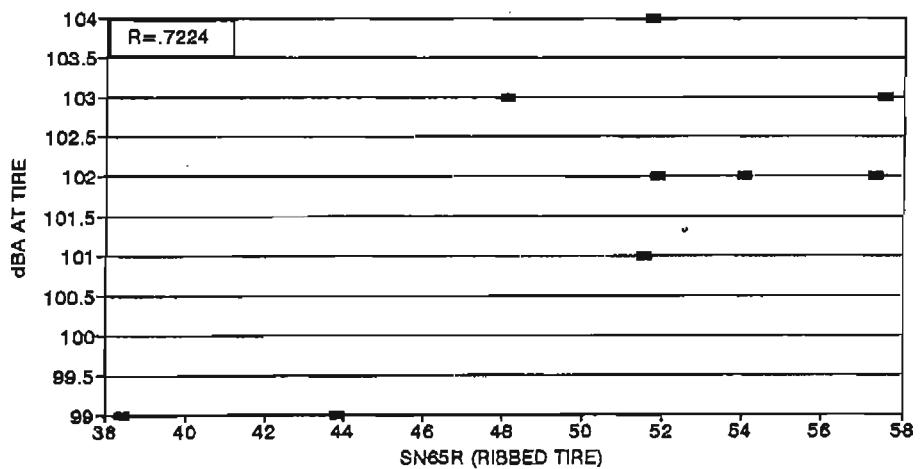

## **Appendix C**

**CHEMICAL AND PHYSICAL ANALYSES OF FLY ASH**

---

TICKET NUMBER: 7717-17993 Job Number: 7717 REPORT DATE: 11/22/93

REPORT TO: Pozzolanic International  
7525 SE 24th St.  
Suite 630  
Mercer Island , WA 98040


POINT OF ORIGIN : Jim Bridger  
SAMPLE ID : 18-93  
TICKETS : T.R. 8420-8557 R.R. 5760-5999  
DATE SAMPLED : 09/30/93 - ASTM: C 618-92A  
DATE RECEIVED : 10/12/93 SPECIFICATIONS


CHEMICAL COMPOSITION (%):	CLASS F	CLASS C
Silicon Dioxide	62.22	
Aluminum Oxide	18.62	
Iron Oxide	4.71	
* * * Total	85.55	70.0 Min
Sulfur Trioxide	0.25	5.0 Max
Calcium Oxide	5.73	5.0 Max
Moisture Content	0.05	3.0 Max
Loss on Ignition	0.25	6.0 Max

**PHYSICAL TEST RESULTS:**

Fineness					
Retained on #325 sieve, (%)	27.29	34	Max	34	Max
Strength Activity Index					
With Portland Cement (%)					
Ratio to Control @ 7 days	82.1				
Ratio to Control @ 28 days	96.6	75	Min	75	Min
Pozzolanic Activity Index					
With Lime @ 7 days (psi)	1040.0				
Water Requirement, % of Control	99.6	105	Max	105	Max
Soundness					
Autoclave Expansion (%)	-0.016	0.8	Max	0.8	Max
Specific Gravity	2.32				

COMMENTS:

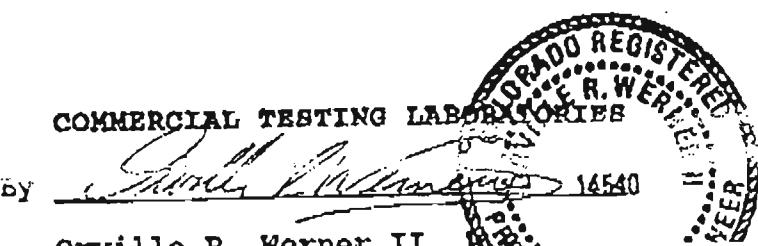

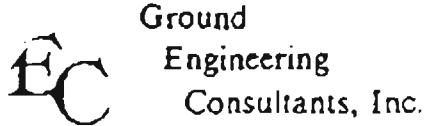

March 17, 1994

Subject: Laboratory Test Results, Concrete  
Mix Designs, DeerTrail Project

Job No. 94-150

Interstate Highway Construction  
7135 South Tucson Way  
P.O. Box 4356  
Englewood, CO 80155  
Airport Field Office

Attention: Mr. Cal Thomas

Gentlemen:

We have summarized results of laboratory tests performed to date on aggregates delivered to our laboratory for the Deertrail concrete mix designs.

Coarse Aggregate:

Gradation:

Sieve Size or No.	Percent Passing
1-1/2"	100
1"	100
3/4"	81
1/2"	38
3/8"	17
No. 4	1.6
No. 8	1.2

Moisture content of pile (delivered) - 5.0%

Specific Gravity (SSD basis) - 2.630

Absorption - 0.89%

Los Angeles Abrasion - 41.3% loss

Fine Aggregate:

## Gradation:

Sieve Size or No.	Percent Passing
3/8"	100
No. 4	100
No. 8	95
No. 16	78
No. 30	47
No. 50	14
No. 100	3.2
No. 200	1.6

Moisture content of pile (delivered) - 7.0%

Specific Gravity (SSD basis) - 2.608

Absorption - 2.31%

Fineness Modulus - 2.63

Sand Equivalent Value - 85

We have also attached mix data for Mix Designs 1, 2 and 3. Compressive and flexural strength test results will be updated as additional values are determined. The tests were completed in accordance with accepted ASTM and AASHTO test procedures. If you have any questions, please do not hesitate to contact our office.

Sincerely,

GROUND ENGINEER CONSULTANTS, INC.

James B. Kowalsky, PE  
27680  
1/1/94

The seal is circular with a decorative border containing the text "PROFESSIONAL ENGINEER" at the top and "COLORADO REGISTERED" at the bottom. In the center, it features "JAMES B. KOWALSKY" above the registration number "27680". Below the number is the date "1/1/94".

**Mix No. 1**BATCH MIXTURE

<u>Item</u>	<u>Description</u>	<u>Weight lbs / Cubic Yard</u>
Cement	Holman III, L.A.	565
Fly Ash	Brigger Pozzolanic, F	113
Coarse Aggregate	Cooley No. 57, Brighton	1586
Fine Aggregate	T&W, Byers	1215
Air Entraining Admixture	Masterbuilders Paveair	10.3 oz
Water	-	287

94035

Physical Properties

Slump	1.5 inches
Air Content	5.9 %
Temperature	62 deg F
Unit Weight	139.9pcf
Relative Yield	0.9972

Compressive Strength

(psi)

	3 days	7 Days	14 Days	28 Days
	3220	4810	5840	
	3090	5040	6080	

Average Strength      3155      4925      5960  
(psi)Flexural Strength

(psi)

	3 days	7 Days	14 Days	28 Days
	480	600	675	
	520	580	660	

Average Strength      500      590      670  
(psi)

HOLNAM INC

IB-106-1-B

Silo Test Certificate  
Average of Test Results

Consignee: I.H.C  
Deer Trail  
East I 70

Car or Truck No. \_\_\_\_\_  
Date Shipped \_\_\_\_\_  
Quantity \_\_\_\_\_

PORLAND CEMENT — Type I-II LA FEDERAL SPECIFICATION

A.S.T.M. DESIGNATION C-150

	Percent
1. Chemical Composition	21.2
Silicon Dioxide (SiO <sub>2</sub> )	4.7
Aluminum Oxide (Al <sub>2</sub> O <sub>3</sub> )	3.2
Ferric Oxide (Fe <sub>2</sub> O <sub>3</sub> )	64.7
Calcium Oxide (CaO)	1.3
Magnesium Oxide (MgO)	2.6
Sulfur Trioxide (SO <sub>3</sub> )	1.4
Loss on Ignition	0.2
Insoluble Residue	5.8
Tricalcium Silicate (C <sub>3</sub> S)	17
Dicalcium Silicate (C <sub>2</sub> S)	7.0
Tricalcium Aluminate (C <sub>3</sub> A)	10
Tetracalcium Aluminoferrite (C <sub>4</sub> AF)	0.29
Alkalies (Na <sub>2</sub> O Equivalent)	400
2. Specific Surface	0.00 %
Elaine, Sq. M. PER Kg	0.00 %
Wagner, Sq. M. PER Kg	0.00 %
3. Soundness	Autoclave Expansion
4. Time of Setting	Vicat, Initial Set      1      Mrs.      30      Mins.
	Vicat, Final Set      4      Mrs.      0.5      Mins.
5. Compressive Strength Tests	1 Day      1 lbs. per Sq. In. 3 Days      3810      1 lbs. per Sq. In. 7 Days      4780      1 lbs. per Sq. In.
6. Air Entrainment	% by Volume      5.8

HOLNAM INC is warranted to conform at the time of shipment with the specification designated above. No other warranty is made or to be implied. Having no control over the use of its cements, HOLNAM does not guarantee finished work.

HOLNAM INC

Portland, Colorado \_\_\_\_\_ Pland

.: November 18, 1994

.: A.G. Peterson

FROM: Jay Goldbaum

SUBJECT: Carbonate sand in PCCP

In order to determine the susceptibility of the sand to polish in project number IR(CX) 070-4(153), Deertrail - East, ASTM test number D 3042 was performed. The test uses a hydrochloric acid solution to dissolve the carbonates in a sample.

According to some research performed, a higher amount of carbonic materials found represents a higher possibility of polishing and/or a loss in friction of the pavement surfaces. The maximum amount of carbonates allowed in PCCP is 25 percent.

After performing ASTM test D 3042 on the sand used in the PCCP at Deertrail, it was found to have 0.42 percent carbonates.

IR(CX) 70-4(153)												
Desertall - EAST												
Class F Results												
Test #	3 Day		7 Day		14 Day		28 Day		260 Day		28 DAY	
	Compressive Strength	Average	Tensile Strength	Average	Required Strength	Average						
EBL												
61	3030	3040	3035	4660	4630	4645	4960	5230	5105	5510	5570	5240
62	3860	4020	3840	4340	4580	4450	4750	4730	4740	5490	5860	5480
63	3310	3350	3330	4320	3970	4145	4120	4610	4365	5430	5280	5330
64	3310	3370	3340	3760	3890	3875	4070	4510	4280	5250	6150	6030
65	2960	2850	2905	3680	3550	3615	3980	3930	3955	4800	4680	4490
66				3590	3570	3580				4580	4530	4440
IAT-86										4660	4720	4485
67				3750	3660	3705				4670	4620	4612
68	3410	3350	3380							4620	4720	4813
69	3310	3210	3260							5220	5050	5530
70	3500	3570	3535	3520	4340	3830				4880	5110	5210
71	3410	3330	3370	4200	4290	4245				5380	5010	4800
IAT-71											5480	5520
72	3280	3310	3300	4080	4120	4080				5050	5450	5130
73	2850	2880	2915	3230	3250	3240				4760	4850	4410
74	2890	2540	2615	3520	3130	3325				4770	4310	4470
75	3230	3610	3420	4540	4550	4545				6240	6210	5250
76										5800	6210	5940
77										4880	5290	4840
78				3460	3680	3570				4880	5090	4420
79										5720	5700	5520
80										5300	5310	5650
81										5430	5450	5190
82				4220	4160	4180				5210	5850	5620
83										5720	5850	5730
84										4720	5210	5030
85										4930	4960	4880
86				4520	4290	4405				5650	5110	5640
87										5360	5300	5140
IAT-87										5430	5220	5325
88										5310	5370	5620
89										5120	4740	4680
90				4180	4260	4225				5290	5880	5370
91										5420	5240	5060
92										4800	4700	4690
93										5410	5380	5850
94				4480	4500	4490				5280	5350	5310
95										5310	5380	5300
96										4700	4830	5080
97				3330	3360	3345				4020	4230	4040
98				4340	3930	4135				5000	4990	4840
99										4360	4550	4610
100				3730	3700	3715				4280	4200	4580
101										4536	4960	4770
102										4400	4270	4250
103				4200	4340	4270				5180	5230	5110
104										4140	4540	4880
105				3340	3700	3520				4340	4220	4340
106										4570	4580	4200
107										5470	5240	4600
108										5080	5360	5180
109				3520	3630	3575				4180	4470	4510
110										4630	4530	4640
111				4580	4610	4585				5190	5580	4930
IAT-111										5790	5800	5775
112										5580	5530	5380
113										5390	6040	5070
114										4890	4880	4840
115				4480	4530	4510				5720	5640	5440
116										4880	4480	4540
117										5420	5360	5670
118										4740	4420	4810
119				4480	4530	4505				5200	5170	5270
120										5220	5350	5040
IAT-120										5260	5230	5245
121										4790	4680	4700
122										4350	4390	4300
123				4590	4820	4805				5170	5540	4890
124										4440	5440	5200
125										5180	5040	5370
126										3850	3940	3910
										3800	385	370
										383	510	575
											543	543
Average (EB & WB)	3257		4039		4451		4988					613
Std. Devt. (EB & WB)	325.2		320		426		564.1					59.9
Max. Value (EB & WB)	4020		6270		5230		6370					725
Min. Value (EB & WB)	2540		2800		3930		2360					510
Number of tests (EB & WB)	26		70		10		402					24
							4942					

11-Oct-84

IR(CX) 70-4(153)

Deertrail - EAST

Class P Results

Test#	3 Day		7 Day		14 Day		28 Day		28 Day		28 DAY	
	Compressive Strength	Average	Tensile Strength	Average	Flexural Strength	Average						
WBL												
1		4120	4210	4185			4590	5270	5340	5200		
2		3990	4130	4060			5090	5480	5170	5247		
3		3870	4130	4000			4760	4960	5060	4927		
4							3580	2990	3610	3393		
5		6270	2800	4535			4100	4010	4420	4177		
6		3470	3630	3550			4350	4350		4350		
7		4230	3510	3870			5300	5240		5270		
IAT-7							5300	5240		5270		
8		4000	4250	4125			2520	2360	2560	2480		
9							5220	4860	5260	5113		
10							5480	5240	5600	5440		
10a							5243	5480	5398	5440		
11							5336	5251	4928	5172		
11a							5020	4940	4630	4863		
12							6008	5936	6061	6002		
12a							6010	5940	6060	6003		
13							5100	4870	5210	5060		
14							5640	5530	5440	5537		
15							5780	5830	5110	5573		
16							4830	4720	4600	4717		
17							5140	5180	5250	5190		
18							4880	5270	4940	5033		
19							5060	4780	5080	4973		
20							5230	5510	5010	5250		
21							5240	3320	5370	4643		
22							5900	5950	6370	6073	498	400
IAT-22							6250	5830		6040		
23							5170	5110	3890	4723		
24							5170	5330	5250	5250		
25							5320	5370	5330	5340		
26							4930	4700	5020	4883		
27							5080	5620	5380	5353		
28							4680	4660	4410	4583		
29							3800	3950	3660	3807		
30							5630	5620	5970	5740		
IAT-31							4860	5130		4995		
31							5120	5150	5280	5183		
32							5110	5230	5320	5220		
33							5200	5220	5060	5160		
34							5060	5160	5680	5300	497	478
35							5010	4760	4290	4687		
36							5220	4740	5210	5057		
37							5240	5230	5080	5187		
38							5100	4990	5380	5157		
39							5110	5340	5080	5177		
IAT-40							4730	4730		4730		
40							4770	4740	4950	4820		
41							5260	5670	5660	5530	460	444
42							5480	5190	4850	5173		
43							4730	4740	4970	4813		
44							4660	5020	4740	4883		
45							4230	4170	4200	4200	339	335
46							4510	4240	4710	4487		
47							5080	5370	5175	5208		
48							4800	5100	4970	4990		
49							3470	3870	3860	3867		
50							4890	4840		4915		
51							4800	4610	4520	4643		
52							4080	4020	4060	4053	335	340
53							5340	4630	5370	5113		
54							5690	4890	5240	5073		
55							4450	4770	4790	4670		
56							4780	4730	4630	4713		
57							5050	5450	5270	5257		
58							3980	3830	4010	3967		
59							5030	5010	4790	4943	439	436
60							4170	4000	4310	4180		